

[Co(NH₃)₅(NO₃)](NO₃)₂ as an energetic coordination precursor for the preparation of Co₃O₄ nanoparticles at low temperature

Saeed Farhadi*; Gholamali Nadri; Masoumeh Javanmard

Department of Chemistry, Lorestan University, Khoramabad 68135-465, Iran

Received 28 January 2016;

revised 27 April 2016;

accepted 02 June 2016;

available online 03 July 2016

Abstract

In this paper, an energetic coordination compound namely pentamminenitratocobalt(III) nitrate, [Co(NH₃)₅(NO₃)](NO₃)₂, was used as a new precursor for the preparation of Co₃O₄ nanoparticles. The results showed that the complex is easily decomposed into the Co₃O₄ nanoparticles at low temperature (200 °C) without employing a surfactant or solvent and any complicated equipment. The product was characterized by differential scanning calorimetry (DSC), X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FT-IR), transmission electron microscopy (TEM) and energy-dispersive X-ray spectroscopy (EDX). Optical and magnetic properties of the product were studied by UV-visible (UV-vis) spectroscopy and a vibrating sample magnetometer (VSM), respectively. FT-IR, XRD and EDS analyses confirmed the formation of highly pure spinel-type Co₃O₄ phase with cubic structure. TEM images showed that the Co₃O₄ nanoparticles are approximately in the range of 10 to 24 nm with a mean size of around 17 nm. The optical spectrum of the Co₃O₄ nanoparticles revealed the presence of two band gaps at 3.45 and 2.20 eV which are blue-shifted relative to reported values for the bulk sample. The magnetic measurement of the product showed a weak ferromagnetic order at room temperature.

Keywords: Co₃O₄ nanoparticles; Energetic complexes; Ferromagnetic order; Pentamminecobalt(III) complex; Thermolysis method; Transition metal oxides.

How to cite this article

Farhadi S, Nadri Gh, Javanmard M. [Co(NH₃)₅(NO₃)](NO₃)₂ as an energetic coordination precursor for the preparation of Co₃O₄ nanoparticles at low temperature. *Int. J. Nano Dimens.*, 2016; 7(3): 201-207., DOI: [10.7508/ijnd.2016.03.03](https://doi.org/10.7508/ijnd.2016.03.03).

INTRODUCTION

Nanostructured metal oxides have attracted great interest in recent years not only for their unique physical and chemical properties that significantly differ from those of corresponding bulk materials but also for wide range of their applications [1]. Among these oxides, spinel-type cobalt oxide (Co₃O₄), as a p-type semiconductor, has potential applications in gas sensors, heterogeneous catalysts, electrochemical devices, Li-ion batteries, magnetic materials and photocatalysts [2-11]. In recent years, the increasing interest has been focused on the synthesis of Co₃O₄ nanostructures with unique sizes and specific shapes because of the influences of particle size on their properties and applications. Various wet-chemical methods such as hydro-/solvothermal method, combustion method, microwave heating, sol-gel process, spray pyrolysis, sonochemical method, coprecipitation, ionic liquid-assisted method, polyol

*Corresponding Author Email: sfarhadi1348@yahoo.com

method and a non-aqueous route have been reported to synthesize Co₃O₄ nanostructures [12-37]. Nevertheless, most of these methods involve complex processes, high calcination temperatures, and expensive and toxic precursors. In addition to these, they are either time consuming or require expensive instruments.

Over the past several years, the use of transition metal coordination compounds as precursors to prepare metal oxide nanostructures has received much attention. This simple method offers several unique advantages and significant merits over other methods, including easy workup, short reaction time, and the preparation of various inorganic nanomaterials with unique sizes, specific shapes and with narrow size distribution. Several coordination compounds have been used to synthesize Co₃O₄ nanostructures [38-43]. Recently, we have found that easily degradable and energetic coordination compounds composed of reducible

ligands and oxidizing anions such as $[\text{Ni}(\text{NH}_3)_6](\text{NO}_3)_2$, $[\text{Co}(\text{NH}_3)_5(\text{CO}_3)](\text{NO}_3)_2$, $[\text{Co}(\text{NH}_3)_6](\text{NO}_3)_3$ can be appropriate precursors to synthesize the metal oxides nanostructures at low temperature [44-46].

In the present work, we wish to report on the direct thermolysis of a well-known energetic pentamminecobalt(III) complex, $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ which has been resulted in Co_3O_4 nanoparticles at low temperature (200°C). The resulting product was characterized by differential scanning calorimetry (DSC), X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FT-IR), energy-dispersive X-ray spectroscopy (EDS), transmission electron microscopy (TEM), UV-visible spectroscopy, and magnetic measurement. The method is a fast, energy-efficient and environmentally friendly route to produce Co_3O_4 nanoparticles in only one step.

EXPERIMENTAL

Materials and characterization techniques

All materials were purchased from Merck Company with high purity. The precursor complex, $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ was synthesized according to the literature method [47]. The thermal behavior of the precursor complex was studied using a Netzsch STA 409 DSC analyser at a heating rate of 5°C min^{-1} in air. The composition and phase purity of the Co_3O_4 nanoparticles were characterized by a Rigaku D/max C III X-ray diffractometer using Ni-filtered $\text{Cu K}\alpha$ radiation ($\lambda = 1.5406 \text{ \AA}$). XRD patterns were recorded in the 2θ range of 10° – 80° with a scanning step of 0.04° . To investigate chemical bonding of the products, infrared spectra were recorded on the diluted samples in KBr pellets using a Shimadzu 160 FT-IR spectrophotometer in the region 4000 – 400 cm^{-1} . The optical absorption spectrum was recorded on a Shimadzu 1650PC UV-vis spectrophotometer in the 200 – 700 nm wavelength range at room temperature. The samples for UV-vis studies were well dispersed in distilled water by sonication for 30 min to form a homogeneous suspension. Particle sizes were determined with a Zeiss EM900 transmission electron microscope operating at 50 kV and equipped with an energy dispersive X-ray spectroscopy. The TEM sample was prepared by dispersing the powder in ethanol by ultrasonic vibration. The magnetic properties of Co_3O_4 nanoparticles were measured using a vibrating sample magnetometer (VSM, Iran Meghnat Sagh Company).


Preparation of Co_3O_4 nanoparticles

In order to prepare Co_3O_4 nanoparticles, an appropriate amount of the energetic $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex (2 g) was

powdered in a mortar and it was loaded into a porcelain crucible. The sample was then transferred into an electric furnace, heated at the rate of $10^\circ\text{C min}^{-1}$ from room temperature to 150°C in air atmosphere and was maintained at this temperature for 1 h. Similar experiments were performed for 2 g samples of the complex at the selected temperatures of 175, 200, 250°C . The obtained product at each temperature was cooled to room temperature and collected for the characterization.

RESULTS AND DISCUSSION

Initially, the thermal behavior of the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex was investigated by DSC analysis. The DSC curve in Fig. 1 shows that the complex is decomposed in two main steps. The first step occurred at about 150°C , shows a small endothermic peak which can be explained by the loss of one or two molecules of NH_3 per molecule of complex. In second step, a sharp exothermic peak is observed in the range of 175 – 200°C which can be related to the explosive decomposition of the complex via a redox process taking place between the NH_3 ligands as reducing agents and the NO_3^- ions as oxidizing agents. This reaction resulted in the solid Co_3O_4 and gaseous products i.e. N_2 , NO , N_2O and H_2O [48]. According to the above results and literature [48], the preparation of Co_3O_4 from the energetic $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex can be written as follows:



The FT-IR spectra of the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex and its decomposition products at different temperatures are shown in Fig. 2. For the starting complex in Fig. 2a, we can see the characteristic bands of the NH_3 ligands at

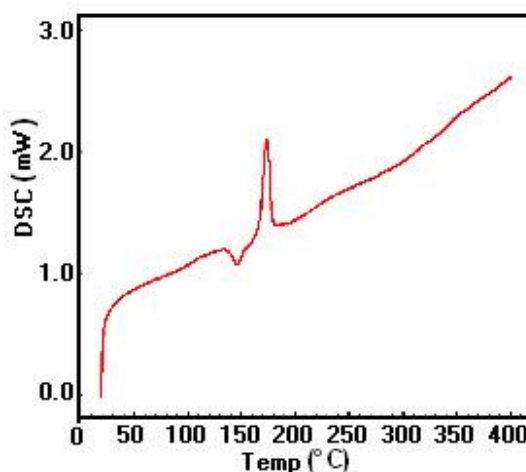


Fig. 1: DSC curve of the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex

approximately 3500-3000, 1600-1500, 1020 cm^{-1} and the bands related to the NO_3 groups at 1450-1250 and 750 cm^{-1} [49]. For the sample decomposed at 150°C (Fig. 2b), most of the bands associated with the complex disappeared and two weak bands of the spinel-type Co_3O_4 structure at about 662 and 565 cm^{-1} are observed [50]. The former band is characteristic of the $\text{Co}^{\text{III}}\text{-O}$ vibration in an octahedral site, and the later one is attributable to the $\text{Co}^{\text{II}}\text{-O}$ vibration in a tetrahedral site of spinel-type Co_3O_4 lattice. As shown in Fig. 2c-e, the intensity of these two bands was

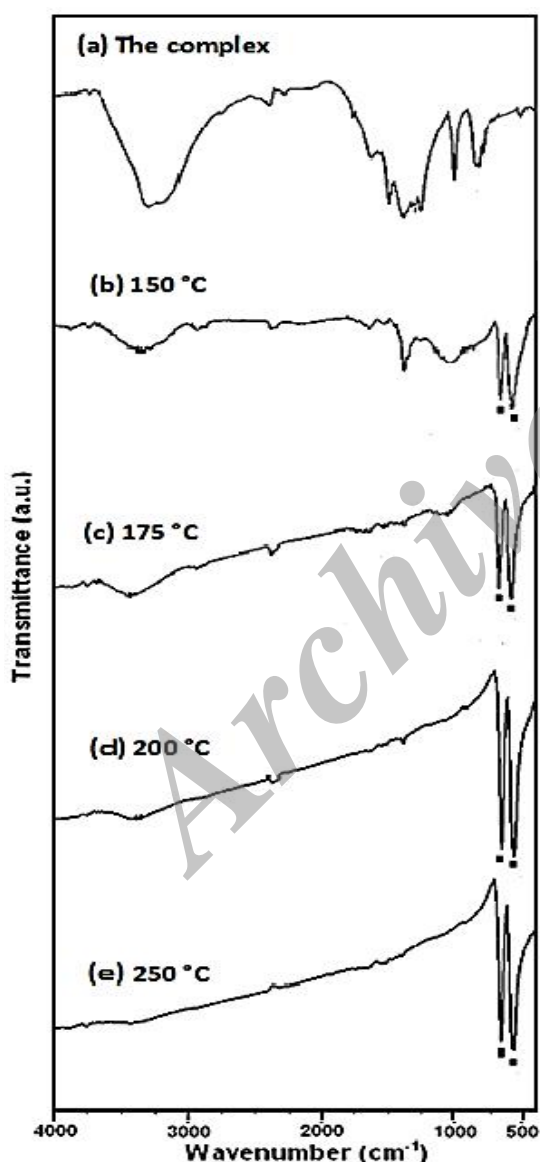


Fig. 2: FT-IR spectra of (a) the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex and its decomposition products at (b) 150 °C, (c) 175°C, (d) 200 °C, and (e) 250 °C

increased with the increase of the decomposition on temperature from 150 to 175°C and, then to 200°C, but further increasing the temperature to 250°C did not change the intensity. This data confirms the complete decomposition of the complex to pure Co_3O_4 phase at 200°C.

The crystal structure and phase compositions of the decomposition products of the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex at different temperatures were investigated by XRD, as shown in Fig. 3. The XRD pattern of sample decomposed at 150°C in Fig. 3a exhibits weak diffraction peaks with 2θ values at 19.50°, 31.37°, 37.02°, 39.10°, 44.97°, 55.84°, 59.58°, 65.44° and 77.65°. These diffraction peaks can be indexed to the crystalline cubic phase Co_3O_4 with lattice constant of $a = 8.076 \text{ \AA}$ and a space group of $\text{Fd}\bar{3}\text{m}$, which are in agreement with the reported values (JCPDS Card No. 76-1802). This result confirms that the formation of the Co_3O_4 phase started at 150°C. As shown in Fig. 3b and 3c,

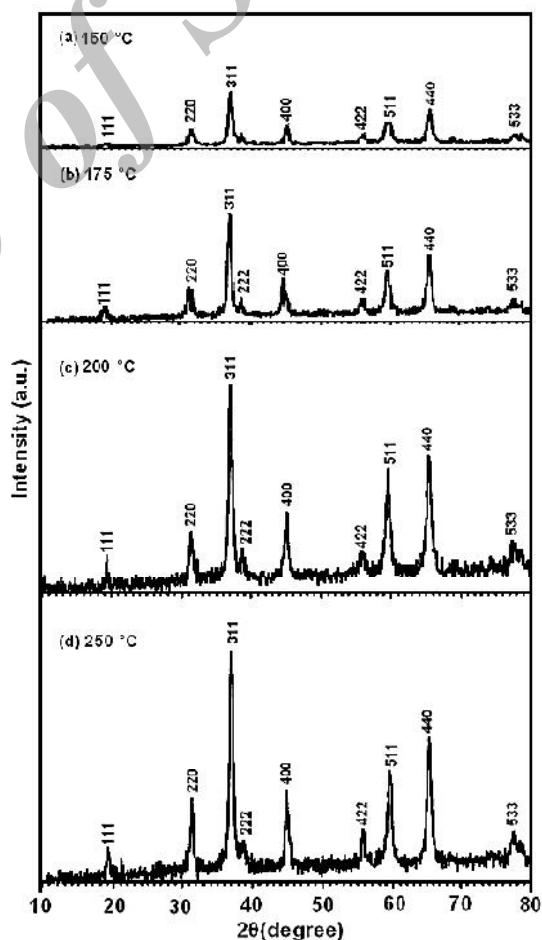


Fig. 3: The XRD patterns for the decomposition products of $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex at (b) 150°C, (c) 175 °C (d) 200°C and (e) 250°C .

the intensity of the characteristic peaks of the Co_3O_4 phase markedly increases as the decomposition temperature increases to 175°C and 200°C. XRD pattern of the sample decomposed at 250°C (Fig. 3d), shows only the peaks related to the Co_3O_4 without obvious changes.

Thus, 200°C is considered as an appropriate temperature for the complete decomposition of the precursor, as indicated by the FT-IR results. At this temperature, no peaks of other impurity phases have been detected, confirming that the final product is highly pure. The considerable broadening of the diffraction peaks demonstrates the nanometer character of the Co_3O_4 particles. The average size of the Co_3O_4 particles prepared at 200°C was estimated by the Debye-Scherrer equation [51]: $D_{\text{XRD}} = 0.9\lambda/(\beta\cos\theta)$ where D_{XRD} is the average crystalline size, λ is the wavelength of $\text{CuK}\alpha$, β is the full width at half maximum (FWHM) of the diffraction peak and θ is the Bragg's angle. The average size of the Co_3O_4 nanoparticles calculated using the most intense peak (311) at $2\theta = 36.26^\circ$ is approximately 18 nm. This value is in accordance with TEM observations (discussed below).

The morphology and particle size of product obtained from the thermolysis of the $[\text{Co}(\text{NH}_3)_5(\text{NO}_3)](\text{NO}_3)_2$ complex at 200°C were investigated by TEM. The TEM image of Co_3O_4 nanoparticles are shown in Fig. 4a. It can be seen

that nanoparticles have spherical morphology with a uniform size. Because of the small dimensions and high surface energy of the particles, it is easy for them to aggregate as seen in Fig. 4a. We also can find from this Fig that the morphology of the particles is almost homogeneous. Histogram revealing the size distribution of the Co_3O_4 nanoparticles is shown in Fig. 4b. From Fig. 4b, we obtained that the diameter sizes of the Co_3O_4 nanoparticles are approximately in the range of 10 to 24 nm with a narrow size distribution. The average particle size is 17 nm calculated from Fig. 4b, which is in agreement with the result calculated for the half-width of diffraction peaks using the Scherrer's formula, allowing for experimental error.

The elemental analysis of the Co_3O_4 nanoparticles was performed using the EDX on the SEM, as shown in Fig. 5. The peaks around 1.05, 6.95 and 7.95 keV are related to the binding energies of CoL , $\text{Co K}_{\alpha 1}$ and $\text{Co K}_{\alpha 2}$, respectively. Also, a peak near 0.50 keV corresponding oxygen is observed. The peak of C at 0.27 keV and peaks of Au at 2.20 and 9.75 keV are related to the SEM holding grid. The atomic percentages of Co and O were found to be 43.22% and 56.78%, respectively, which are near to the theoretical ratio (3:4) of the Co_3O_4 phase. The result indicates that the synthesized product is composed of high purity Co_3O_4 nanoparticles.

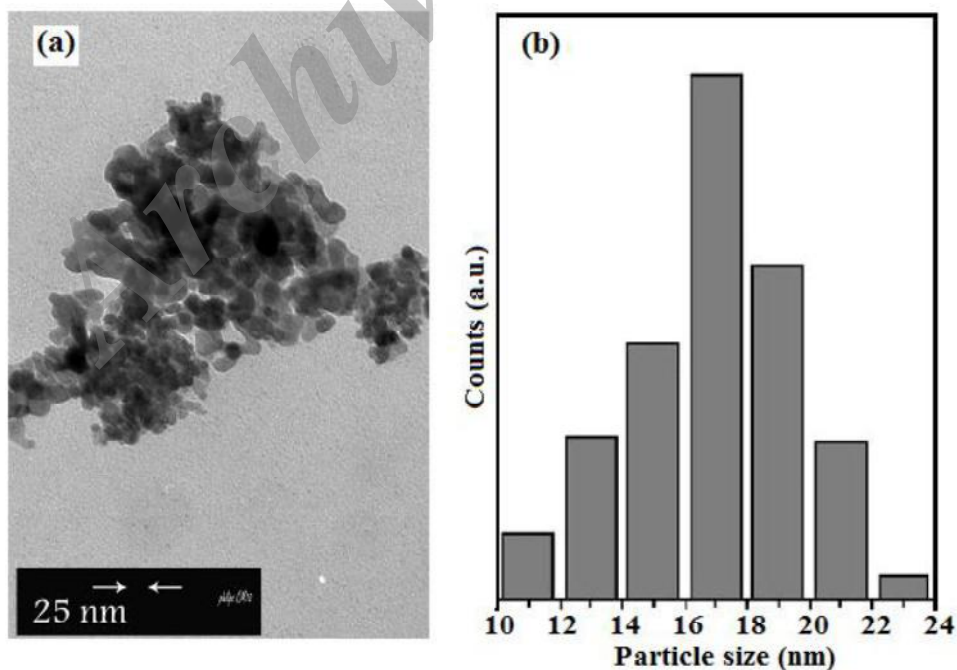


Fig. 4: (a) TEM image of the Co_3O_4 nanoparticles, and (b) Histogram showing the diameter distribution of the Co_3O_4 nanoparticles

The optical absorption properties of the as-prepared Co_3O_4 nanoparticles were investigated at room temperature by UV-vis spectroscopy. As can be seen in Fig. 6, two absorption bands appear in the wavelength ranges of 200–375 and 385–625 nm. These bands can be assigned to the $\text{O}^{2-} \rightarrow \text{Co}^{2+}$ and the $\text{O}^{2-} \rightarrow \text{Co}^{3+}$ charge transfer processes, respectively [52]. According to the following equation for a semiconductor [24]: $(\alpha h\nu)^2 = K(h\nu - E_g)$, where α is the absorption coefficient, K is a constant, $h\nu$ is the discrete photo energy (in eV), and E_g is the band gap energy, and the energy intercept of a plot of $(\alpha h\nu)^2$ vs $h\nu$ yields E_g for a direct transition (see the inset of Fig 6). The band gaps of the obtained Co_3O_4 nanoparticles are calculated to be 3.45 and 2.20 eV which are blue-shifted relative to reported values for the bulk sample (2.19 and 1.48 eV, respectively) [33,53]. The increase in the band gaps of the Co_3O_4 nanoparticles may ascribe to the small size effects of nanoparticles.

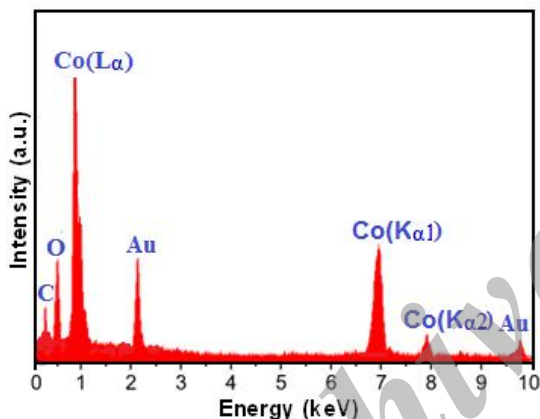


Fig. 5: EDX spectrum of the Co_3O_4 nanoparticles prepared at 200 °C.

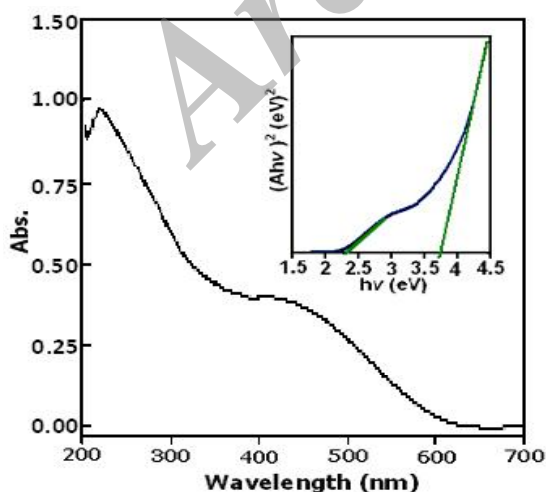


Fig. 5: EDX spectrum of the Co_3O_4 nanoparticles prepared at 200 °C.

The magnetic property of the Co_3O_4 nanoparticles was measured at room temperature. As shown in Fig. 7a, the magnetization is approximately linear with the field and it does not saturate even at the applied field of 8 kOe. Fig. 7b indicates the expansion of magnetization near the lower applied field. We can see a fine hysteresis loop which is characteristic of weak ferromagnetic behaviour, although bulk Co_3O_4 has antiferromagnetic nature. This behavior may arise due to uncompensated surface spins and/or due to finite size effects of the Co_3O_4 nanoparticles [11, 54-56].

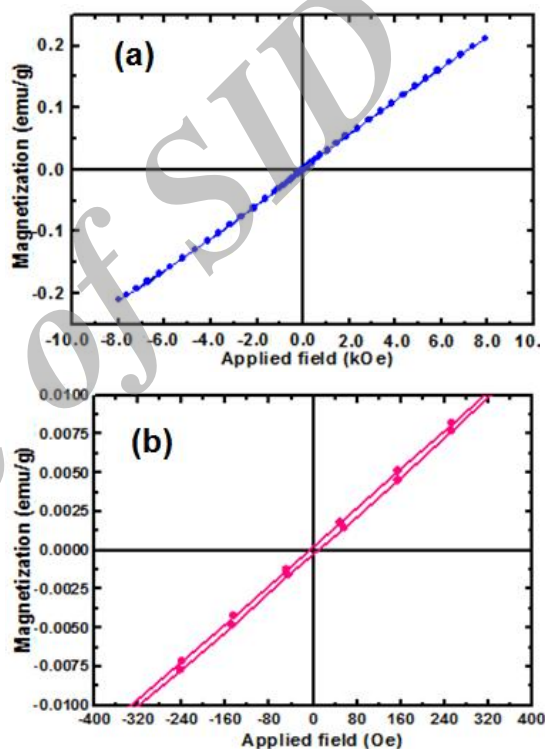


Fig. 7: (a) Magnetization curve as a function of applied magnetic field for Co_3O_4 nanoparticles at room temperature, and (b) the expansion of magnetization vs. field near the lower applied field

CONCLUSIONS

In conclusion, Co_3O_4 nanoparticles with an average particle size of 17 nm have been successfully prepared via thermal decomposition of the $[\text{Co}(\text{NH}_3)_5\text{NO}_3](\text{NO}_3)_2$ at 200 °C. Co_3O_4 nanoparticles are formed from this complex via a redox reaction between NH_3 ligands and the NO_3^- ions. This method yields spherical-like Co_3O_4 nanoparticles with a narrow size distribution and weak ferromagnetic behavior. The estimated optical absorption band gaps of the Co_3O_4 nanoparticles are relatively blue-shifted,

compared with the values for the bulk sample. This approach provides a one-step simple and inexpensive route for the preparation of Co_3O_4 nanoparticles with high purity in order to high-technology applications.

ACKNOWLEDGEMENTS

The authors are grateful to the Lorestan University Research Council and Iran Nanotechnology Initiative Council (INIC) for financial support of this work.

REFERENCES

- [1] Klabunde K. J., Richards R. M., (2012), *Nanoscale Materials in Chemistry*. 2nd edn. Wiley, New York.
- [2] Mate V. R., Shirai M., Rode, C. V., (2013), Heterogeneous Co_3O_4 catalyst for selective oxidation of aqueous veratryl alcohol using molecular oxygen. *Catal. Commun.* 33: 66-69.
- [3] Warang T., Patel N., Santani A., Bazzanella N., Kale A., Miotello, A., (2012), Pulsed laser deposition of Co_3O_4 nanoparticles assembled coating: Role of substrate temperature to tailor disordered to crystalline phase and related photocatalytic activity in degradation of methylene blue. *Appl. Catal. A: Gen.* 423-424: 21-27.
- [4] Casas-Cabanas M., Binot O. G., Larcher D., Lecup A., Giordani V., Tarascon, J. M., (2009), Defect chemistry and catalytic activity of nanosized Co_3O_4 . *Chem. Mater.* 21: 1939-1947.
- [5] Askarnejad A., Bagherzadeh M., Morsali A., (2010), Catalytic performance of Mn_2O_3 and Co_3O_4 nanocrystals prepared by sonochemical method in epoxidation of styrene and cyclooctene. *Appl. Surf. Sci.* 256: 6678-6682.
- [6] Lou X. W., Deng D., Lee J. Y., Feng J., Archer L. A., (2008), Self-supported formation of needlelike Co_3O_4 nanotubes and their application as lithium-ion battery electrodes. *Adv. Mater.* 20: 258-262.
- [7] Chou S. L., Wang J. Z., Liu H. K., Dou, S. X., (2008), Electrochemical deposition of porous Co_3O_4 nanostructured thin film for lithium-ion battery. *J. Power. Sourc.* 182: 359-364.
- [8] Li Y. G., Tan B., Wu Y. Y., (2008), Mesoporous Co_3O_4 nanowire arrays for lithium ion batteries with high capacity and rate capacity. *Nano Lett.* 8: 265-270.
- [9] Li W. Y., Xu L. N., Chen J., (2005), Co_3O_4 nanomaterials in lithium-ion batteries and gas sensors. *Adv. Funct. Mater.* 15: 851-857.
- [10] Sugimoto T., Matijevic E., (1979), Colloidal cobalt hydroxide oxides, preparation and properties of monodispersed Co_3O_4 . *J. Inorg. Nucl. Chem.* 41: 165-172.
- [11] Makhlof S. A., (2002), Magnetic properties of Co_3O_4 nanoparticles. *J. Magn. Magn. Mater.* 246: 184-190.
- [12] Sun L., Li H., Ren L., Hu C., (2009), Synthesis of Co_3O_4 nanostructures using a solvothermal approach. *Solid State Sci.* 11: 108-112.
- [13] Chen Y., Zhang Y., Fu S., (2007), Synthesis and characterization of Co_3O_4 hollow spheres. *Mater. Lett.* 61: 701-705.
- [14] Lai T., Lai Y., Lee C., Shu Y., Wang C., (2008), Microwave-assisted rapid fabrication of Co_3O_4 nanorods and application to the degradation of phenol. *Catal. Today.* 131: 105-110.
- [15] Wang W. W., Zhu, Y. J., (2005), Microwave-assisted synthesis of cobalt oxalate nanorods and their thermal conversion to Co_3O_4 rods. *Mater. Res. Bull.* 40: 1929-1935.
- [16] Li L., Chu Y., Liu Y., Song J. L., Wang D., Du X. W., (2008), A facile hydrothermal route to synthesize novel Co_3O_4 nanoplates. *Mater. Lett.* 62: 1507-1510.
- [17] Du J., Chai L., Wang G., Li K., Qian Y., (2008), Controlled synthesis of one-dimensional single-crystal Co_3O_4 nanowires. *Aust. J. Chem.* 61: 153-158.
- [18] Wang R. M., Liu C. M., Zhang H. Z., Chen C. P., Guo L., Xu H. B., Yang S. H., (2004), Porous nanotubes of Co_3O_4 : synthesis, characterization and magnetic properties. *Appl. Phys. Lett.* 85: 2080-2082.
- [19] Li Y., Zhao J., Dan Y., Ma D., Zhao Y., Hou S., Lin H., Wang Z., (2011), Low temperature aqueous synthesis of highly dispersed Co_3O_4 nanocubes and their electrocatalytic activity studies. *Chem. Eng. J.* 166: 428-434.
- [20] Sun H., Ahmad M., Zhu J., (2013), Morphology-controlled synthesis of Co_3O_4 porous nanostructures for the application as lithium-ion battery electrode. *Electrochim. Acta.* 89: 199-205.
- [21] Ren M., Yuan S., Su L., Zhou Z., (2012), Chrysanthemum-like Co_3O_4 architectures: Hydrothermal synthesis and lithium storage performances. *Solid State Sci.* 14: 451-455.
- [22] Yang L. X., Zhu Y. J., Li L., Zhang L., Tong H., Wang W. W., (2006), A facile hydrothermal route to flower-like cobalt hydroxide and oxide. *Eur. J. Inorg. Chem.* 23: 4787-4792.
- [23] Jiu J., Ge Y., Li X., Nie L., (2002), Preparation of Co_3O_4 nanoparticles by a polymer combustion route. *Mater. Lett.* 54: 260-263.
- [24] Gu F., Li C., Hu Y., Zhang L., (2007), Synthesis and optical characterization of Co_3O_4 nanocrystals via a facile combustion method. *J. Cryst. Growth.* 304: 369-373.
- [25] Gardey-Merino M. C., Palermo M., Belda R., Fernández de Rapp M. E., Lascalea G. E., Vázquez P. G., (2012), Combustion synthesis of Co_3O_4 nanoparticles: fuel ratio effect on the physical properties of the resulting powders. *Proced. Mater. Sci.* 1: 588-593.
- [26] Ai L. H., Jiang J., (2009), Rapid synthesis of nanocrystalline Co_3O_4 by a microwave-assisted combustion method. *Powder Tech.* 195: 11-14.
- [27] Li L., Ren J., (2006), Rapid preparation of spinel Co_3O_4 nanocrystals in aqueous phase by microwave irradiation. *Mater. Res. Bull.* 41: 2286-2290.
- [28] Bhat A. S., Bhat D. K., Tai C. W., Santosh M. S., (2011), Microwave-assisted synthesis and magnetic studies of cobalt oxide nanoparticles. *Mater. Chem. Phys.* 125: 347-350.
- [29] Ma J., Zhang S., Liu W., Zhao Y., (2010), Facile preparation of Co_3O_4 nanocrystals via a solvothermal process directly from common Co_2O_3 powder. *J. Alloys Compd.* 490: 647-651.
- [30] Lester E., Aksentiyeva G., Li J., Gomez S., Gonzalez-Gonzalez J., Poliakoff, M., (2012), Controlled continuous hydrothermal synthesis of cobalt oxide (Co_3O_4) nanoparticles. *Prog. Cryst. Growth Charact. Mater.* 58: 3-13.
- [31] Baydi M. E., Poillat G., Rehspringer J. L., Gautier J. L., Koenig J. F., Chartier P., (1994), A sol-gel route for the preparation of Co_3O_4 catalyst for oxygen electrocatalysis in alkaline medium. *J. Solid State Chem.* 109: 281-288.
- [32] Kim D. Y., Ju S. H., Koo H. Y., Hong S. K., Kang Y. C., (2006), Synthesis of nanosized Co_3O_4 particles by spray pyrolysis. *J. Alloys Compd.* 417: 254-258.
- [33] Kumar R. V., Diamant Y., Gedanken A., (2000), Sonochemical synthesis and characterization of nanometer-size transition metal oxides from metal acetates. *Chem. Mater.* 12: 2301-2305.
- [34] Wang X., Chen X. Y., Gao L. S., Zheng H. G., Zhang Z., Qian Y. T., (2004), One-dimensional arrays of Co_3O_4 nanoparticles: Synthesis, characterization, and optical and electrochemical properties. *J. Phys. Chem. B.* 108: 16401-16404.
- [35] Fan S., Liu X., Li Y., Yan E., Wang C., Liu J., Zhang Y., (2013), Non-aqueous synthesis of crystalline Co_3O_4 nanoparticles for lithium-ion batteries. *Mater. Lett.* 91: 291-293.
- [36] Jiang J., Li L., (2007), Synthesis of sphere-like Co_3O_4 nanocrystals via a simple polyol route. *Mater. Lett.* 61: 4894-4896.
- [37] Zou D., Xu C., Luo H., Wang L., Ying T., (2008), Synthesis of Co_3O_4 nanoparticles via an ionic liquid-assisted methodology at room temperature. *Mater. Lett.* 62: 1976-1978.
- [38] Traversa E., Sakamoto M., Sadaoka Y., (1998), A chemical route for the preparation of nanosized rare earth Perovskite-type oxides for electroceramic applications. *Part. Sci. Technol.* 16: 185-214.
- [39] M. Y. Masoomi, A. Morsali, (2012), Applications of metal-organic coordination polymers as precursors for preparation

- t of nano-materials. *Coord. Chem. Rev.* 256: 2921-2943.
- [40] Mohandes F., Davar F., Salavat-Niasari M., (2010), Preparation of Co_3O_4 nanoparticles by nonhydrolytic thermolysis of $[\text{Co}(\text{Pht})(\text{H}_2\text{O})_n]$ polymers. *J. Magn. Magn. Mater.* 322: 872-877.
- [41] Ren L., Wang P., Han Y., Hu C., Wei B., (2009), Synthesis of $\text{CoC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$ nanorods and their thermal decomposition to Co_3O_4 nanoparticles. *Mater. Phys. Lett.* 476: 78-83.
- [42] Thangavelu K., Parameswari K., Kuppusamy K., Haldorai Y., (2011), A simple and facile method to synthesize Co_3O_4 nanoparticles from metal benzoate dihydrazinate complex as a precursor. *Mater. Lett.* 65: 1482-1484.
- [43] Salavat-Niasari M., Khansari A., Davar F., (2009), Synthesis and characterization of cobalt oxide nanoparticles by thermal treatment process. *Inorg. Chim. Acta.* 362: 4937-4942.
- [44] Farhadi S., Pourzare K., (2012), Simple and low-temperature preparation of Co_3O_4 sphere-like nanoparticles via solid-state thermolysis of the $[\text{Co}(\text{NH}_3)_6](\text{NO}_3)_3$ complex. *Mater. Res. Bull.* 47: 1550-1556.
- [45] Farhadi S., K. Pourzare, (2014), Synthesis and characterization of Co_3O_4 nanoplates by simple thermolysis of the $[\text{Co}(\text{NH}_3)_2(\text{C}_2\text{O}_4)_3] \cdot 4\text{H}_2\text{O}$ complex. *Polyhedron.* 67: 104-110.
- [46] Farhadi S., Roostaie-Zaniyani Z., (2011), Simple and low-temperature synthesis of NiO nanoparticles through solid-state thermal decomposition of the hexa(amine) Ni(II) nitrate, $[\text{Ni}(\text{NH}_3)_6](\text{NO}_3)_2$, complex. *Polyhedron.* 30: 1244-1249.
- [47] Bailar J. C., (1953), Acidopentamminecobalt (III) salts. *Inorg. Synth.* 4: 171-174.
- [48] Kristóf J., Horváth A., Szabó P., (1990), Simultaneous thermoanalytical investigations on the rapid decomposition of pentamminecobalt (III) complexes. *J. therm. Analys.* 36: 1191-1204.
- [49] Nakamoto K., (2009), Infrared and Raman spectra of inorganic and coordination compounds, Part B: Applications in coordination, organometallic, and bioinorganic chemistry, 6th edn. Wiley, New York.
- [50] Pejova B., Isahi A., Najdoski M., (2001), Fabrication and characterization of nanocrystalline cobalt oxide thin films. *Mater. Res. Bull.* 36: 161-170.
- [51] Klug H. P., Alexander L. E., (1964), X-ray Diffraction Procedures. 2nd edn. Wiley, New York.
- [52] He T., Chen D. R., Jiao X. L., Wang Y. L., Duan Y. Z., (2005), Solubility-controlled synthesis of high-quality Co_3O_4 nanocrystals. *Chem. Mater.* 17: 4023-4030.
- [53] Gulino A., Dapporto P., Rossi P., Fragala I., (2003), A novel self-liquid MOCVD precursor for Co_3O_4 thin films. *Chem. Mater.* 15: 3748-3752.
- [54] Ichianagi Y., Kimishima Y., Yamada S., (2004), Magnetic study on Co_3O_4 nanoparticles. *J. Magn. Magn. Mater.* 272-276: e1245-e1246.
- [55] Kodama R. H., Makhlof S. A., Berkowitz, A. E., (1997), Growth mechanism and magnon excitation in NiO nanowalls. *Phys. Rev. Lett.* 79: 1393-1396.
- [56] Ozkaya T., Baykal A., Toprak M. S., Koseoglu Y., Durmus Z., (2009), Reflux synthesis of Co_3O_4 nanoparticles and its magnetic characterization. *J. Magn. Magn. Mater.* 321: 2145-2149.