

The Effect of Preparation Design on the Fracture Resistance of Zirconia Crown Copings (Computer Associated Design/Computer Associated Machine, CAD/CAM System)

E. Jalalian¹, B. Atashkar^{2✉}, R. Rostami²

¹Associate Professor, Department of Fix Prosthodontics, Dental Branch, Azad University, Tehran, Iran

²Dentist

Abstract:

Objective: One of the major problems of all ceramic restorations is their probable fracture against the occlusal force. The aim of the present in-vitro study is to compare the effect of two marginal designs (chamfer & shoulder) on the fracture resistance of zirconia copings, CERCON (CAD/CAM).

MATERIALS AND METHODS: This in vitro study was done with single blind experimental technique. One stainless steel die with 50° chamfer finish line design (0.8 mm depth) was prepared using milling machine. Ten epoxy resin dies were made, The same die was retrieved and 50° chamfer was converted into shoulder (1 mm). again ten epoxy resin dies were made from shoulder dies. Zirconia cores with 0.4 mm thickness and 35 µm cement Space fabricated on the 20 epoxy resin dies (10 samples chamfer and 10 samples shoulder) in a dental laboratory. Then the zirconia cores were cemented on the epoxy resin dies and underwent a fracture test with a universal testing machine (GOTECH AI-700LAC, Arson, USA) and samples were investigated from the point of view of the origin of the failure.

RESULT: The mean value of fracture resistance for shoulder margins were 788.90±99.56 N and for the chamfer margins were 991.75±112.00 N. The student's T-test revealed a statistically significant difference between groups (P=0.001).

CONCLUSION: The result of this study indicates that marginal design of the zirconia cores effects on their fracture resistance. A chamfer margin could improve the biomechanical performance of posterior single zirconia crown restorations. This may be because of strong unity and round internal angle in chamfer margin.

Key Words: Preparation Design; Fracture Resistance; Zirconia; CAD/CAM

Journal of Dentistry, Tehran University of Medical Sciences, Tehran, Iran (2011; Vol. 8, No.3)

✉ Corresponding author:
B. Atashkar
berivan.atashkar@gmail.com

Received: 29 March 2011
Accepted: 30 June 2011

INTRODUCTION

One of the major problems of the all ceramic restorations is their probable fracture against the occlusal and lateral force [1]. The common restorations contain metal which leads to toxic, chemical and allergic effects [1]. The differ-

ence between their color and natural tooth is another problem [1] Most of the people prefer tooth colored crowns [1]. The major benefits of all ceramic crowns is their esthetic and biocompatible effects [2]. Some crown fractures due to the relatively low mechanical resistance

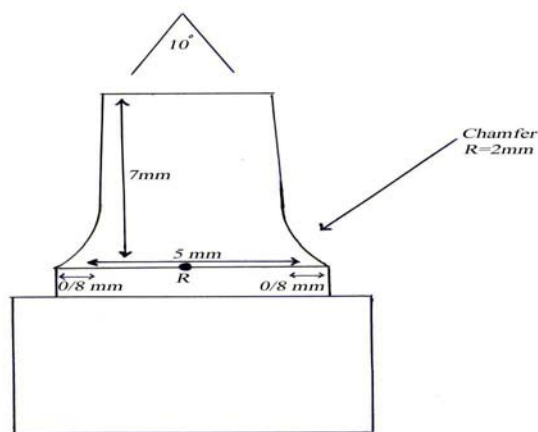


Fig (a1): Diagram of chamfer

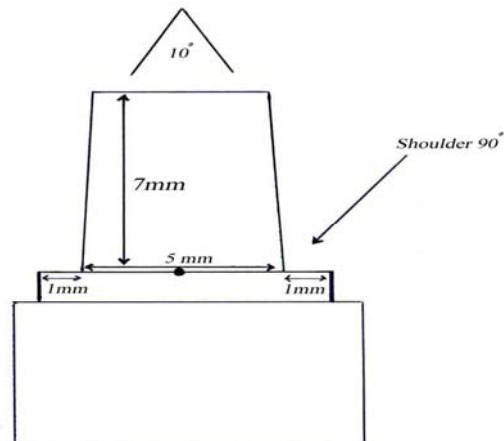


Fig (a2): Shoulder preparation

of ceramic crowns have become more apparent [1]. This is mainly due to the magnitude of the biting forces applied on the premolar and molar teeth and to the inherent brittleness of ceramics [3,4]. Ceramic materials are sensitive to the tensile stresses, and superficial flaws and internal voids effect on their fracture resistance [1]. Such defects may represent the sites of crack initiation. This phenomenon may be influenced by different factors such as marginal design and thickness of the restoration, residual processing stress, magnitude and direction and frequency of the applied load, elastic modulus of the restoration components, restoration-cement interfacial defects and oral environmental effects [5]. In one research, the comparison of stress distribution during mastication between maxillary second premolars restored with metal-ceramic crowns and non-restored teeth was done by finite element analysis method (FEA). They registered high stresses at the cervical line of the restored teeth within the dentin-metal interface and within the ceramic-metal interface [6]. Florian Beuer suggested that shoulder margin has a greater fracture resistance than chamfer margin [7]. Sadan et al proposed that both of these types of finishing lines are considered to be adequate for the tooth [8]. Di Iorio et al suggested that the shoulder margin could improve the biomechanical performance of single crown alumina

restorations [9]. De Jager et al discovered that for long lasting restorations in posterior region it is advisable to make a chamfer with collar preparation [10]. Cho L et al suggested that chamfer margins with 0.9 and 1.2 mm depths have greater fracture resistance than shoulder and rounded shoulder margins with 1.2 mm depths. [11]. Potiket et al suggested that a 1mm deep shoulder finishing line with a rounded internal line angle has good fracture strength for the natural teeth restored with all ceramic crowns [12]. Rammersberg et al discovered that a minimally invasive 0.5 mm axial chamfer tooth preparation has the greatest stability for posterior metal free crowns [13]. The aim of the present in vitro study is to compare the resistance to fracture under static compressive load (not cyclic) applied to zirconia cores with chamfer and shoulder margins. The hypothesis of the present study is the effect of marginal design of crowns on an improved mechanical performance of cercon crowns, from a clinical point of view. Such a condition can be achieved preparing a chamfer margin in crowns instead of a shoulder margin.

MATERIALS AND METHODS

This in vitro study was done by using one machined standard stainless steel dye with 7 mm height and 5 mm diameter. The axial walls were 10° convergent [14]. The marginal area of



Fig (b1): Standard dies of Chamfer

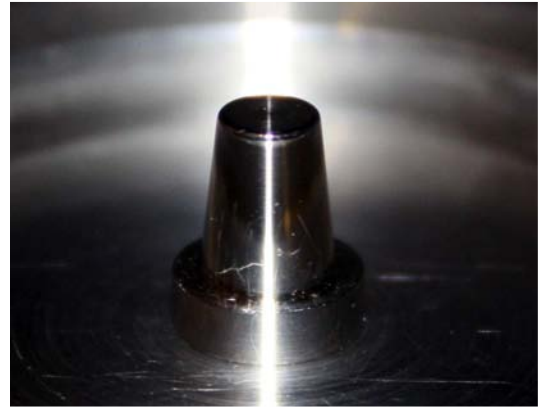


Fig (b2): Shoulder preparation



Fig (c1): Epoxy resin dies with chamfer



Fig (c2): Shoulder margin



Fig (d1): Fracture area in chamfer




Fig (d2): Shoulder margin

the dye was prepared with 50° chamfer finish line (0.8 mm depth) [15,16].


(figure a1, b1). 10 poly vinyl siloxane impressions (PVC, Elite H-D+, Zhermach, Germany) were made and ten epoxy resin dyes

(CW2215, Hunstman-Germany) were created from these Impressions (Fig c1).

Afterwards. The standard dye was converted into shoulder with 1 mm depth [15,16]. (Fig a2, b2).

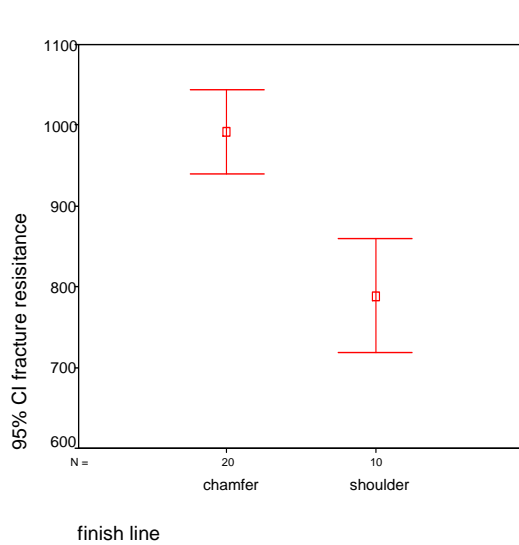

Graph 1. Error-bar graph shows the mean fracture resistance of shoulder and chamfer margin with 95% confidence interval.

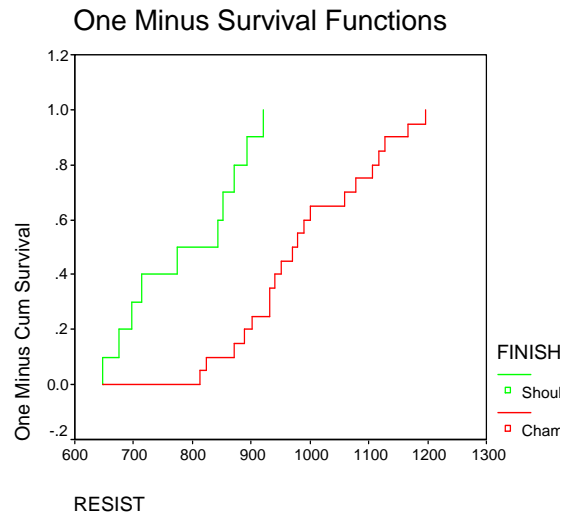

Graph 2. Kaplan-Meier graph shows the cumulative distribution of fracture /load in the chamfer and shoulder finishing lines.

Again 10 PVC impressions were made and ten epoxy resin dyes were created from these impressions (Figure c2) [7,9]. (20 copings were made of a partially sintered ZrO₂ ceramic material by using CAD/CAM technology (Cercon Smart Ceramics, Degu Dent, Hanau, Germany). The copings with 0.4mm thickness and [15,16] 35µm cement space[7]. milled out from the presintered ZrO₂ by cercon milling (Cercon, Brain, Dego Dent, Hanau, Germany) and Cercon Heat (Degu Dent, Hanau, Germany) heated.

them at 1350°C for 6 hours Because the coping determinates the overall resistance to fracture of veneered crown mainly [15,17] porcelain veneering was omitted.

Copings were evaluated visually, those with margin damaged and visually unacceptable were rejected and another coping was made instead. Each coping was cemented on its definitive dye with GI (GC Gold Labeled, Tokyo, Japan) [13] by an experienced technician and Finger pressure was applied during the setting time [18].

Table 1: Fracture resistance of chamfer and shoulder edge zirconia cores

Margin design	N	Mean	Std. Deviation	Std. Error	95% Confidence Interval for Mean		Minimum	Maximum
					Lower Bound	Upper Bound		
chamfer	20	991.7500	112.00088	25.04416	939.3320	1044.1680	813.00	1196.00
shoulder	10	788.9000	99.56399	31.48490	717.6762	860.1238	647.00	921.00

Downloaded from <http://journals.tums.ac.ir/> on Wednesday, April 18, 2012

After cementation, excess luting agent was removed and fitness was considered accomplished when two or more investigators determined-by visual inspection-that no marginal gap was visible [7]. Ten samples were stored in a saline solution at room temperature for 24 hours. Mechanical tests were carried out using a universal testing machine (GOTECH AI-700LAC, Arsona, USA). The compressive static load was applied at the center of the occlusal surface along the long axis of dye with a crosshead speed of 0.5 mm/min according to previous studies [7] that starts from 0N and increased until fracture occurred [19]. The fracture load data were automatically recorded using by vista software, which also completed stress-strain diagram and recorded the breaking load. Samples were investigated from the point of view of the origin of the failure (Fig. d1, 2).

RESULTS

The mean \pm SD of fracture resistance were 788.90 ± 99.56 N for the shoulder and 991.75 ± 112.00 N for chamfer margin (Graph 1). Both of minimum and maximum fracture resistance of the two groups were more than intra oral loads. The student's t-test revealed a statistically significant difference between two groups ($p=0.001$). This research carried out with 95% confidence, Kaplan Meir graph showed the design of fracture, that chamfer margin bears more cracks till fracture than shoulder margin (Graph 2). Figure d 1,2 showed that the origin of failure of cores with chamfer margin was axial wall and in shoulder margin, the 90° sharp internal angle was the point of failure (Table 1).

DISCUSSION

In this study the student's t-test revealed a statistically significant difference between the groups .fracture resistance of chamfer margin was more than shoulder margin. Elastic modulus of the materials that supported core af-

ected on the fracture resistance of the core [20] .Thus, in this study, we use epoxy resin dye that its stiffness is more than brass dye [21]. Another difference between this study and clinical conditions is the unknown nature of the bonding between luting agent and dye material. It is reasonable to suppose the presence of a hybrid layer at the dentin-cement interfaces effects on the biomechanical behavior of the core/supporting dye system. However, both of these factors equally influenced on the two groups in the present study. So, it is possible to make a comparison between the two groups. Fracture resistance of the two groups are more than biting forces [22], so we could use all of these marginal designs in the posterior all ceramic crowns successfully, and it is a very good replacement for PFM crowns. The difference of fracture resistance between the two groups revealed that the chamfer margin has more fracture resistance than shoulder margin (comment D5), because Chamfer margin has a curve and round internal angle which leads to more marginal fitness and spread load better and we don't have such a condition in a 90° shoulder margin. We use GI for cementation, so we have a strong unity in the margins that make a greater fracture resistance [23,24]. It seems that shoulder margin has the worst marginal fitness in all ceramic materials, so in this condition because of sharp internal angle, we have no strong unity in this marginal design that makes a lower fracture resistance than chamfer margins.

Limitation:

1. We used epoxy resin for casting impressions that was expensive and had long last setting time (about 24-36 hours at room temperature).
2. Cementation was done by figure pressure.
3. Marginal fitness was considered by visual inspection (not SEM) that no marginal gap was visible.
4. CAD/CAM system could not scan 90° sharp internal angle in the shoulder margin

well, so the thickness of cement increased in internal angle and decreased fracture resistance.

CONCLUSION

The results of this study indicate that marginal design effects on fracture resistance. A chamfer margin could improve the mechanical performance of the posterior single crown zirconia restorations. This might be due to the strong unity and round internal angle in the chamfer margin.

REFERENCES

- 1-Jalalian E, Aletaha NS. The effect of two marginal designs (chamfer and shoulder) on the fracture resistance of all ceramic restorations, Inceram: an in vitro study. *J Prosthodont Res* 2011 Apr;55(2):121-5.
- 2-Ferrance JL. Using posterior composites appropriately. *J Am Dent Assoc* 1992 Jul;123(7):53-8,663-6.
- 3-Etemadi S, Smales RJ. Survival of resin-bonded porcelain veneer crowns placed with and without metal reinforcement. *J Dent* 2006 Feb;34(2):139-45.
- 4-Mclaren EA, White SN. Survival of In-Ceram crowns in a private practice: a prospective clinical trial. *J Prosthet Dent* 2000 Feb;83(2):216-22.
- 5-Webber B, McDonald A, Knowles J. An in vitro study of the compressive load at fracture of procera All ceramic crowns with varying thickness of veneer porcelain. *J Prosthet Dent* 2003 Feb;89(2):154-60.
- 6-Aykul H, Toparli M, Dalkiz M. A calculation of stress distribution in metal-porcelain crowns by using three-dimensional finite element method. *J Oral Rehabil* 2002 Apr;29(4):381-6.
- 7- Beuer F, Aqqstaller H, Edelhoff D, Gernet W. Effect of preparation design on the fracture resistance of zirconia crown copings. *Dent Mater J* 2008 May;27(3):362-7.

- 8-Sadan A, Blatz MB, Lang B. Clinical consideration for densely sintered alumina and zirconia restorations: Part 1. *Int J Periodontics Restorative Dent* 2005 Jun;25(3):213-9.
- 9-Di Iorio D, Murmura G, Orsini G, Scarano A, Caputi S. Effect of margin design on the fracture resistance of Procera all ceram cores: an in vitro study. *J Contemp Dent Pract* 2008 Feb 1;9(2):1-8.
- 10-De Jager N, Pallav P, Feilzer AJ. The influence of design parameters on the FEA-determined stress distribution in CAD-CAM produced all-ceramic dental crowns. *Dent Mater* 2005 Mar;21(3):242-51.
- 11-Cho L, Choi J, Yi YJ, Park CJ. Effect of finish line variants on marginal accuracy and fracture strength of ceramic optimized polymer/fiber-reinforced composite crowns. *J Prosthet Dent* 2004 Jun;91(6):554-60.
- 12-Potiket N, Chiche G, Finger IM. In vitro fracture strength of teeth restored with different all-ceramic crown systems. *J Prosthet Dent* 2004 Nov;92(5):491-5.
- 13-Rammersberg P, Eickemeyer G, Erdlt K, Pospiech P. Fracture resistance of posterior metal-free polymer crowns. *J Prosthet Dent* 2000 Sep;84(3):303-8.
- 14-Jalalian E, Keshavarzi G. Comparison of Heavy Chamfer and Shoulder Finish line Designs on Marginal Adaptation of All-ceramic IPS e.max press Restorations. *J Res Dent* 2005;5(3):53-7.
- 15-Shillingburg Herbert T, Hobo Sumiya, Whitsett Lowell D, Jucobi Richard, Bruckett Susan E. *Fundamentals of fixed prosthodontics*. 3rd ed. America: Quintessence; 1997. p. 139-71.
- 16-Gavelis JR, Mornecy JD, Riley ED, Sozio RB. The effect of various finish line preparation on the marginal seal and occlusal seat of full crown preparations. *J Prosthet Dent* 1981 Feb;45(2):138-45.
- 17-Beuer F, Kerier T, Erdeit KJ, Schweiger J, Eichberger M, Gerent W. Influence of

veneering on the fracture resistance of zirconium restorations.

18-Att W, Komine F, Gerds T, Strub JR. Marginal

adaptation of three

different zirconium dioxide three-unit fixed dental prostheses. *J Prosthet Dent* 2009 Apr;101(4):239-47.

19-Jalalian E, Moghadam L. Compare the fracture resistance of 2 All ceramic systems, IPS e.max, IPS Empress. *J Dent (Shiraz University)* Spring 2008;9(2):51-7.

20-Scherrer SS, de Rijk WG. The fracture resistance of all ceramic crowns on supporting structure with different elastic moduli. *Int J Prosthodont* 1993 Sep-Oct;6(5):462-7.

21-Ayad MF. Effect of the crown preparation margin and dye type on the marginal

accuracy of fiber-reinforced composite crowns. *J Contemp Dent Pract* 2008 Feb 1;9(2):9-16.

22-Gibbs CH, Anusavice KJ, Young HM, Jones JS, Esquivel-Upshaw JF. Maximum clenching force of patients with moderate loss

of posterior tooth support: a pilot study. *J Prosthet Dent* 2002 Nov;88(5):498-502.

23-Hyun-ok Cho, Dong-wan Kang. Marginal fidelity and fracture strength of IPS-Empress ceramic crowns according to different cement types. *J Korean Acad Prosthodont* 2002;40(6):545-60.

24-Beuer F, Naumann M, Gernet W. Marginal adaptation of three different zirconium dioxide three-unit fixed dental prostheses. *J Prosthet Dent* 2009;101(4):239-47.

Archive of SID