

Effect of the Type of Endodontic Sealer on the Bond Strength Between Fiber Post and Root Wall Dentin

Ramin Mosharraf^{1✉}, Sepideh Zare²

¹Professor, Dental Material Research Center and Department of Prosthodontics, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran

²Private Practice, Isfahan, Iran

Abstract

Objectives: An important factor that interferes with the bonding between the root canal wall and resin cement is the root canal sealer remnant. There is controversy about the effect of eugenol-containing sealers on the bond strength between resin cements and fiber post. The aim of this study was to evaluate the effect of the type of endodontic sealer on the bond strength of FRC posts cemented with resin cement to the root canal wall.

Materials and Methods: In this in vitro study, 20 extracted mandibular first premolars were endodontically treated and divided into two groups according to the endodontic sealer used (n=10): G1: AH₂₆ (Resin based); and G2: Endofill (Eugenol-based). After preparing post space, adhesive resin cement (Panavia F 2.0) was used for cementation of the fiber post to the root canal dentin. Three 3 mm thick slices were obtained from each root.

The push-out test was performed with a cross-head speed of 1 mm/minute. Two-way ANOVA and Tukey post hoc tests were used for analyzing data ($\alpha=0.05$).

Results: The two-way ANOVA showed that different root canal sealers ($P=0.037$) had significant effects on bond strength (BS), but root canal regions ($P=0.811$) and interaction between root canal sealers and root canal regions ($P=0.258$) had no significant effects on BS. Maximum and minimum mean values were observed in the AH₂₆ group, the apical region and the Endofill group in the apical region, respectively. Post Hoc Tukey test revealed that there were no significant differences between different root canal regions in both cements ($P>0.05$).

Conclusion: The region of root canal had no effect on the bond strength of cemented fiber posts to the root canal. Eugenol-based sealers (Endofill) significantly reduced the bond strength between fiber posts luted with resin cement to the root canal.

Key Words: Resin Cements; Dental Bonding; Zinc Oxide-Eugenol Cement

Journal of Dentistry, Tehran University of Medical Sciences, Tehran, Iran (2014; Vol. 11, No. 4)

✉ Corresponding author:
R. Mosharraf, Dental Material Research Center and Department of Prosthodontics, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran

mosharraf@dnt.mui.ac.ir

Received: 28 February 2014

Accepted: 19 March 2014

INTRODUCTION

Intra-radicular posts are used to provide retention for restoration of the coronal structure of endodontically treated teeth [1-7].

In the recent years, the fiber reinforced composite (FRC) posts have become more popular because of their suitable physical characteristics that are similar to tooth structure [8, 9].

The FRC posts are cemented in root canal space using different resin cements [3]. The overall retention of FRC posts in the root canal depends on the bond strength between different parts of the combined 'sandwich' post-cement-dentin assembly [10-13]. Many of the fiber post failures occur between the root canal wall and adhesive resin cement [14, 15]. So, understanding the factors that interfere with the bonding between the root canal wall and resin cement is important [16]. One of these interfering factors is the root canal sealer remnant [17]. The zinc oxide-eugenol-based sealers have the widest use today. These sealers can collect free radicals that disturb the polymerization reaction of resin cements [18]. It has been claimed that this can decrease the bond strength between the FRC post and root canal dentin [2, 15, 18-20].

However, other researchers have reported that eugenol-containing sealers do not have any significant reduction in the adhesion between cemented FRC post with resin cement to the root wall [18, 21-26]. The aim of this study was to evaluate the effect of the type of endodontic sealer on the bond strength of FRC posts cemented with resin cement to the root wall dentin. The null hypothesis investigated was that the bond strength of FRC posts cemented with resin cement in the presence of different endodontic sealers is not significantly different.

MATERIALS AND METHODS

In this *in vitro* study, 20 extracted human mandibular first premolars were selected.

A total sample size of 20 (at least 10 per group) was required to detect a difference of at least 80% between any two groups with a power of 84% at a 5% significance level. The selected teeth did not have any caries, cracks or fractures, resorption, open apex or previous root canal treatments.

The teeth were cleaned of calculus or soft tissue remnants and were placed for two hours in 2.5% *NaOCl* (Golrang, Golrang co., Tehran, Iran) and then stored in 0.1% *NaN₃* solution.

Diamond discs (Ref.070, *D&Z*, Berlin, Germany) mounted in a dental lathe machine (*KaVo* Polishing Unit, *EWL* 80, Germany) were used at low speed under constant water irrigation for removing teeth crowns to achieve a 15-mm root length. Barbed broaches (*Dentsply/Maillefer*, Ballaigues, Switzerland) were used to remove pulp tissues. The same operator performed canal instrumentation using the step-back technique (1-mm short of the apical foramen). The master apical file was the number 35 K-file (*Dentsply/Maillefer*, Switzerland).

During canal preparation stages, the canals were irrigated with 5.25% sodium hypochlorite solution (Golrang, Iran).

Finally, paper points were used to dry the root canals (*Aria dent*, *Asia Chemi Teb Co*, Tehran, Iran).

The roots were randomly divided into two groups of 10 specimens each (Table 1). In each group, obturation was performed by the vertical condensation method using one type of root canal sealers (Table 1) and gutta-percha (*Aria dent*, Tehran, Iran).

Table 1. Root Canal Sealers Used in This Study

| Root Canal Type | Trade Mark | Manufacturer |
|-----------------|------------------|--|
| Resin-Based | AH ₂₆ | Dentsply Caulk, Milford, Germany |
| Eugenol-Based | Endofill | Dentsply, Indústria e Comércio Ltda., Petrópolis, RJ, Brazil |

Provisional restorative material (GC Caviton; GC Dental Products Corp., Tokyo, Japan) was used to fill the coronal root canal orifices and the teeth were stored for one week in 100% humidity at 37°C to ensure the setting of the used root canal sealers.

Then, coronal gutta-percha of each root was removed to a depth of 10-mm with a Gates Glidden drill #3 (Dentsply/Maillefer, Switzerland) and 4-mm gutta-percha was preserved in their apices. All post spaces were prepared to a No. 3 post drill (Fibio, Anthogyr, Sallanches, France). Finally, the canals were irrigated with distilled water and dried with paper points (Aria dent, Tehran, Iran).

For post length and diameter similarity, a glass reinforced fiber post size #3 (Hetco fiber post, Hakim Toos, Mashhad, Iran) was tried in the post spaces and then all posts were cut to the length of 10-mm from their apex with diamond discs (Ref.070, D&Z) mounted in a dental lathe machine (KaVo Polishing Unit, KaVo EWL) under water irrigation. In all groups, the shortened posts were cleaned with 70% ethanol for 60s, rinsed with distilled water and air-dried.

According to a previous study (6), the posts were immersed in 20% H₂O₂ for 20 minutes at room temperature. The posts were rinsed with running water for 2 minutes. After air-drying, the post surfaces were painted with a single layer of a silane coupling agent (Ultradent® Porcelain Etch and Silane, Ultradent Products Inc., UT, USA) for 60s and dried for 60s with gentle air stream.

In all groups, the root canal walls were conditioned with an autopolymerizing primer (ED-primer, Kuraray Medical Inc., Tokyo, Japan) for 60s. Then, the post spaces were air-dried and the excess primer was removed with paper points (Aria dent, Iran). In the cementation stage, equal amounts of base and catalyst pastes of an adhesive composite resin cement (Panavia F2.0, Kuraray Medical Inc., Tokyo, Japan) were mixed and applied on the prepared post surfaces and into the post spaces

with a lentulo spiral instrument (Dentsply/Maillefer, Switzerland). The fiber posts were inserted into the root canals using gentle finger pressure. After removing the excess cement around the post, oxygen-inhibiting gel (Oxy-guard II, Kuraray Medical Inc. Tokyo, Japan) was used to protect the remaining cement. The resin cement was light cured for 60s by a halogen light unit with 500-mW/cm² intensity (Coltolux50, Coltene, Altstätten, Switzerland). Before each light exposure, Coltolux light meter (Coltene, Altstätten, Switzerland) was used for monitoring accurate light intensity of the light output.

After storing all specimens in 37°C saline for one week, all the specimens were subjected to thermocycling treatment for 5000 cycles at temperatures alternating between 5 and 55°C for 30s each with an intermediate pause of 15 seconds.

Each dental root was sectioned perpendicular to its long axis using a diamond disc (Ref.070, D&Z, Germany) mounted in a cutting machine (TL-3000, Vafaei Industrial, Tehran, Iran) at low speed under water irrigation to create three post/dentin slices (coronal, middle and apical) with 3-mm thickness for each slice. Due to using tapered fiber posts, the post diameters and each slice size were measured using a digital caliper (Mitutoyo digital caliper 500-714-10, Mitutoyo Co, Tokyo, Japan) with 0.01 mm accuracy.

Push out test was performed with a universal testing machine (Walt+Bai AG Testing Machines Industries trass 4, Löhningen, Switzerland) at across head speed of 1 mm/min. The push-out pin was placed on the center of the apical end of the sliced fiber post and in an apico-coronal direction without inserting extra forces on the surrounding root canal walls. Therefore, it was necessary to make three push-out pins in three diameters (0.7, 0.9 and 1.0 mm) that were used for each three-root section, respectively (apical, middle and coronal parts). The peak force (*N*) required to extrude the fiber post from each root slice was

recorded for all specimens. The bond strength in MPa was calculated with the following formula:

$$A = \pi(r_1 + r_2)\sqrt{(r_1 - r_2)^2 + h^2}$$

In this formula, π is the constant 3.14, r_1 is the coronal post radius, r_2 is the apical post radius and h is the slice thickness in mm.

The data were analyzed (SPSS/PC16.0; SPSS Inc., Chicago, Ill) using two-way ANOVA and Post Hoc Tukey test at $P < 0.05$ level of significance.

RESULTS

Table 2 shows the mean tensile bond strength (TBS) and standard deviation (SD) values for all experimental groups in different root canal regions.

The two-way ANOVA showed that root canal sealer as a main factor ($P=0.037$) had significant effect on BS, but root canal dentin regions ($P=0.811$) and the interaction between root canal sealers and root canal regions ($P=0.258$) had no significant effects on BS (Table 3). The AH₂₆ had the highest TBS mean value especially in the apical region. The lowest TBS mean value was seen in the Endofill group and in the apical region. Post Hoc Tukey test revealed that there were no significant differences between different root canal regions in both groups ($P > 0.05$) (Table 4).

DISCUSSION

The results of this investigation rejected the null hypothesis that different endodontic sealers do not have any effect on the bond strength of FRC posts cemented with resin cement.

Table 2. Descriptive Statistics and Mean TBS (MPa) and SDs for Study Groups (n=10)

| Cement | Region | Mean | Std. Deviation | 95% Confidence Interval | |
|------------------|---------|------|----------------|-------------------------|-------------|
| | | | | Lower Bound | Lower Bound |
| Endofill | Coronal | 2.41 | .90 | 1.54 | 1.54 |
| | Middle | 1.79 | 1.03 | .92 | .92 |
| | Apical | 1.74 | 1.41 | .88 | .88 |
| AH ₂₆ | Coronal | 2.41 | 1.24 | 1.55 | 1.55 |
| | Middle | 2.61 | 1.73 | 1.74 | 1.74 |
| | Apical | 3.18 | 1.65 | 2.32 | 2.32 |

Table 3. Two-way ANOVA Results on the Effects of Surface Treatments, Root Canal Regions and Their Interaction on the TBS

| Source | Type III Sum of Squares | df | Mean Square | F | Sig. |
|-----------------|-------------------------|----|-------------|--------|------|
| Corrected Model | 14.50 ^a | 5 | 2.90 | 1.55 | .18 |
| Intercept | 334.52 | 1 | 334.52 | 179.60 | .00 |
| Cement | 8.53 | 1 | 8.53 | 4.58 | .03 |
| Region | .78 | 2 | .39 | .21 | .81 |
| Cement * Region | 5.18 | 2 | 2.59 | 1.39 | .25 |
| Error | 100.58 | 54 | 1.86 | | |
| Total | 449.60 | 60 | | | |
| Corrected Total | 115.08 | 59 | | | |

a. R Squared = .126 (Adjusted R Squared = .045)

According to the present study, the mean tensile bond strength (TBS) of fiber posts that were luted in the root canals with resin based sealer (AH₂₆) was significantly higher than those luted with eugenol containing sealer (Endofill). Other studies have also showed that eugenol containing root canal sealers can decrease the bond strength of resin cements [1-3, 16, 18-20, 27]. It has been mentioned that eugenol (2-methoxy-4-allylphenol) can spread in dentinal tubules and its phenolic components can deactivate the molecules in the growing polymer chains and jeopardize resin cement setting and decrease the bond strength [1, 3]. However, other studies did not find any statistically significant difference between different types of root canal sealer on the retention of glass fiber posts using resin cements [21, 22, 24, 25, 28]. On the other hand, a greater amount of eugenol is released during the first two weeks of using eugenol containing sealer [18]. In the present study, post cementation was performed one week after completing endodontic treatment. So the remnants of the eugenol containing sealer could interfere with the polymerization reaction of resin cement and decrease its bond strength.

However, some authors reported that there are no differences between effects of various root canal sealers on the tensile bond strength of fiber posts [21-26, 28].

It is stated that during post space preparation, most of the root canal sealer remnants are removed and the amount of debris and free eugenol available to inhibit the polymerization reaction of the resin cement is decreased.

Therefore, creating a clean post space is one of the most important factors in achieving bonding with resin cements [28].

Another technique for cleaning the post space wall is phosphoric acid etching followed by water rinsing [11, 29].

Self-etching systems that eliminate etching, rinsing, and drying steps may decrease the bond strength of self-etching systems due to incomplete cleaning of the root canal space [30, 31].

The resin cement system used in this study has a self-etching bonding system (ED primer) that is less aggressive than etching with 37% phosphoric acid [29, 32].

So the created thick smear layer in the post space might decrease the bond strength of the used resin cement in this study.

Table 4. Post Hoc Test (Tukey's HSD) for Comparing All Test Groups

| (I) Region | (J) Region | Mean Difference (I-J) | Std. Error | Sig. | 95% Confidence Interval | |
|------------|------------|-----------------------|------------|------|-------------------------|-------------|
| | | | | | Lower Bound | Upper Bound |
| Coronal | Middle | .21 | .431 | .87 | -.82 | 1.25 |
| | Apical | -.05 | .431 | .99 | -1.09 | .98 |
| Middle | Coronal | -.21 | .431 | .87 | -1.25 | .82 |
| | Apical | -.26 | .431 | .81 | -1.30 | .77 |
| Apical | Coronal | .05 | .431 | .99 | -.98 | 1.09 |
| | Middle | .26 | .431 | .81 | -.77 | 1.30 |

Based on observed means.

The error term is Mean Square (Error) = 1.863.

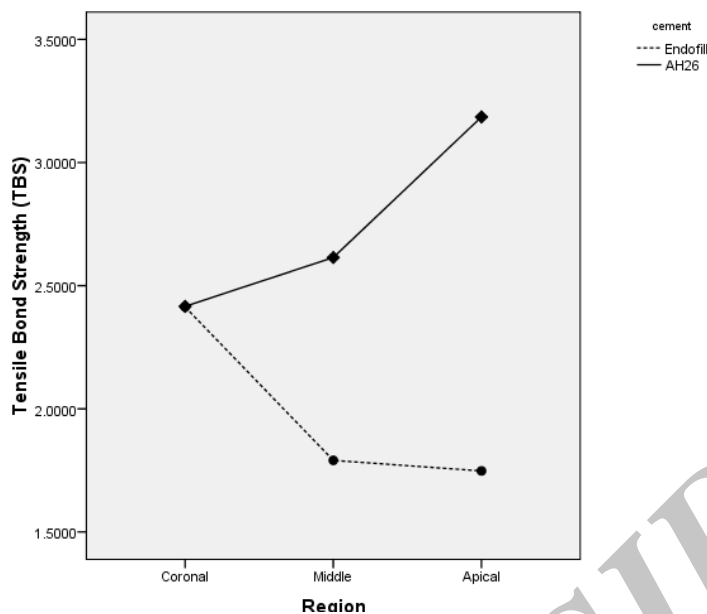


Fig 1. Results for tensile bond strength in all experimental groups

Bond strength of resin cement can be at the highest level if the orifices of dentinal tubules are kept open [2], but eugenol can spread in these tubules and modify the surface of the cement resin and decrease bond strength [3]. It has been showed that using alcohol or acid conditioning in the post space can increase bond strength [32]. The self-etching system (ED-primer) that was used in this study did not condition the post space wall and the lower bond strength of the Endofill group and decreasing the bond strength from the coronal to apical region in this group can be explained by this fact. It is interesting that in AH₂₆ group (resin based sealer) the bond strength was increased in more apical regions (Figure 1).

This can be due to lower penetration of the resin sealer into dentinal tubules or the presence of residues of resin based sealer in the apical portion of post space. These residues can bond with post space walls and may help better bonding with resin cement.

This finding is in accordance with studies [33, 34] that used resin cements and resin based sealers and found highest push out strengths in the apical sections.

Therefore, resin based sealers can be used in the inaccessible apical site within the root canal space; thereby creating strong bonding strength as well as a fluid-tight seal [34]. Jha [33] imputed a greater bond strength in the apical third to factors such as the greater wear of this region by endodontic reamers and creating a clean dentin that comes in better contact with the bonding agents. In addition,, he stated that there is an intimate contact between the post and root canal wall in this area, while the misfit between post and root canal space in the coronal region results in a greater volume of resin cement that can increase stress in the cement layer due to polymerization shrinkage.

Moreover, because the cement layer is the weakest area between the post and the post space wall, the greater thickness of the cement may be the cause of the reduced bonding strength observed in the coronal third [14]. Although these argumentations can explain the higher bonding strength in the apical third of specimens in the AH₂₆ group, they cannot clarify the opposite condition in the Endofill group.

In the Endofill group, our results are in accordance with studies that have reported higher bonding strength in the more coronal thirds [5, 11, 35].

The higher tubular density and diameter of the coronal third of the post space are more than the other regions. Furthermore, the dentinal hybridization is not uniform and lateral branches of resin tags are not seen in the apical thirds of post space [36]. Furthermore, more access to the coronal third of the canal makes etching and applying the adhesive agents [36, 37] and direct light transmission to canal walls [36] more effective in this area. However, Aksornmuang *et al.* [35] found no significant differences in the bond strengths among different regions of the root canal walls.

They related this result to this fact that their used light source had a light intensity of about 90 ± 3 mW/cm², which was not enough to completely cure composite resin. The present study had some limitations. For example, the specimens had no coronal tooth structure, only one type of fiber post and adhesive were evaluated and the influences of fatigue loading on the push out TBS of specimens were not investigated.

In vitro tensile tests for measuring bond strength may not be exactly representative of the clinical conditions. Therefore, clinical studies should be performed to validate the results of the present study.

CONCLUSION

Within the limitation of this in vitro study it was concluded that:

1. The type of root canal sealer had significant effect on the bond strength of cemented fiber posts.
2. Eugenol-based sealers (Endofill) significantly reduced the bond strength of fiber posts luted with resin cement.
3. There were no significant differences between different root canal regions in both groups.

REFERENCES

- 1- Dias LL, Giovani AR, Silva Sousa YT, Vansan LP, Alfredo E, Sousa-Neto MD, et al. Effect of eugenol-based endodontic sealer on the adhesion of intraradicular posts cemented after different periods. *J Appl Oral Sci.* 2009 Nov-Dec;17(6):579-83.
- 2- Demiryurek EO, Kulunk S, Yuksel G, Sarac D, Bulucu B. Effects of three canal sealers on bond strength of a fiber post. *J Endod.* 2010 Mar;36(3):497-501.
- 3- Aleisa K, Alghabban R, Alwazzan K, Morgano SM. Effect of three endodontic sealers on the bond strength of prefabricated fiber posts luted with three resin cements. *J Prosthet Dent.* 2012 May;107(5):322-6.
- 4- Mosharraf R, Baghaei Yazdi N. Comparative evaluation of effects of different surface treatment methods on bond strength between fiber post and composite core. *J Adv Prosthodont.* 2012 May;4(2):103-8.
- 5- Mosharraf R, Haerian A. Push-out bond strength of a fiber post system with two resin cements. *Dent Res J (Isfahan).* 2011 Dec;8(Suppl 1):S88-93.
- 6- Mosharraf R, Ranjbarian P. Effects of post surface conditioning before silanization on bond strength between fiber post and resin cement. *J Adv Prosthodont.* 2013 May;5(2):126-32.
- 7- Khamverdi Z, Abbasi S, Habibi E, Kasraei S, Azarsina M, Ebadi S. Effect of storage time on microtensile bond strength between quartz fiber post and composite core after different post surface treatments. *J Conserv Dent.* 2011 Oct;14(4):361-5.
- 8- Huber L, Cattani-Lorente M, Shaw L, Krejci I, Bouillaguet S. Push-out bond strengths of endodontic posts bonded with different resin-based luting cements. *Am J Dent* 2007 Jun;20(3):167-72.
- 9- Rathke A, Haj-Omer D, Muche R, Haller B. Effectiveness of bonding fiber posts to root canals and composite core build-ups. *Eur J Oral Sci.* 2009 Oct;117(5):604-10.

- 10- Zicari F, De Munck J, Scotti R, Naert I, Van Meerbeek B. Factors affecting the cement-post interface. *Dent Mater.* 2012 Mar;28(3):287-97.
- 11- Akgungor G, Akkayan B. Influence of dentin bonding agents and polymerization modes on the bond strength between translucent fiber posts and three dentin regions within a post space. *J Prosthet Dent.* 2006 May;95(5):368-78.
- 12- Akgungor G, Sen D, Aydin M. Influence of different surface treatments on the short-term bond strength and durability between a zirconia post and a composite resin core material. *J Prosthet Dent.* 2008 May;99(5):388-99.
- 13- Ferrari M, Cagidiaco M, Grandini S, De Sanctis M, Goracci C. Post placement affects survival of endodontically treated premolars. *J Dent Res.* 2007 Aug;86(8):729.
- 14- Gomes MF, Botta SB, Matos AB, Netto NG. The interference of the cleaning procedure of root walls with two different solvents on the adhesion of fiberglass intraradicular posts. *J Contemp Dent Pract.* 2012 May;13(3):275-9.
- 15- Serafino C, Gallina G, Cumbo E, Ferrari M. Surface debris of canal walls after post space preparation in endodontically treated teeth: a scanning electron microscopic study. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod.* 2004 Mar;97(3):381-7.
- 16- Teixeira CS, Pasternak-Junior B, Borges AH, Paulino SM, Sousa-Neto MD. Influence of endodontic sealers on the bond strength of carbon fiber posts. *J Biomed Mater Res B Appl Biomater.* 2008 Feb;84(2):430-5.
- 17- Demiryurek EO, Kulunk S, Sarac D, Yuksel G, Bulucu B. Effect of different surface treatments on the push-out bond strength of fiber post to root canal dentin. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod.* 2009 Aug;108(2):e74-80.
- 18- Izadi A, Azarsina M, Kasraei S. Effect of eugenol-containing sealer and post diameter on the retention of fiber reinforced composite posts. *J Conserv Dent.* 2013 Jan;16(1):61-4.
- 19- Baldissara P, Zicari F, Valandro LF, Scotti R. Effect of root canal treatments on quartz fiber posts bonding to root dentin. *J Endod.* 2006 Oct;32(10):985-8.
- 20- Aleisa K, Al-Dwairi Z, Lynch E, Lynch C. In Vitro Evaluation of the Effect of Different Endodontic Sealers on Retentive Strength of Fiber Posts. *Oper Dent.* 2013 Sep-Oct;38(5):539-44.
- 21- Manicardi CA, Versiani MA, Saquy PC, Pecora JD, de Sousa-Neto MD. Influence of filling materials on the bonding interface of thin-walled roots reinforced with resin and quartz fiber posts. *J Endod.* 2011 Apr;37(4):531-7.
- 22- Aggarwal V, Singla M, Miglani S, Kohli S. Effect of different root canal obturating materials on push-out bond strength of a fiber dowel. *J Prosthodont.* 2012 Jul;21(5):389-92.
- 23- Han G, Xiong Z, Chen Y. [Effects of two endodontic sealers on the bond strength of two fiber posts]. *Hua Xi Kou Qiang Yi Xue Za Zhi.* 2011 Oct;29(5):497-500.
- 24- Kurtz JS, Perdigao J, Geraldeli S, Hodges JS, Bowles WR. Bond strengths of tooth-colored posts, effect of sealer, dentin adhesive, and root region. *Am J Dent.* 2003 Sep;16 Spec No:31A-36A.
- 25- Mannocci F, Ferrari M, Watson TF. Microleakage of endodontically treated teeth restored with fiber posts and composite cores after cyclic loading: a confocal microscopic study. *J Prosthet Dent.* 2001 Mar;85(3):284-91.
- 26- Souza-Junior EJ, Bueno VC, Dias CT, Paulillo LA. Effect of endodontic sealer and resin luting strategies on pull-out bond strength of glass fiber posts to dentin. *Acta Odontol Latinoam.* 2010;23(3):216-21.
- 27- Paul SJ, Scharer P. Effect of provisional cements on the bond strength of various adhesive bonding systems on dentine. *J Oral Rehabil.* 1997 Jan;24(1):8-14.

- 28- Davis ST, O'Connell BC. The effect of two root canal sealers on the retentive strength of glass fibre endodontic posts. *J Oral Rehabil.* 2007 Jun;34(6):468-73.
- 29- Zhang L, Huang L, Xiong Y, Fang M, Chen JH, Ferrari M. Effect of post-space treatment on retention of fiber posts in different root regions using two self-etching systems. *Eur J Oral Sci.* 2008 Jun;116(3):280-6.
- 30- Van Landuyt KL, Kanumilli P, De Munck J, Peumans M, Lambrechts P, Van Meerbeek B. Bond strength of a mild self-etch adhesive with and without prior acid-etching. *J Dent.* 2006 Jan;34(1):77-85.
- 31- Jacques P, Hebling J. Effect of dentin conditioners on the microtensile bond strength of a conventional and a self-etching primer adhesive system. *Dent Mater.* 2005 Feb;21(2):103-9.
- 32- Tjan AH, Nemetz H. Effect of eugenol-containing endodontic sealer on retention of prefabricated posts luted with adhesive composite resin cement. *Quintessence Int.* 1992 Dec;23(12):839-44.
- 33- Jha P, Jha M. Retention of fiber posts in different dentin regions: an in vitro study. *Indian J Dent Res.* 2012 May;23(3):337-40.
- 34- Babb BR, Loushine RJ, Bryan TE, Ames JM, Causey MS, Kim J, et al. Bonding of self-adhesive (self-etching) root canal sealers to radicular dentin. *J Endod.* 2009 Apr;35(4):578-82.
- 35- Aksornmuang J, Foxton RM, Nakajima M, Tagami J. Microtensile bond strength of a dual-cure resin core material to glass and quartz fibre posts. *J Dent.* 2004 Aug;32(6):443-50.
- 36- Topcu FT, Erdemir U, Sahinkesen G, Mumcu E, Yildiz E, Uslan I. Push-out bond strengths of two fiber post types bonded with different dentin bonding agents. *J Biomed Mater Res B Appl Biomater.* 2010 May;93(2):359-66.
- 37- Perdigao J, Gomes G, Lee IK. The effect of silane on the bond strengths of fiber posts. *Dent Mater.* 2006 Aug;22(8):752-8.