

RESEARCH PAPER

Biosynthesis of Gold Nanoparticles Using Aqueous Extract of Stem of *Periploca Aphylla* Plant

Massoud Kaykhaii¹, Nafiseh haghpaizir^{1,*} and Jafar Walisadeh²

¹ Department of Chemistry, Faculty of Sciences, University of Sistan and Baluchestan, Zahedan, Iran

² Department of Biology, Faculty of Sciences, University of Sistan and Baluchestan, Zahedan, Iran

ARTICLE INFO

Article History:

Received 05 February 2018

Accepted 12 March 2018

Published 01 April 2018

Keywords:

Au Nanoparticles

Characterization

Periploca aphylla

UV/Vis Spectrophotometry

ABSTRACT

This present work reports an ecofriendly approach for the synthesis of gold nanoparticles (Au NPs) using aqueous stem extract of *Periploca aphylla* as a reducing and stabilizing agent, has been discussed. This approach is simple, cost-effective and stable for a long time, reproducible at room temperature and in an eco-friendly manner to obtain a self-assembly of Au NPs. Two parameters were optimized for the fabrication of gold nanoparticles including the pH and contact time. The resulting nanoparticles are characterized using UV-vis, TEM, XRD and FT-IR spectroscopic techniques. UV-visible spectra of the aqueous medium containing gold nanoparticles showed a surface plasmon resonance peak at 535 nm. Uniform spherical shapes were observed for biosynthesized Au NPs within range of 25–30 nm by transmission electron microscopy. XRD results confirmed the presence of gold nanoparticles with face centered cubic structure. FT-IR analysis was performed to analyze the biomolecules responsible for the reduction of Au NPs.

How to cite this article

Kaykhaii M, haghpaizir N, Walisadeh J. Biosynthesis of Gold Nanoparticles Using Aqueous Extract of Stem of *Periploca Aphylla* Plant. J Nanostruct, 2018; 8(2):152-158. DOI: 10.22052/JNS.2018.02.005

INTRODUCTION

Application of nano-scale materials, ranging from 1–100 nm, is an emerging area of nanotechnology. Nanoparticles exhibit completely new and improved properties based on specific characteristics such as size, distribution and morphology, if compared with larger particles of the bulk material they are made of. Nanomaterials have a long list of applicability in improving the human life and its environment.[1],[2] Nanoparticles present a higher surface to volume ratio with decreasing size of nanoparticles. As specific surface area of nanoparticles is increased, their biological effectiveness can increase due to the increase in surface energy.[3]

Different methods are used for the synthesis of gold nanoparticles. A number of methods

including physical and chemical processes [4-10], electrochemical reduction [11-12] photochemical reduction [13-14] and heat evaporation [15-16] for synthesis of metal nanoparticles were developed considering the real life application of nanoparticles in the area of medicine [17], catalysis [18] detection [19], drug delivery[20] etc. Chemical synthesis methods lead to some chemically toxic substances being absorbed on the surface that may have negative effects on medical applications, limiting them.[21] Therefore, the need for the development of a clean, reliable, biocompatible, benign, and eco-friendly process to synthesize nanoparticles without using toxic chemicals leads to turning researchers toward “green” chemistry and bioprocesses.[22] Biological methods for nanoparticle synthesis using microorganisms,

* Corresponding Author Email: haghpaizir_65@yahoo.com

enzymes, and plants or plant extracts have been suggested as possible ecofriendly alternatives to chemical and physical methods [23],[24]. Recently the studies started under green chemistry for the search of benign methods for the development nanoparticles and searching antibacterial, antioxidant, and antitumor activity of natural products. Biosynthetic processes have received much attention as a viable alternative for the development of metal nanoparticles where plant extract is used for the synthesis of nanoparticles without any chemical ingredients [25-29]. Bioinspired synthesis of nanoparticles has advantages over chemical and physical methods as it is a cost effective and environment friendly and does not need to use high pressure, energy, temperature and toxic chemicals. The main benefit of using the green chemistry route for the fabrication of gold nanoparticles is to fabricate a material that will be compatible for pharmaceutical and other biomedical applications since the toxic chemicals are not used during the fabrication of nanoparticles [30]. Moreover, using a plant extract can decrease the cost of preparation and eliminate the need for any special culture preparation and isolation technique compared with using bacteria and fungi for fabrication of nanoparticles [31].

Using plants for nanoparticle synthesis can be advantageous over other biological processes because it eliminates the elaborate process of maintaining cell cultures and can also be suitably scaled up for large-scale nanoparticle synthesis [32]. Moreover, plants have been used to fabricate nanoparticles since they are readily available, safe to handle, and they have a broad variability of metabolites that can aid in reduction [33].

MATERIALS AND METHODS

Preparation of plant extract

Periploca aphylla Stem shown in Fig. 1 was collected from Delfard region in Iran. Fresh Stems were used for the extraction of the active components. The Stems were shade dried for 2–3 weeks at room temperature and then powdered. Briefly, 1 g of Stem powder was weighed and mixed in 100 mL of de-ionized water and boiled at 30°C for 30 min . The obtained extraction was filtered using Whatman No. 1 filter paper and filtered to get the extract. then,the collected extract was centrifuged, in order to eliminate any biomaterials that could interfere with binding of Au ion to the biomass or construction of the nanoparticles. The

filtrate is used as reducing agent and stabilizer.

Synthesis of gold nanoparticles

Typical synthesis process of gold nanoparticles, 2 mL of *Periploca aphylla* extract is added to avigorously stirred 4 mL aqueous solution of $\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$ 1mM and the final volume was adjusted to 50 mL with deionised water at room temperature and stirring continued for 30 min. To initialize the reduction of gold ions, the pH of the solution is adjusted to be 4 using NaOH and HCl 1mM. Reduction takes place rapidly less than 1 min as indicated by stable light violet colour of the solution. At the end of reaction, the Au NPs solution thus obtained was purified by repeating the centrifugation thrice at 10000 rpm for 30 min at 4 °C followed by redispersion of the pellet in deionised water and studied by adjusting the effects of pH and time parameter on the synthesis rate and amonth of the Au NPs were monitored by UV-vis Spectrophotometer.

Characterization of Au NPs

The synthesized gold nanoparticles were subjected to UV–visible analysis in the wavelength range of 200–800 nm using Shimadzu spectrophotometer (Model UV-1800) operating at a resolution of 1 nm. A transmission electron microscope (EM10C) measurements were carried out to bring out the morphology of the green synthesized nanoparticles in terms of size and



Fig. 1. Photograph of *P.aphylla* used in the biosynthesis.

shape. Crystalline Au NPs were determined by Bruker D8advance X-ray diffraction (XRD) analysis using Cu K α radiation ($\lambda = 1.54060 \text{ \AA}$). The purified Au NPs were examined for the presence of biomolecules using FTIR analysis. The spectrum obtained from the dried sample was recorded on FTIR spectrum (Perkin–Elmer). A Metrohm model pH lab 827 meter was used for pH measurements.

RESULT AND DISCUSSION

Effect of pH on Au nanoparticles synthesis

pH play an important role in the nanoparticles synthesis, this factor induce the reactivity of leaf extract with gold ions. The effect of pH on the reduction of gold ion and synthesis of gold nanoparticles by *Periploca aphylla* extract was studied using UV-visible spectroscopy. Fig 2 shows the absorption spectra of gold nanoparticles formed at various pH values ranging e from 2 to 7 of the reaction mixture consisting of 4ml aqueous AuCl₄ 1mM and 2ml *Periploca aphylla* extract at wavelength 535 nm after 30 min. The optimum pH for the completion of reaction from this study was 4 (Fig. 3). In low pH, small with broadening Surface Plasmon Resonance (SPR) band was formed indicates formation of smal size of nanoparticles. In *Periploca aphylla* Stem mediated synthesis acidic pH 4 shows narrow peak at 535 nm with maximum production with sharp peak.

The sharp peak indicates formation of spherical shape of gold nanoparticles. [35],[36]. Several results are reported pH is plays an important role in shape and size control synthesis process of gold nanoparticles[37].

The present investigation indicates acidic pH is more suitable for synthesis of gold nanoparticles using *Periploca aphylla* of extract of stem. but, Pandey et al. [38] reported that the gold nanoparticles show maximum stability at the pH 10 by aqueous extract of *Momordica charantia*.

Effect of time on Au nanoparticles synthesis

The effect of the incubation time was studied by monitoring the absorption spectra of gold nanoparticles formed in the reaction media at different durations every 5 min at wavelength 535 nm after adding 2ml of *Periploca aphylla* extract to 4 ml aqueous solution of HAuCl₄.3H₂O 1mM which was adjusted to pH 4 and the reaction was monitored using UV/Vis spectrophotometer from 0 to 30 min in order to optimise the time required for the reaction completion. Fig. 2 shows the UV-Vis spectra of reduction of gold ions to gold nanoparticles using *Periploca aphylla* extract at different reaction times. It was found that when the incubation time was less than 1 min, gold nanoparticles appeared. Moreover, it was observed that by increasing the time of reaction,

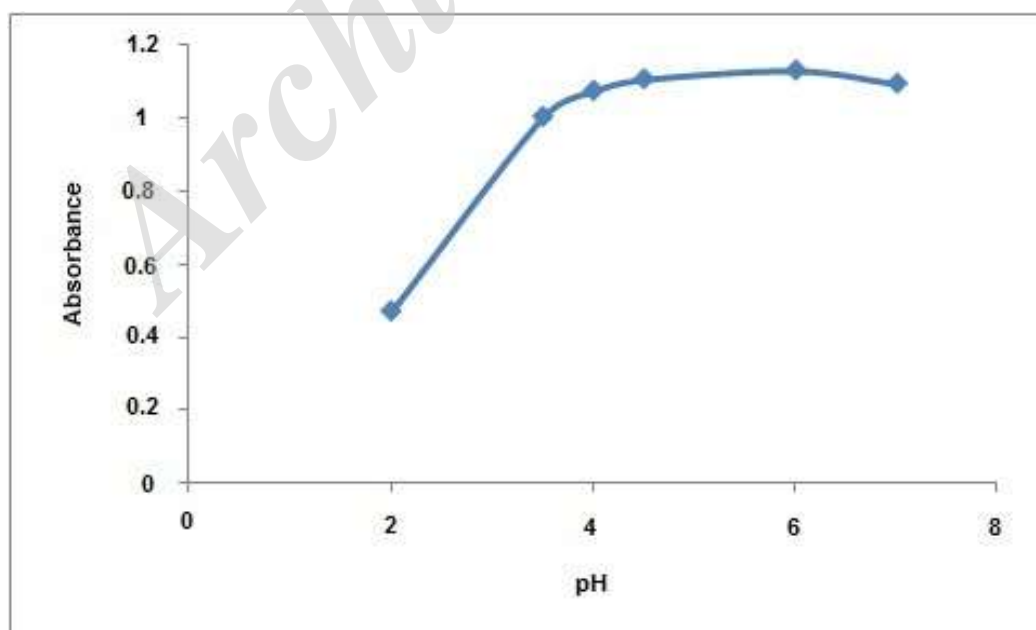


Fig. 2. The effect of pH on synthesis of Au nanoparticles by tem extract of P.aphylla at wavelength 535 nm

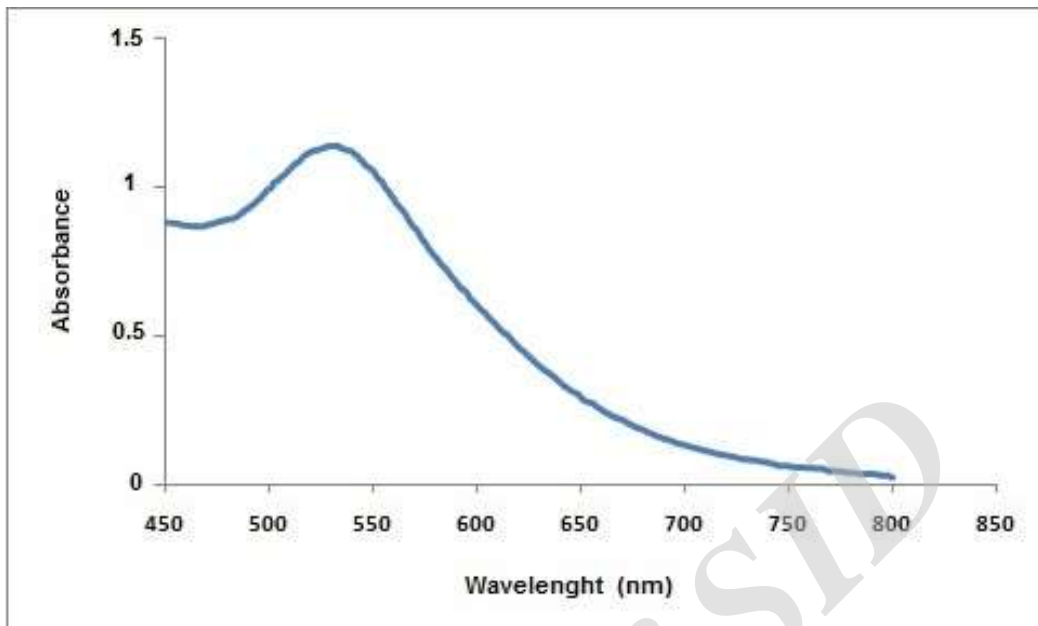


Fig. 3. UV visible spectra of Au nanoparticles synthesized by stem extract of P.aphylla

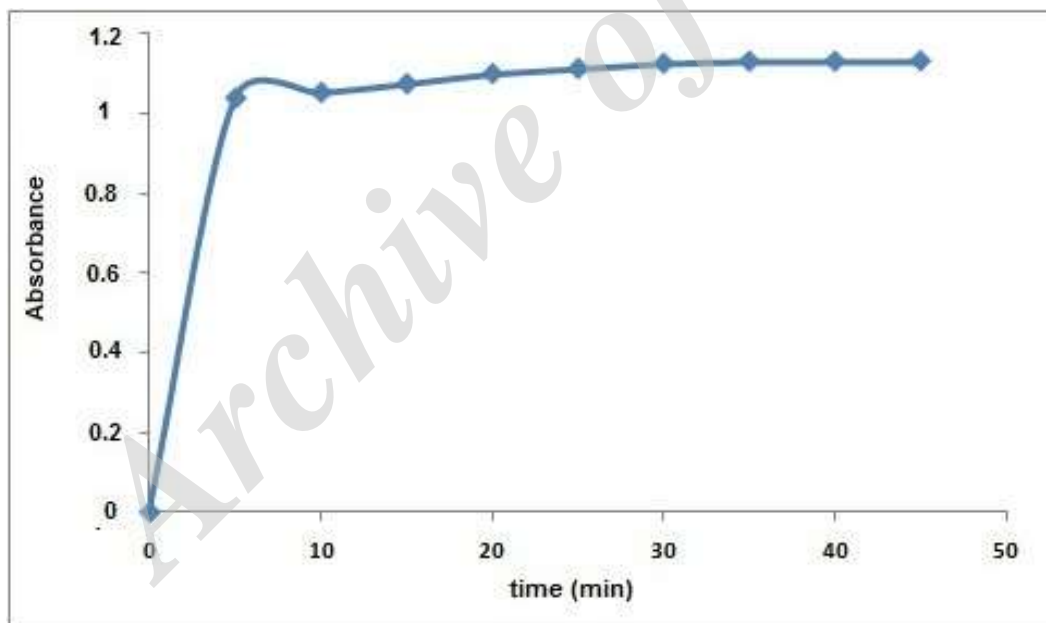


Fig. 4. The effect of time on synthesis of Au nanoparticles by P.aphylla at wavelength 535 nm

the absorbance intensity and amount of formed GNPs at wavelength 535 nm increased within 30min, but after that only a slight variation can be observed. From the spectrum, it was found that the optimum incubation time for the completion of reaction in this study was 30 min. In addition, it was observed that increasing the incubation

time to more than 30 min did not increase the absorption significantly, which indicates the stability of biosynthesized nanoparticles, whereas synthesis from other plant extracts takes 2 to 4 h. When employing microorganisms, the formation of gold nanoparticles is a slow process (reaction time between 24 and 120 h).[38]. This

stability is resulting from the presence of organic compounds that are along with nanoparticles that those existence ascertained by helping FT-IR spectra.

Transmission Electron Microscope (TEM)

In addition to UV spectroscopy which confirms reduction and shape of gold ions to gold nanoparticles. The size, shape and distribution of

synthesized gold nanoparticles were characterized by Transmission Electron Microscope. TEM image of the GNPs synthesized at pH 4 shows the presence of spherical monodispersed nanoparticles ranging from 25 to 30 nm and has an average size of about 27 nm (Fig. 5).

X-ray diffraction

X-ray Diffraction pattern was recorded for the

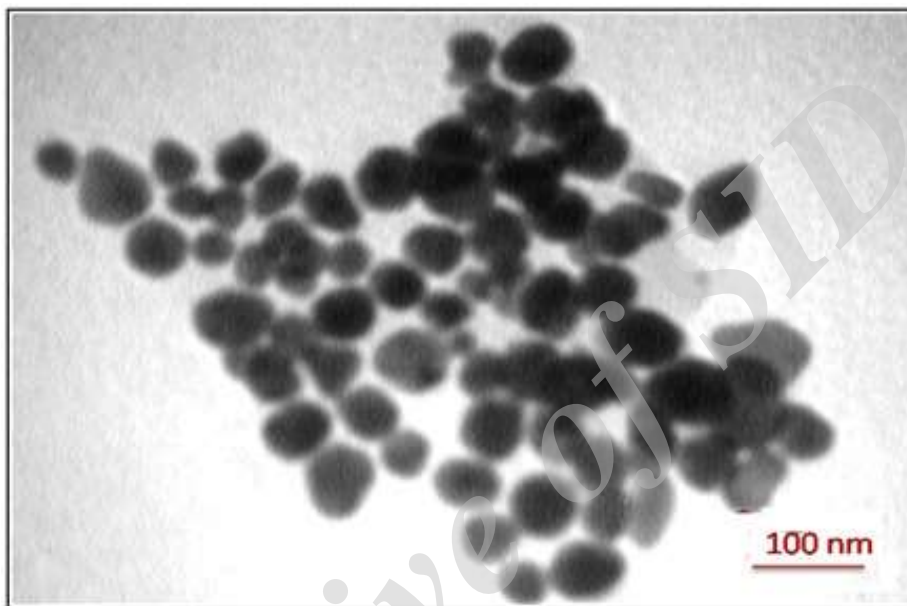


Fig. 5. TEM image of gold nanoparticles synthesized by stem extract of P.aphylla

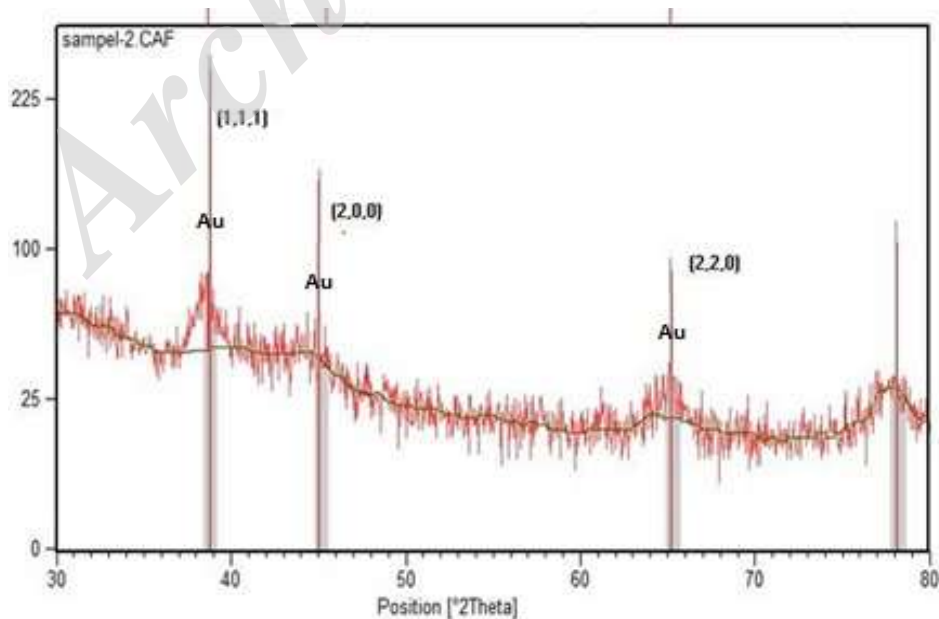


Fig. 6. XRD pattern of Aunanoparticles synthesized by stem extract of P. aphylla

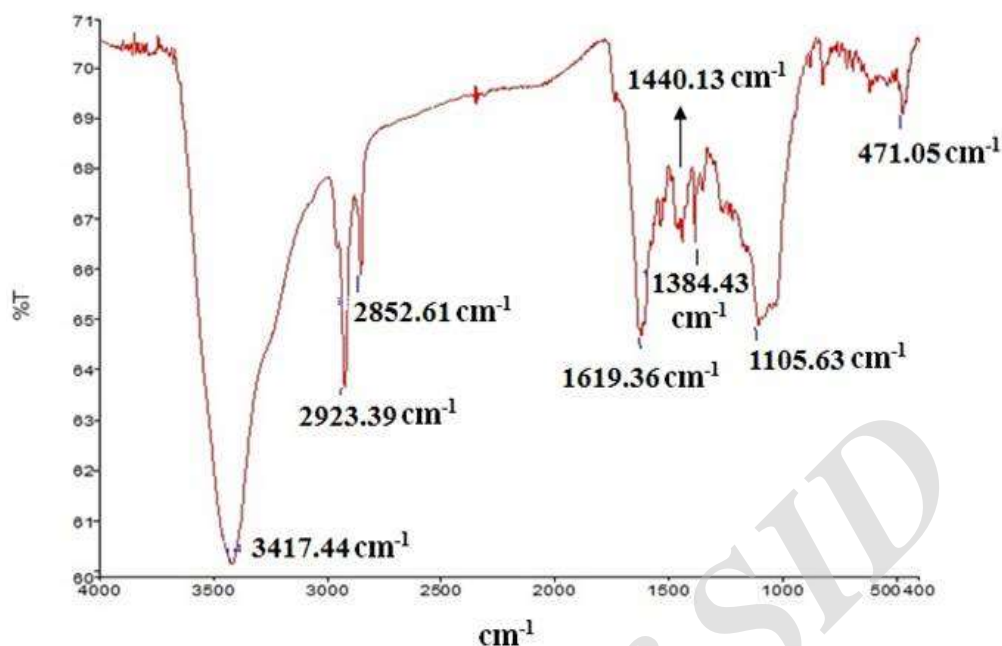


Fig. 7. FTIR spectra of Au nanoparticles synthesized by stem extract of *P.aphylla*

synthesized Au NPs (Fig. 6). The diffraction peak at 2θ values 38.68° , 45.48° , 65.15° assigned to the (1 1 1), (2 0 0), (2 2 0) of lattice plane of face centered cubic (fcc) for Au nanoparticle, respectively. The average size of nanoparticles was calculated using Debye-Scherrer's equation [39] by determining the width of the peaks and found to be 28, 22 and 32 nm respectively which is fairly in agreement with the TEM measurement.

Fourier transform infrared spectroscopy

FTIR measurement was carried out to identify the possible biomolecules in extract of stem of *Periploca aphylla* responsible for capping leading to efficient stabilization of the gold nanoparticles. Prominent IR bands (Fig. 6a and 7b) are observed at 3417.44 , 2923.39 , 2852.61 , 1619.36 , 1440.13 and 1105.63 cm^{-1} . Most of the FT-IR bands are characteristic of flavonoids and terpenoids present in the plant extract. The sharp bands at 3417.44 , and 2914 , 2847 cm^{-1} arise from -N-H and C-H stretching modes respectively. The absorption bands located at 1440.13 , 1384 and 1105.63 cm^{-1} may be attributed to -C-N , -C-O-C and -C-O stretching modes. The vibrational bands corresponding to bonds such as as-N-H , -C=C , -C-O , -C-O-C and -C-N are derived from the water soluble compounds such as flavonoids, terpenoids and protein present in extract of Stem of *periploca aphylla* plant. The presence of these

biomolecules in the extract could be responsible for the reduction of gold ions, formation and stabilization of the biosynthesized nanoparticles.

CONCLUSION

The spanning new and simple method for biosynthesis of Au NPs by *P. aphylla* extract offers a valuable contribution in the area of green synthesis and nanotechnology without adding using any toxic reagents and thus has potential for use in biomedical and agricultural applications. The nanoparticles were characterized by UV-vis, TEM, XRD and FTIR measurements. Rapid synthesis and amount of gold nanoparticles was attained maximum when altering such pH effective parameters. The optimum conditions for biosynthesis of Au NPs are observed to be at pH 4 and incubation time 30 min. The NPs synthesized were predominantly spherical with size of 25-30 nm *P.aphylla* extract was acts as a capping agent and reducing agent in the nanoparticles synthesis. It is a better source for the rapid synthesis of gold nanoparticles. The synthesis of Au NPs by *P.aphylla* extracts indicated that flavonoids, terpenoids and protein compounds could be responsible for the reduction of gold ions, formation and stabilization of the biosynthesized nanoparticles. This green method is a single step process, economic viability, non-toxic, ecofriendly and rapid production of nanoparticles. **CONFLICT OF INTEREST**

The authors declare that there are no conflicts of interest regarding the publication of this manuscript.

REFERENCE

- Cushing B. L., Kolesnichenko V. L., O'Connor C. J. Recent advances in the liquid-phase syntheses of inorganic nanoparticles. *Chem. Rev.* 2004; 104(9): 3893-3946
- Lekshmi NC, Sumi SB, Viveka S, Jeeva S, Brindha JR. Antibacterial activity of nanoparticles from *Allium sp.* *Microbiol. Biotech. Res.* 2012; 2(1): 115-119.
- Rao C. N. R, Kulkarni G. U, Thomas P. J, Edwards P. P. Metal nanoparticles and their assemblies. *Chem. Soc. Rev.* 2000; 29: 27-35.
- Brocchi E.A, Motta M.S, Solorzano I.G, Jena P.K, Moura F.J. Alternative chemical-based synthesis routes and characterization of nano-scale particles. *Mater Sci. Eng. B.* 2004; 112(2-3): 200-205.
- Janbey A, Pati R.K, Tahir S, Pramanik P. A new chemical route for the synthesis of nano-crystalline α -Al₂O₃ powder. *Europ. Ceram. Soc.* 2001; 21: 2285-2289.
- Hunt E.M, Plantier K.B, Pantoya M.L. Nano-scale reactants in the self-propagating high-temperature synthesis of nickel aluminide. *Acta Mater.* 2004; 52(11): 3183-3191.
- Yu D.G. Formation of colloidal silver nanoparticles stabilized by Na⁺-poly(γ -glutamic acid)-silver nitrate complex via chemical reduction process. *Colloids Surf. B.* 2007; 59(2): 171-178.
- Tan Y, Wang Y, Jiang L, Zhu D. Thiosalicylic acid-functionalized silver nanoparticles synthesized in one-phase system. *J. Colloid Interface Sci.* 2002; 249: 336-345. 9. Petit C, Lixon P, Pileni M.P. In situ synthesis of silver nanocluster in AOT reverse micelles. *J. Phys. Chem.* 1993; 97(49) 12974-12983.
- Vorobyova S.A, Lesnikovich A.I, Sobal N.S. Preparation of silver nanoparticles by interphase reduction. *Colloids Surf. A.* 1999; 152: 375-379.
- Liu Y.C, Lin L.H. New pathway for the synthesis of ultrafine silver nanoparticles from bulk silver substrates in aqueous solutions by sonoelectrochemical methods. *Electrochem. Commun.* 2004; 6: 1163-1168.
- Sandmann G, Dietz H, Pliehl W. Preparation of silver nanoparticles on ITO surfaces by a double-pulse method. *J. Electroanal. Chem.* 2000; 491:78-86.
- Mallik K, Witcomb M.J, Scurrill M.S. Self-assembly of silver nanoparticles in a polymer solvent: formation of a nanochain through nanoscale soldering. *Mater. Chem. Phys.* 2005; 9: 221-224.
- Keki S, Torok J, Deak G. Silver Nanoparticles by PAMAM-Assisted Photochemical Reduction of Ag(+). *J. Colloid Interface Sci.* 2000; 229 : 550-553.
- Bae C.H, Nam S.H, Park S.M. Formation of silver nanoparticles by laser ablation of a silver target in NaCl solution. *Appl. Surf. Sci.* 2002; 197-198: 628-634.
- Smetana A.B, Klabunde K.J, Sorensen C.M. Synthesis of spherical silver nanoparticles by digestive ripening, stabilization with various agents, and their 3-D and 2-D superlattice formation. *J. Colloid Interface Sci.* 2005; 284 (2) 521-526.
- Sanvicens N, Marco M.P. Multifunctional nanoparticles--properties and prospects for their use in human medicine. *Trends Biotechnol.* 2008; 26(8): 425-33.
- Johnson B.F.G. From clusters to nanoparticles and catalysis. *Coord. Chem. Rev.* 1999; 190-192: 1269-1285.
- Peng H, Soeller C, Cannell M.B, Bowmaker G.A, Cooney R.P, Sejdik J.T. Electrochemical detection of DNA hybridization amplified by nanoparticles. *Biosensors Bioelectron.* 2006; 21(9): 1727-1736.
- Bhumkar D.R, Joshi H.M, Sastry M, Pokharkar V.B. Chitosan reduced gold nanoparticles as novel carriers for transmucosal delivery of insulin. *Pharm. Res.* 2007; 24(8): 1415-1426.
- Panda T, Deepa K. Biosynthesis of Gold Nanoparticles *Nano sci. Nano technol.* 2011; 11: 10279-10294.
- Jain N, Bhargava A, Majumdar S, Panwar J. Extracellular biosynthesis and characterization of silver nanoparticles using *Aspergillus flavus* NJP08: a mechanism perspective. *Nanoscale.* 2011; 3(2): 635-641.
- Nestor A.R.V, Mendieta V.S, Lopez M.A.C, Espinosa R.M.G, Alatorre J.A.A. Solventless synthesis and optical properties of Au and Ag nanoparticles using *Camellia sinensis*. *Mater. Lett.* 2008; 62: 3103-3105. 24. Shankar S.S, Rai A, Ankamwar B, Singh A, Ahmad A, Sastry M. Biological synthesis of triangular gold nanoprisms. *Nat. Mater.* 2004; 3: 482-488.
- khadivi Derakhshan F, Dehnad A.R, Salouti M., Babaei H, Parsa L. Extracellular biosynthesis of gold nanoparticles by metal resistance bacteria: *Streptomyces griseus* Synth. *React. Inorg., Met.-Org., Nano-Met. Chem.* 2012; 42(6) 868-871.
- Parashar V, Parashar R, Sharma B, Pandey A.C. Parthenium leaf extract mediated synthesis of silver nanoparticles: A novel approach towards weed utilization. *Nanomater. Biostruct.* 2009; 4(1): 45-50.
- Philip D.. Biosynthesis of Au, Ag and Au-Ag nanoparticles using edible mushroom extract. *Spectrochim. Acta, Part A.* 2009; 73: 374-381.
- Smitha S.L, Philip D, Gopchandran K.G. Green synthesis of gold nanoparticles using *Cinnamomum zeylanicum* leaf broth. *Spectrochim. Acta, Part A.* 2009; 74: 735-739.
- Song J.Y, Jang H.K, Kim B.S. Biological synthesis of gold nanoparticles using *Magnolia kobus* and *Diopyros kaki* leaf extracts. *Process. Biochem.* 2009; 44(10): 1133-1138.
- Geethalakshmi R, Sarada D.V.L, Synthesis of plant-mediated silver nanoparticles using *Trianthema decandra* extract and evaluation of their anti microbial activities. *Int. J. Eng. Sci. Res. Technol.* 2010; 2(5): 970-975.
- Saxena A, Tripathi R.M, Singh R.P. Biological synthesis of silver nanoparticles by using onion (*Allium cepa*) extract and their antibacterial activity *Dig. J. Nanomater. Biostruct.* 2010; 5(2) : 427-432
- Vigneshwaran N, Nachane R.P, Balasubramanya R.H, Varadarajan P.V. A novel one-pot green synthesis of stable silver nanoparticles using soluble starch. *Carbohydr. Res.* 2006; 341(12) : 2012-2018.
- Alzahrani E, Welham K. Optimization Preparation of the Biosynthesis of Silver Nanoparticles Using Watermelon and Study of Its Antibacterial Activity. *Int. J. Basic Appl. Sci.* 2014; 3: 392-400.
- Noguez C. Surface plasmons on metal nanoparticles: the influence of shape and physical environment. *Phys. Chem.* 2007; 111: 3806-3819.
- Amin M, Anwar F, Janjua M.R.S.A, Iqbal M.A, Rashid U. Green Synthesis of Silver Nanoparticles through Reduction with *Solanum xanthocarpum* L. Berry Extract: Characterization, Antimicrobial and Urease Inhibitory Activities against *Helicobacter pylori*. *Int. J. Mol. Sci.* 2012; 13: 9923-9941.
- Shankar S.S, Ahmad A, Pasricha R, Sastry M. Bioreduction of chloroaurate ions by geranium leaves and its endophytic fungus yields gold nanoparticles of different shapes *Mater Chem.* 2003; 13: 1822-1826.
- Pondey S, Oza G, Mewada A, Sharon M. Green Synthesis of Highly Stable Gold Nanoparticles using *Momordica charantia* as Nano fabricator. *Arch. Appl. Sci. Res.* 2012;4(2): 1135-1141.
- Raghunandan D, Basavaraja S, Mahesh B, Balaji S, Manjunath S. Y, Venkataraman A. Biosynthesis of stable polyshaped gold nanoparticles from microwave-exposed aqueous extracellular anti-malignant guava (*Psidium guajava*) leaf extract *Nanobiotechnol.* 2009; 5: 34-41.