

# The Effects of Lyophilization on the Physico-Chemical Stability of Sirolimus Liposomes

Saeed Ghanbarzadeh<sup>1,2</sup>, Hadi Valizadeh<sup>3</sup>, Parvin Zakeri-Milani<sup>4\*</sup>

<sup>1</sup> Drug Applied Research Center and Faculty of Pharmacy, Tabriz University of Medical Sciences, Tabriz, Iran.

<sup>2</sup> Student Research Committee, Tabriz University of Medical Sciences, Tabriz, Iran.

<sup>3</sup> Research Center for Pharmaceutical Nanotechnology and Faculty of Pharmacy, Tabriz University of Medical Sciences, Tabriz, Iran.

<sup>4</sup> Liver and Gastrointestinal Diseases Research Center and Faculty of Pharmacy, Tabriz University of Medical Sciences, Tabriz, Iran.

## ARTICLE INFO

### Article Type:

Research Article

### Article History:

Received: 6 October 2012

Accepted: 7 October 2012

ePublished: 7 February 2013

### Keywords:

Liposome

Sirolimus

Lyophilization

Stability

## ABSTRACT

**Purpose:** The major limitation in the widespread use of liposome drug delivery system is its instability. Lyophilization is a promising approach to ensure the long-term stability of liposomes. The aim of this study was to prepare sirolimus-loaded liposomes, study their stability and investigate the effect of lyophilization either in the presence or in the absence of lyoprotectant on liposome properties. **Methods:** Two types of multi-lamellar liposomes, conventional and fusogenic, containing sirolimus were prepared by modified thin film hydration method with different ratio of dipalmitoylphosphatidylcholine (DPPC), cholesterol and dioleoylphosphoethanolamine (DOPE), and were lyophilized with or without dextrose as lyoprotectant. Chemical stability investigation was performed at 4°C and 25°C until 6 months using a validated HPLC method. Physical stability was studied with determination of particle size (PS) and encapsulation efficiency (EE %) of formulations through 6 months. **Results:** Chemical stability test at 4°C and 25°C until 6 months showed that drug content of liposomes decreased 8.4% and 20.2% respectively. Initial mean EE % and PS were 72.8 % and 582 nm respectively. After 6 months mean EE % for suspended form, lyophilized without lyoprotectant and lyophilized with lyoprotectant were 54.8 %, 62.3% and 67.1 % at 4°C and 48.2%, 60.4 % and 66.8 % at 25°C respectively. Corresponding data for mean PS were 8229 nm, 2397 nm and 688nm at 4°C and 9362 nm, 1944 nm and 737 nm at 25°C respectively. **Conclusion:** It is concluded that lyophilization with and without dextrose could increase shelf life of liposome and dextrose has lyoprotectant effect that stabilized liposomes in the lyophilization process.

## Introduction

Sirolimus (Rapamycin, SRL, Rapamune, C<sub>51</sub>H<sub>79</sub>NO<sub>13</sub>, CAS No: 53123-88-9), a carbocyclic lactone-lactam macrolide antibiotic, is a natural fermentation product of the streptomyces hygroscopicus discovered in Rapa Nui (Easter Island). Although initially isolated as an antifungal agent with potent anticandida activity, subsequent studies revealed impressive antitumor and immunosuppressive activities. It binds to the immunophilin FKBP12 and interferes with the function of mTOR, thus blocking the progression from G1 to the S phase of the cell cycle and blockage of the response of T and B cells to cytokines and consequently cell proliferation. Although SRL and Tacrolimus are structural analogs, they have different mechanisms of action. Sirolimus is available in oral solution and tablet form. It is rapidly but poorly absorbed after oral administration with an estimated bioavailability of 15%.<sup>1-8</sup>

Liposomes are artificial vesicles, composed of lipidic amphiphiles, usually phospholipids, which organize themselves in water to form an aqueous core surrounded by a lipidic bilayer. This structure allows liposomes to transport both hydrophilic and lipophilic compounds and have led to their clinical use as drug carriers of several drug classes including antibiotics, antifungals and anticancer agents. Liposomes have a 50-year history of use with numerous applications. Their utility has included toxicity buffering of drugs, targeting to specific tissue sites, enhancement of drug efficacy or potency, dissolution of insoluble drugs and sustained release of drugs.<sup>9-16</sup>

However, its potential application as therapeutic agent is still challenged by its physical and chemical instabilities in aqueous dispersions (e.g., hydrolysis and oxidation of phospholipids, encapsulated solute leakage and liposome aggregation) for long-term storage.

\*Corresponding author: Parvin Zakeri-Milani, Department of Pharmaceutics, Faculty of Pharmacy, Tabriz University of Medical Sciences, Tabriz, Iran. 51664. Tel: +98 (411) 3392593, Fax: +98 (411) 3344798, E-mail: pzakeri@tbzmed.ac.ir

Liposome dispersions prepared from commercially available lipids do not meet the required standards for long-term stability of pharmaceutical preparations. If they are stored as aqueous dispersions the encapsulated drugs tend to leak out of the bilayer structure and the liposomes might aggregate or fuse on storage and it is generally necessary to use them within the first few months of preparation. Accordingly, many methods available for stabilization of liposome have been investigated, such as lyophilization, freezing, spray-drying and supercritical fluid technology. Among these, lyophilization is the main approach used to extend the shelf-life of liposomes, especially for liposome containing thermo-sensitive drugs. Some liposomal products in the market or in clinical trials are provided as a lyophilized powder.<sup>17-21</sup>

A variety of sugars, including sucrose, glucose, fructose, maltose, arabinose and trehalose have been shown to act as lyoprotectant during dehydration/rehydration of liposomes.<sup>22-26</sup>

In the present study, SRL-entrapped multilamellar liposomes were prepared using the thin film hydration method. Physical stability tests of liposomal formulations of SRL were performed at 4°C and 25°C. Moreover the prepared liposomes were lyophilized to study the effect of lyophilization with and without lyoprotectant and also to investigate the lyoprotectant effect to protect liposomes against fusion and leakage during storage at the same temperatures.

## Materials and Methods

### Materials

Sirolimus was obtained from Poli Company (Lazio, Italy). Dipalmitoylphosphatidylcholine (DPPC) and dioleoylphosphoethanolamine (DOPE) were purchased from Lipoid GMBH (Ludwigshafen, Germany). Cholesterol (Chol) was obtained from Merck Company (Darmstadt, Germany). All solvents were HPLC grade and all reagents were of analytical grade and were purchased from Merck Company (Darmstadt, Germany).

### Liposome preparation

SRL multilamellar liposomal formulations with different molar ratios were prepared using the thin film hydration technique. The lipid components (DPPC and Chol) either alone or mixed with DOPE, in the case of fusogenic liposome, with different molar ratios were dissolved in chloroform:methanol mixture (3:1, % v/v) in a round-bottomed flask. The organic solvents were slowly removed under reduced pressure, using a rotary evaporator (Buchi, Zurich, Switzerland), at 45°C, above gel-liquid crystal transition temperature (T<sub>c</sub>) of phospholipids, such that a very thin film of dry lipids was formed on the inner surface of the flask. The dry lipid film was slowly hydrated with 20 ml of phosphate buffered saline (PBS) (pH 7.4) containing SRL 500 µg/ml for 3 hrs in rotary leading to the formation of multi-

lamellar liposomes. The resulting suspension was sonicated for 10 min to reduce liposome size.

### Chemical stability of SRL

Samples of liposomal formulations in suspension and lyophilized form in 4°C and 25°C were investigated initially and monthly until 6 months using previously developed HPLC method.<sup>27</sup>

### Lyophilization of liposomes and subsequent reconstitution

The lyoprotectant (dextrose) was dissolved in phosphate buffered saline at concentration of 10%. Liposomal suspensions in buffer with or without lyoprotectant were freeze-dried (ZIRBUS sublimator 400, ZIRBUS Technology, Bad Grund, Germany) where the liquid was frozen at -195°C. Dehydration step lasted for 2 days at temperature of -40°C until dried powder formed. The resulting lyophilized powders were rehydrated to its original volume at room temperature with PBS, and following the addition of PBS the samples were equilibrated at room temperature for 30 min. Then the samples were subjected to the following tests.

### Physical stability of liposomal formulations

Storage stability of all suspensions and lyophilized formulations was tested at 4°C and 25°C for six months.

### Determination of drug content and encapsulation efficiency (EE %) of liposomes

Untrapped drug was separated using dialysis method at temperature below gel-liquid-crystalline transition temperature (T<sub>c</sub>) in sink condition after 24 hrs. Drug content in the liposome dispersion and untrapped drug were analyzed with RP-HPLC system (Beckman, USA). The as follow: Knauer C18 column (4.6×150mm, 5µm) (Berlin, Germany) was used at 54°C, mobile phase consisting of acetonitril and ammonium acetate buffer (pH5.8)(70:30, % v/v) with flow rate of 1.5 ml/min, detection wavelength was set at 278 nm and injection volume was 150µl. A linear response was observed over a concentration range of 125–2000 ng/ml (r<sup>2</sup> > 0.991). For all quality control (QC) standards in intraday and interday assay, accuracy and precision ranges were 0.96 to 6.30 and 0.86 to 13.74 respectively, demonstrating the acceptable precision and accuracy over the analytical range. EE % was calculated by the following equation:<sup>28-32</sup>

$$EE (\%) = [(C_{\text{total}} - C_{\text{free}}) / C_{\text{total}}] \times 100$$

Where C<sub>total</sub> is total drug concentration which was added and C<sub>free</sub> is the concentration of untrapped drug.

### Measurement of particle size distribution of liposome

Mean vesicle size and size distribution profile of liposome was determined using particle size analyzer

(Shimadzu, Japan) which uses laser diffraction method. All sample measurements were conducted in triplicate.

## Results and Discussion

### Chemical stability of SRL

After six months storage at 4°C and 25°C, drug content of liposomes following disruption of liposome in methanol and after enough dilution was analyzed with RP-HPLC method. Results revealed that SRL content of liposomes after 6 months was  $91.6 \pm 2.3\%$  at 4°C and  $79.8 \pm 3.6\%$  at 25°C for suspended form. Respective results for lyophilized form at the end of 6 months storage were  $92.3 \pm 1.6\%$  and  $81.6 \pm 2.7\%$  (Figure 1). Therefore it can be concluded that hydrolysis has small effect in SRL degradation.

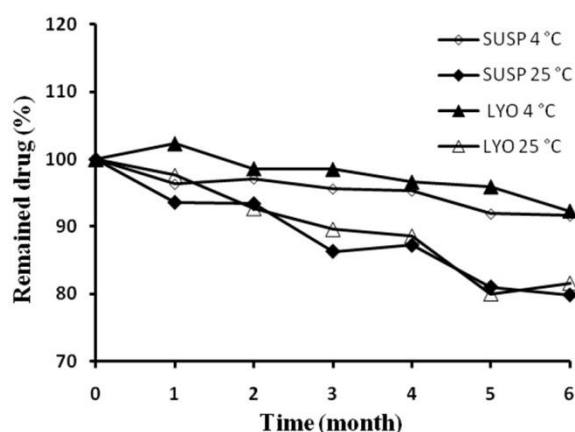


Figure 1. Chemical stability of SRL during 6 months in the suspension and lyophilized form

### Physical stability studies

Physical stability study of SRL liposomes was conducted at refrigeration temperature (4°C) and at room temperature (25°C) for a period of 6 months. Drug entrapment of liposomes in suspension and reconstituted liposome was evaluated monthly. The results are demonstrated in Figure 2 in terms of percentage of SRL retained in the liposomes.

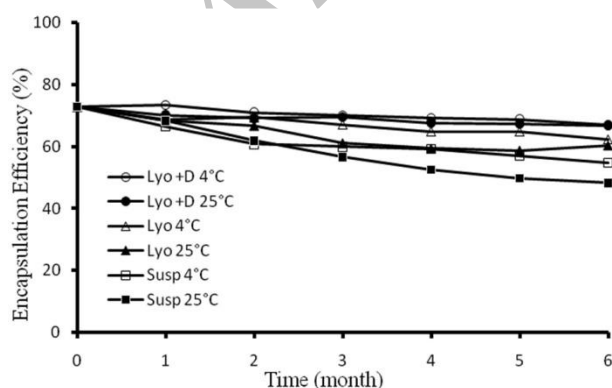


Figure 2. Mean EE % of different forms of multilamellar SRL liposomes stored at 4°C and 25°C


Mean initial EE % for liposomes was 72.8 % and average retained SRL percent in liposomal

formulations after 6 months were 54.8 %, 62.3 % and 67.1 % for suspended form, lyophilized without lyoprotectant and lyophilized with dextrose (Lyo + D) respectively. The retained drug in formulations after 6 months storage at 25°C was 48.2 %, 60.4 % and 66.8 % respectively (Figure 2).

Lyophilization increases the shelf-life of liposomal formulation and preserves it in dried form as a lyophilized cake to be reconstituted with water prior to administration. To maintain the same particle size distribution after lyophilization- rehydration cycle, a lyoprotectant needs to be added. Since the process of lyophilization is harmful for the liposome integrity, an obvious decrease in the encapsulation efficiency is seen for lyophilized formulations. In fact freeze-drying leads to destroy the membrane function of the phospholipid bilayer. In the present study we have used dextrose as protecting agent. It is well-known that sugars can be applied to prevent aggregation of nanoparticles during drying and storage. A literature review reveals that in previous studies various sugars were investigated for their ability to protect liposomes against fusion and leakage during lyophilization process. Glavas-Dodov et al, showed that particle size, EE % and release profile did not differ significantly after lyophilization with saccharose.<sup>33</sup> However, in this study dextrose showed protective effect for SRL liposomes. This protective ability can extend both prevention of vesicle fusion and retention of encapsulated drug within the liposome. The protective effect during liposome lyophilization is mainly determined by the formulation factors, such as the nature of the drug, the lipid bilayer composition, and the choice of lyoprotectants. The stabilization property of sugars has been explained by the particle isolation theory, water replacement hypothesis and vitrification theory.<sup>34-38</sup> Liposomes with lyoprotectant showed better stability, as indicated by higher drug retention. Suspended form liposomes had the less stability. Initial mean particle size of liposomes was 582 nm, which after 6 months storage at 4°C were increased up to 8229 nm, 2397 nm and 688 nm for suspended form, lyophilized without lyoprotectant and lyophilized with dextrose respectively. However in storage at 25°C particle sizes were increased more significantly up to 9362 nm, 1944 nm and 737 nm respectively (Figure 3). Considering 0.01 as significance level, only difference in particle size for formulation lyophilized with dextrose and stored at 4°C wasn't significant ( $P=0.026$ ) and in all other formulations differences were significant ( $P<0.005$ ).

As mentioned before more SRL retained in liposomes in lyophilized formulations compared to suspension form, but with using dextrose for lyophilization of multi-lamellar liposomes, EE % was higher. The leakage of entrapped SRL could be explained by the fact that in the suspension form, lyophilization and rehydration of a liposomal suspension can result in leakage of internal aqueous contents. Whereas, with using dextrose as a lyoprotectant and in the absence of

protective agent, the amount of entrapped SRL didn't decrease significantly ( $P > 0.15$ ).

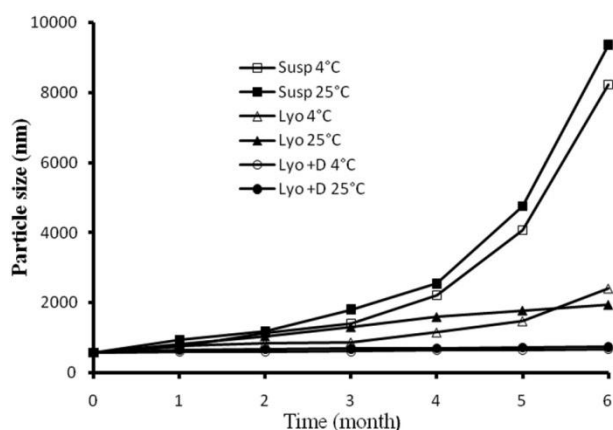

**Figure 3.** Mean particle size of different forms of multilamellar SRL liposomes stored at 4°C and 25°C.

### Conclusion

Instabilities of liposomes during storage are a serious limiting factor for their applicability as drug delivery systems. Lyophilization is a commonly used drying technique for thermolabile pharmaceuticals and also various studies have demonstrated that lyophilization is an effective way to overcome the instability problems of liposomes in the aqueous state. The present work focuses on physicochemical characterization of lyophilized SRL loaded multi-lamellar liposomes and short-term storage stability studies of formulation. The process of lyophilization is often used to prepare pharmaceutical formulations to achieve commercially practicable shelf life and easy handling (shipping and storage). It is important to have a product of a desirable quality and maintain physicochemical characteristics of formulation during storage. It was observed that there was no significant change in drug content at 4°C and 25°C storage conditions for 6 months in lyophilized liposomes with and without dextrose as lyoprotectant ( $P > 0.15$ ) but decreasing drug content in suspension forms was significant at both 4°C and 25°C ( $P = 0.009$  and  $P = 0.005$  respectively). Whereas significant increase ( $P < 0.005$ ) in size were observed at the same temperatures over 6 months of storage in all formulations except lyophilized form with lyoprotectant ( $P = 0.026$ ). Taken together, studies showed superior stability of the lyophilized product after reconstitution in comparison with those of the suspension product, and physico-chemical stability of products which have dextrose was most superior. Then we could conclude that lyophilization with and without dextrose could increase shelf life of liposome and glucose has lyoprotectant effect that stabilized liposomes in the lyophilization process. Overall, studies on the optimization of formulation and technological parameters to improve the lyoprotective effect are still required for improving liposome lyophilization.

### Acknowledgement

The authors would like to thank the authorities of Research Center for Pharmaceutical Nanotechnology, Tabriz University of Medical Sciences, for financial support. This article is based on a thesis submitted for PhD degree (No. 54) in Faculty of Pharmacy, Tabriz University of Medical Sciences, Tabriz, Iran.

### Conflict of interest

The authors report no conflicts of interest.

### References

- Bargnoux AS, Bonardet A, Chong G, Garrigue V, Deleuze S, Dupuy AM, et al. Evaluation of an immunoassay (abbott-imx analyzer) allowing routine determination of sirolimus: Comparison with lc-ms method. *Transplant Proc* 2006;38(7):2352-3.
- Campanero M, Cardenas E, Sadaba B, Garca Quetglas E, Muaoz-Juarez M, Gil-Aldea I, et al. Therapeutic drug monitoring for sirolimus in whole blood of organ transplants by high-performance liquid chromatography with ultraviolet detection. *J Chromatogr* 2004;1031(1-2):265-73.
- Holt DW, Lee T, Johnston A. Measurement of sirolimus in whole blood using high-performance liquid chromatography with ultraviolet detection. *Clin Ther* 2000; 22 Suppl B:B38-48.
- Holt DW, Lee T, Johnston A. Measurement of sirolimus in whole blood using high-performance liquid chromatography with ultraviolet detection. *Clin Ther* 2000;22 Suppl B:B38-48.
- Ong ATL, van Domburg RT, Aoki J, Sonnenschein K, Lemos PA, Serruys PW. Sirolimus-eluting stents remain superior to bare-metal stents at two years: Medium-term results from the rapamycin-eluting stent evaluated at rotterdam cardiology hospital (research registry). *J Am Coll Cardiol* 2006;47(7):1356-60.
- Park D, Kim Y, Yun S, Kang S, Lee S, Lee C, et al. Comparison of zotarolimus-eluting stents with sirolimus- and paclitaxel-eluting stents for coronary revascularization: The zest (comparison of the efficacy and safety of zotarolimus-eluting stent with sirolimus-eluting and paclitaxel-eluting stent for coronary lesions) randomized trial. *J Am Coll Cardiol* 2010;56(15):1187-95.
- Song Y, Hahn J, Choi S, Choi J, Lee S, Jeong M, et al. Sirolimus- versus paclitaxel-eluting stents for the treatment of coronary bifurcations: Results from the cobis (coronary bifurcation stenting) registry. *J Am Coll Cardiol* 2011;55(16):1743-50.
- Sakurai R, Inajima T, Kaneda H, Nagai R, Hashimoto H. Sirolimus-eluting stents reduce long-term mortality compared with bare metal stents in st-segment elevation myocardial infarction: A meta-analysis of randomized controlled trials. *Int J Cardiol* 2012;In Press, doi: 10.1016/j.ijcard.2011.12.054.
- Moeller S, Kegler R, Sternberg K, Mundkowsky RG. Influence of sirolimus-loaded nanoparticles on physiological functions of native human polymorphonuclear neutrophils. *Nanomed Nanotechnol Biol Med* 2012;8(8):1293-300.



9. Agashe H, Lagisetty P, Awasthi S, Awasthi V. Improved formulation of liposome-encapsulated hemoglobin with an anionic non-phospholipid. *Colloids Surf B Biointerfaces* 2011;75(2):573-83.
10. Chang C, Liu D, Lin S, Liang H, Hou W, Huang W, et al. Liposome encapsulation reduces cantharidin toxicity. *Food Chem Toxicol* 2008;46(9):3116-21.
11. da Silva Malheiros P, Daroit DJ, da Silveira N, Brandelli A. Effect of nanovesicle-encapsulated nisin on growth of *listeria monocytogenes* in milk. *Food Microbiol* 2011;27(1):175-8.
12. Fallon MS, Chauhan A. Sequestration of amitriptyline by liposomes. *J Colloid Interface Sci* 2006;300(1):7-19.
13. Fillion P, Desjardins A, Sayasith K. Encapsulation of DNA in negatively charged liposomes and inhibition of bacterial gene expression with fluid liposome-encapsulated antisense oligonucleotides. *Biochim Biophys Acta* 2001;1515(1):44-54.
14. Franz-Montan M, Silva ALR, Fraceto LF, Volpato MC, Paula Ed, Ranali J, et al. Liposomal encapsulation improves the duration of soft tissue anesthesia but does not induce pulpal anesthesia. *J Clin Anesth* 2011;22(5):313-7.
15. Fresta M, Villari A, Puglisi G, Cavallaro G. 5-fluorouracil: Various kinds of loaded liposomes: Encapsulation efficiency, storage stability and fusogenic properties. *Int J Pharm* 1993;99(2-3):145-56.
16. Gabizon A, Shmeeda H, Horowitz AT, Zalipsky S. Tumor cell targeting of liposome-entrapped drugs with phospholipid-anchored folic acid-peg conjugates. *Adv Drug Del Rev* 2004;56(8):1177-92.
17. Arnold K, Okhi S, Krumbiegel M. Interaction of dextran sulfate with phospholipid surfaces and liposome aggregation and fusion. *Chem Phys Lipids* 1990;55(3):301-7.
18. Comiskey SJ, Heath TD. Leakage and delivery of liposome-encapsulated methotrexate-aspartate in a chemically defined medium. *Biochim Biophys Acta* 1990;1024(2):307-17.
19. SanAnna V, Malheiros P, Brandelli A. Liposome encapsulation protects bacteriocin-like substance p34 against inhibition by maillard reaction products. *Food Res Int* 2011;44(1):326-30.
20. Chen C, Han D, Cai C, Tang X. An overview of liposome lyophilization and its future potential. *J Controlled Release* 2010;142(3):299-311.
21. Suakowski WW, Pentak D, Nowak K, Sua KA. The influence of temperature, cholesterol content and pH on liposome stability. *J Mol Struct* 2005;744:737-47.
22. Sundaramurthi P, Suryanarayanan R. Calorimetry and complementary techniques to characterize frozen and freeze-dried systems. *Adv Drug Del Rev* 2012;64(5):384-95.
23. Abdelwahed W, Degobert G, Stainmesse S, Fessi H. Freeze-drying of nanoparticles: Formulation, process and storage considerations. *Adv Drug Del Rev* 2006;58(15):1688-713.
24. Wang W. Lyophilization and development of solid protein pharmaceuticals. *Int J Pharm* 2000;203(1-2):1-60.
25. Konan YN, Gurny R, Allamann E. Preparation and characterization of sterile and freeze-dried sub-200 nm nanoparticles. *Int J Pharm* 2002;233(1-2):239-52.
26. Wolf M, Wirth M, Pittner F, Gabor F. Stabilisation and determination of the biological activity of L-asparaginase in poly(D,L-lactide-co-glycolide) nanospheres. *Int J Pharm* 2003;256(1-2):141-52.
27. Islambulchilar Z, Ghanbarzadeh S, Emami S, Valizadeh H, Zakeri-Milani P. Development and validation of an hplc method for the analysis of sirolimus in drug products. *Adv Pharm Bull* 2012;2(2):135-9.
28. Nii T, Ishii F. Encapsulation efficiency of water-soluble and insoluble drugs in liposomes prepared by the microencapsulation vesicle method. *Int J Pharm* 2005;298(1):198-205.
29. Piel G, Piette M, Barillaro V, Castagne D, Evrard B, Delattre L. Betamethasone-in-cyclodextrin-in-liposome: The effect of cyclodextrins on encapsulation efficiency and release kinetics. *Int J Pharm* 2006;312(1-2):75-82.
30. Sanchez-Lopez V, Fernandez-Romero JM, Gamez-Hens A. Evaluation of liposome populations using a sucrose density gradient centrifugation approach coupled to a continuous flow system. *Anal Chim Acta* 2009;645(1-2):79-85.
31. Yuba E, Kojima C, Harada A, Tana G, Watarai S, Kono K. Ph-sensitive fusogenic polymer-modified liposomes as a carrier of antigenic proteins for activation of cellular immunity. *Biomaterials* 2010;31(5):943-51.
32. Modi S, Xiang T, Anderson BD. Enhanced active liposomal loading of a poorly soluble ionizable drug using supersaturated drug solutions. *J Controlled Release* 2012;162(2):330-9.
33. Glavas-Dodov M, Fredro-Kumbaradzi E, Goracinova K, Simonoska M, Calis S, Trajkovic-Jolevska S, et al. The effects of lyophilization on the stability of liposomes containing 5-fu. *Int J Pharm* 2005;291(1-2):79-86.
34. Kuo JHS, Hwang R. Preparation of DNA dry powder for non-viral gene delivery by spray-freeze drying: Effect of protective agents (polyethyleneimine and sugars) on the stability of DNA. *J Pharm Pharmacol* 2004;56(1):27-33.
35. Hinrichs WLJ, Sanders NN, De Smedt SC, Demeester J, Frijlink HW. Inulin is a promising cryo- and lyoprotectant for pegylated lipoplexes. *J Controlled Release* 2005;103(2):465-79.
36. Sun WQ, Leopold AC, Crowe LM, Crowe JH. Stability of dry liposomes in sugar glasses. *Biophys J* 1996;70(4):1769-76.
37. Van Winden ECA, Crommelin DJA. Long term stability of freeze-dried, lyoprotected doxorubicin liposomes. *Eur J Pharm Biopharm* 1997;43(3):295-307.
38. Komatsu H, Saito H, Okada S, Tanaka M, Egashira M, Handa T. Effects of the acyl chain composition of phosphatidylcholines on the stability of freeze-dried small liposomes in the presence of maltose. *Chem Phys Lipids* 2001;113(1-2):29-39.