



Original Article

Crystal Violet Dye Removal by Low-Cost Nano-Superabsorbent Hydrogel: Thermodynamic and Isotherm Model

Hadeel K. Albdairi^{1,*}, Aseel M. Aljeboree²

¹Ministry of Interior Affairs, Babylon Police command, Criminal Evidence Investigation Department, Iraq

²Department of Chemistry, College of Sciences for Girls, University of Babylon, Hilla, Iraq

ARTICLE INFO

Article history

Receive: 2022-05-03

Received in revised: 2022-06-10

Accepted: 2022-07-25

Manuscript ID: JMCS-2207-1569

Checked for Plagiarism: Yes

Language Editor:

Dr. Fatimah Ramezani

Editor who approved publication:

Dr. Ali H. Jawad Al-Taie

DOI:10.26655/JMCHMSCI.2023.2.2

KEYWORDS

Adsorption isotherms

Guluronic acid

Hydrogels

Liquid wastes



Pollutants

ABSTRACT

Dye contamination is a major source of environmental pollution and health dangers practically in each section of the developing world, as people add color to textiles, paper, leather, and other materials to adorn and preserve them. Nowadays, green methods are considered the most important ways to solve environmental problems, especially the problems of the aquatic environment, and they fulfill the requirements of social, environmental, and economic guarantees. A new, environmental-friendly, and stable absorbent material has been prepared with absorbent properties based on biopolymers that have been successfully applied during the polymerization process with free radicals as a superabsorbent Ag-g-PAA/AC hydrogel. Many techniques were used to study the surface properties of the prepared hydrogel, including (FTIR, XRD, and FE-SEM). Several factors that affected the adsorption process were studied, including the effect of dye concentration, effect of hydrogel weight, effect of pH, and surface reactivation. Also, the adsorption isotherms of the Freundlich and Langmuir models were studied. Based on the findings, it was discovered that, depending on the R_2 value, adsorption isotherms followed the Freundlich model.

GRAPHICAL ABSTRACT

Crystal Violet Dye removal by low-cost nano-superabsorbent hydrogel

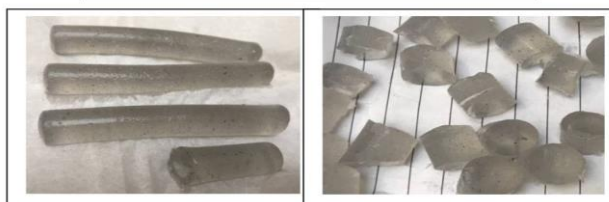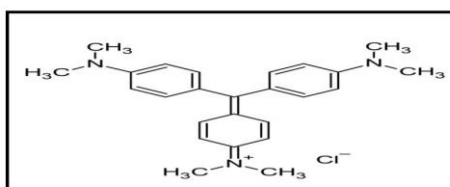

* Corresponding author: Hadeel K. Albdairi

✉ E-mail: Email: annenayad@gmail.com

© 2023 by SPC (Sami Publishing Company)

Introduction

After industrial development and the increase in the population, the treatment of pollutants, liquid wastes resulting from factories of various industries and factories of pharmaceuticals and dyes has become an essential topic for solving the problem of pollution of the aquatic environment [1–3]. Therefore, there was an urgent need to produce an inexpensive absorbent material used in water treatment.

Activated carbon is one of the absorbent materials with a high efficiency in removing pollutants, especially dyes [4,5]. It is an available, inexpensive, and environmentally friendly material. Agricultural waste is one of the sources to obtain activated carbon, such as pomegranate peels, melon peels, coconut peels, date kernels, peels of oranges and lemons, cotton stalks, stems of cornflowers and plant stems, sunflower, and others [6,7].

Alginates, which are polysaccharide polymers of d-manuronic acid and guluronic acid extracted from brown seaweed, can broaden the field of applications. Alginate hydrogels are widely used in bio-medical applications like drug delivery, cell encapsulation, and tissue engineering [8–10].

However, these hydrogels are considered as a set of limited mechanical properties, and this causes an insufficient form of cellular interactions. It has been reported that hydrogels are so soluble that they cannot be controlled after calcium ion loss [11–14]. The aim of the present work concerns the feasibility of using activated carbon, through loading with hydrogel, for the removal of crystal violet dye, studying the factors affecting the adsorption process such as the effect of dye concentration, the effect of Ag-g-PAA/AC hydrogel weight, the effect of pH, and the effect of adsorption isotherms.

Materials and Method

Chemicals

Alginate of sodium (Ag), $C_6H_9NaO_7$, has a low viscosity (MW= 216.12g/mol), acrylic acid (AAC) $C_3H_4O_2$ (MW= is 72.06 g.mol⁻¹). N, N'-methylene bisacrylamide $C_7H_{10}N_2O_2$ is a type of acrylamide (MBA) (MW = 154.17 g.mol⁻¹), sodium per sulfate (KPS) $K_2S_2O_8$ (MW = 270.31 g/mol), hydrochloric acid (HCl), hydroxide of sodium (NaOH), crystal violet (CV), $C_{25}H_{30}N_3Cl$ (MW=407.98 g.mol⁻¹), and has the maximum wavelength of 565 nm, as displayed in Figure 1. After purification, all chemicals were of the highest analytical purity.

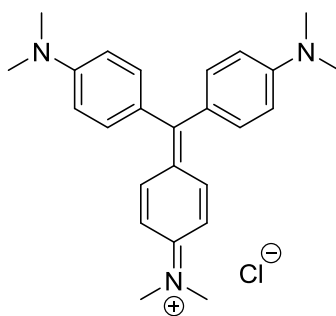


Figure 1: Chemical structures of Crystal Violet (CV) dye

Adsorption experiments

The removal capacity of hydrogel-based absorbent for crystal violet dye was investigated via usual batch adsorption experiments. Standard solutions of crystal violet dye were prepared by dissolving 0.5 g of crystal violet in 500 ml of distilled water. Solution of pH was adjusted by 0.1 N HCl or NaOH. 100 mL of solution of CV dye was taken and put in Erlenmeyer flasks 100 ml at pH 7.6, and then several parameters were studied such as the equilibrium time, temperature, weight of adsorbent, and the initial concentration of CV

dye. The adsorption experiments were conducted at 25°C and an agitation rate of 120 rpm on a shaking shaker water bath. After the contact time, the adsorbent was separated from aqueous solutions via centrifugation at 6000 rpm for 15 minutes. The CV residual concentration was estimated in each aliquot by using spectrophotometer UV-visible. The removal percentage% and adsorption capacity of CV dye were calculated by Equations 1 and 2:

$$\text{Removal Percentage } E\% = \frac{C_0 - C_e}{C_0} \times 100 \quad (1)$$

$$\text{Adsorption capacity } Q_e = \frac{(C_0 - C_e)V_{ml}}{W_{gm}} \quad (2)$$

Preparation of Ag-g-PAA / AC hydrogel

Sodium alginate (Ag) by dissolving 2 gm in 40 ml of DW with continuous stirring until all the substance was dissolved in the distilled water at 1 hour. 0.5 gm of activated carbon (AC) was added to 20 ml of DW with continuous stirring to sodium alginate (Ag) solution at 1 hour after. Next, the amount of acryl acid (about 4 ml) was added to the reaction mixture with constant stirring, and then about 0.03 gm of potassium sulphate (KPS) in (1ml) of DW was added to the reaction mixture

dropwise to the amount of N, N'-methylene bisacrylamide (MBA). About 0.05 gm in 1ml of DW was added with continuous stirring until the substance was dissolved. To complete the polymerization reaction, the temperature was increased to 75°C for three hours. After being submerged in DW to remove unreacted components, the Ag-g-PAA/AC hydrogel composite was dried at 60°C and used in experiment (Figure 2) [15].



Figure 2: Preparation of Ag-g-PAA / AC hydrogel

Results

Characterization of the adsorbent

The AC presence in the hydrogel structure leads to fill up the pores of Ag-g-PAA/AC hydrogel and minimize the heterogeneity of the surface. Due to the fact that CV dye immobilization on hydrogel partially blocked surface porosity, the hydrogel preserved a porous nature for CV adsorption, as depicted in Figure (3b).

The IR spectra wear utilized to characterize the Ag-g-PAA/AC hydrogel (Figure 3a) before and after the surface adsorption method on the CV dye, as shown in Figure 3c. Hence, due to the

adsorption intensity, a clear and significantly more than a few CV dye was observed among Ag-g-PAA/AC hydrogel composite. In addition, the hydrogels before the adsorption method with the CV dye illustrated a clear decrease in the IR spectra in the intensity of the bands adjacent to the adsorption [16–18]. The surface contains the acidic group that leads to a difference in the intensity of absorption.

The X-ray diffraction patterns of hydrogel with AC are presented in Figure (3d), which indicates that Ag-g-pAA/AC is amorphous and no crystalline materials from the peaks are presented in the broad band in the case of Ag-g-PAA/AC hydrogel.

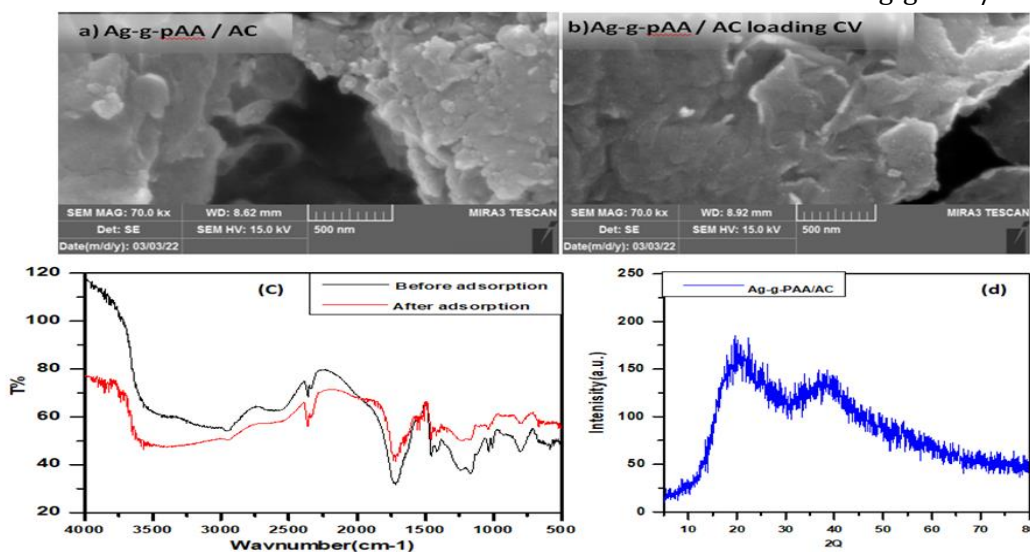


Figure 3: FESEM image: (a) Ag-g-PAA/AC, (b) Ag-g-PAA/ AC loading CV, (c) FT-IR spectra of Ag-g-PAA/AC hydrogel surface before, and after adsorption of CV dye, and (d) XRD Ag-g-PAA/AC

Effect of different parameter

Effect of absorbent dosage

The effect of weight of Ag-g-PAA/AC hydrogel composite on the removal of CV dye is demonstrated in Figure 4. The data reveals that increase in the weight amount causes a decrease in the residual concentration of the CV dye at contact time, and thus it leads to an increase in the absorption removal capacity [19–23]. Certainly, the absorption values of the removal efficiency raised from 80.12 to 93.09% as the weight of Ag-

g-PAA/AC hydrogel composite was increased from 0.01 to 0.08 g/100 ml. Such a trend is mainly attributed to an increase in the sorption, surface area, and the availability of more sorption sites. In contrast, the CV sorbed quantity per unit weight of Ag-g-PAA/AC hydrogel composite was decreased by the increase in absorbent dose. The values adsorption capacity was decreased from 801.12 to 116 mg/g as the weight of Ag-g-pAA/AC hydrogel composite was increased from 0.01 to 0.08 g/100 ml [24,25].

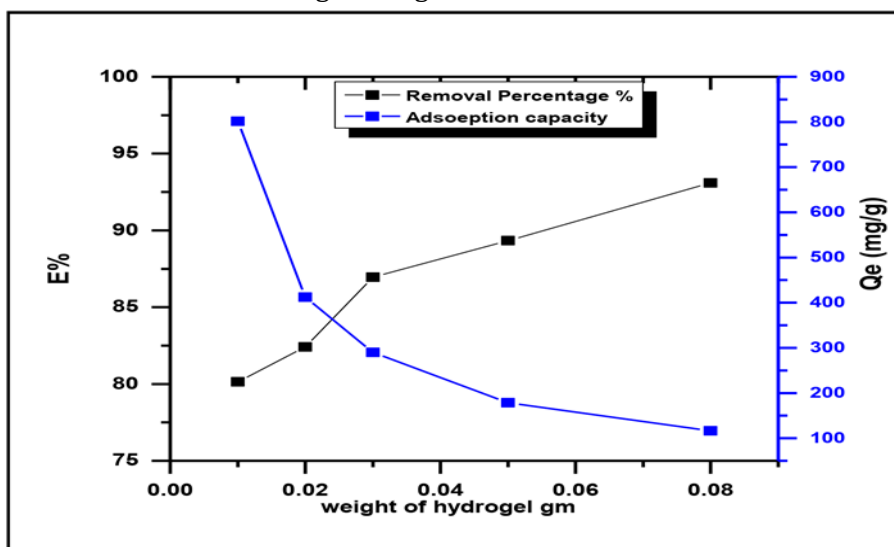


Figure 4: The effect of weight of Ag-g-PAA/AC hydrogel surface on CV dye: Experimental conditions: pH 6.2, initial conc. 100mg/L, and 25°C.

Effect of pH

The pH is an essential and important factor to determine the absorption efficiency of Ag-g-PAA/AC hydrogel composite at the optimum conditions of 25°C, the equilibrium time of 60 min, and the absorbent weight of 0.05 gm where it

depends mainly on the pH of the CV dye and the hydrogel, as depicted in Figure 5. It was found that the adsorption efficiency increases with increasing pH from (148.1 to 190.34 mg/g), where the best pH solution was 10 in the basic medium [26,27].

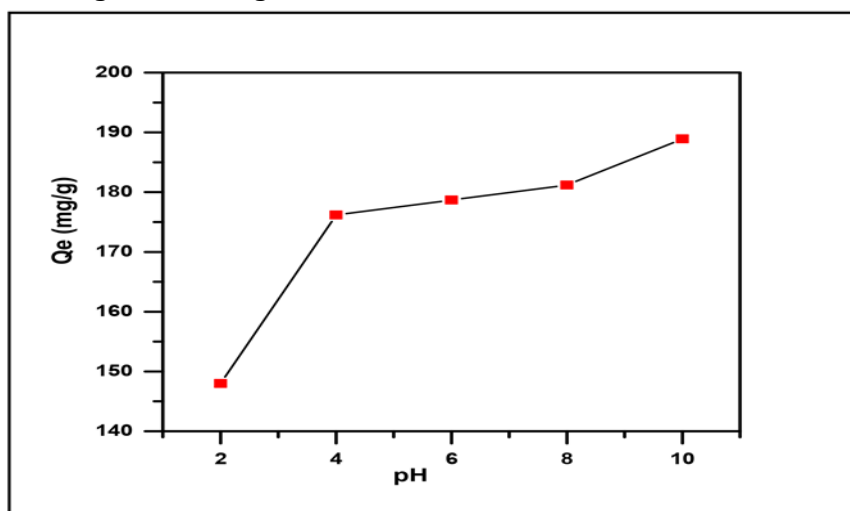


Figure 5: The effect of solution pH in CV adsorption uptake on (SA-g-PAAC)/AC hydrogel surface at 25°C

Regeneration of Crystal Violet (CV)

A study on the regeneration method carries out to see the re-activation of adsorbent and reuse potential of the adsorbate. If the CV desorption occurred via desorbing agents like (CH₃COOH, H₂SO₄, HCl, and NaOH at the concentration of 0.1

N), it was found the possibility of reactivating the surface and using it again, as indicated by the results in Table (1). The use of hydrochloric acid (0.1 N) was compared with the rest of the solutions, where the percentage of removal (90.012%) was through re-washing it only once [28,29].

Table 1: The desorption efficiency comparison of several types of solutions for the Crystal Violet (CV) on Ag-g-PAA/AC hydrogel

Re-generation and Desorption	E%
HCl	90.012
H ₂ SO ₄	80.874
acetone	60.66
NaOH	45.44

Adsorption Isotherm

The values of isotherm constants and their respective R₂ correlation coefficients are given in Figure 6 and Table 2. The R₂ calculated values suggested that the isotherm Langmuir and isotherm Freundlich models were fitted well with the result on adsorption equilibrium of Crystal Violet dye. The best (q_{max}) according to the isotherm Langmuir model was found to be 180 mg/g at 25°C.

In the isotherm Freundlich, the value of n (0.706) indicated the CV optimal adsorption on poly (Ag-g-AAc)/AC hydrogel by physical chemisorption on the heterogeneous surface of the hydrogel. It has been suggested that the n value between 1 and 10 represents an optimal sorption method. The KF calculated value in isotherm Freundlich was 33.574, suggesting the CV efficient adsorption by poly (SA-g-AAc)/AC hydrogel [30,31].

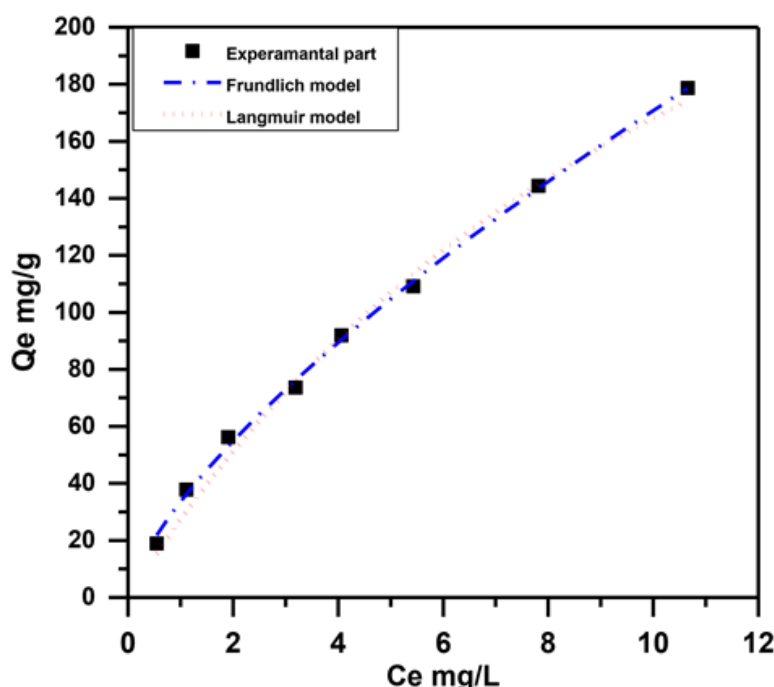


Figure 6: Nonlinear fitness of several adsorption models of CV adsorption dye on Ag-g-PAA/AC hydrogel, conc. = 100 mg. L⁻¹, Temp. = 25°C, and mass of polymer (0.05 g/L)

Table 2: Freundlich and Langmuir Isotherms model parameter of Congo red adsorbed on Ag-g-PAA/AC

Isotherm models	Parameters	Ag-g-PAA/AC
Freundlich	KF	33.574 ± 1.006
	1/n	0.706 ± 0.015
	R ₂	0.9987
Langmuir	qm (mg/g)	392.445 ± 8.153
	KL(L/mg)	0.0749 ± 0.0023
	R ₂	0.9912

Adsorption Thermodynamic Parameter

The spontaneity of the CV adsorption of Ag-g-PAA/AC hydrogel was evaluated by adsorption thermo-dynamics (Figure 7). Thermodynamics parameters counting change enthalpy (ΔH°), change entropy (ΔS°), and change free energy (ΔG°) were calculated by using the experimental result at several temperatures by Van't Hoff Equation (Eq. (3)).

$$\ln k = - \Delta G^\circ / RT = - \Delta H^\circ / RT + \Delta S^\circ / R \quad (3)$$

The negative value enthalpy of the CV adsorption on Ag-g-PAA/AC hydrogel indicated that the adsorption was endothermic and the positive

value entropy suggested that the randomness raised as the adsorption proceed. The (ΔS°) was attributed to the liberation of water molecules from the hydrated shell of the absorbed species. The change free energy of the CV adsorption was estimated by using Eq. (4) and listed in Table (3), as follow:

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (4)$$

The values ΔG° of the adsorptions under all testing conditions were negative, suggesting that the dye adsorption was a spontaneous process. Table (3) represents the CV adsorption thermodynamic factor on Ag-g-pAA/AC hydrogel.

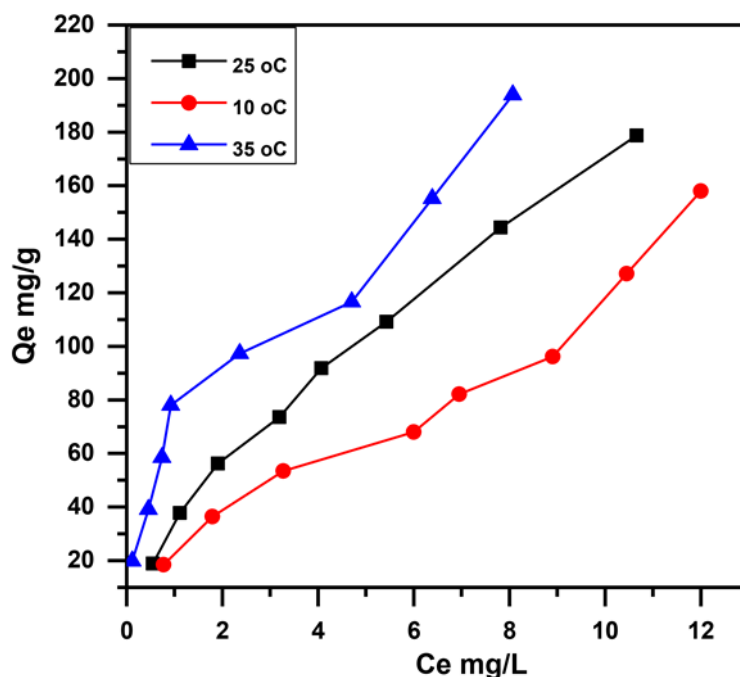


Figure 7: The CV Adsorption isotherms on Ag-g-PAA/AC hydrogel at different temperatures

Table 3: Thermodynamic factors for CV dye adsorption on Ag-g-PAA/AC hydrogel

Thermodynamic parameter			
ΔH (kJ/mol.)	ΔG (kJ/mol.)	ΔS (kJ/K.mol.)	Equilibrium Constant (K)
20.688	-6.512	88.453	12.5

Conclusion

In this study, the adsorption of crystal violet dye on Ag-g-PAA/AC hydrogel as a reactive surface was highly efficient in the color removal of the CV dye from an aqueous solution. The highest removal percentage of CV was (90.56%) at an equilibrium time of one hour, the dye concentration of (100 mg/L), and the weight of the hydrogel (0.05gm). Also, pH plays a key role in the color removal of the CV dye, as the greatest pH was in the alkaline medium. The process of reactivation of the surface Ag-g-PAA/AC hydrogel was applied and used again, as the hydrochloric acid gave the best removal efficiency when washing only once. The adsorption isotherms were studied, which matched the Freundlich model depending on the value of (R_2).

Funding

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

Authors' contributions

All authors contributed to data analysis, drafting, and revising of the paper and agreed to be responsible for all the aspects of this work.

Conflict of Interest

There are no conflicts of interest in this study.

ORCID

Hadeel K. Albdairi

<https://www.orcid.org/0000-0002-5419-3149>

References

- [1]. Hiew B.Y.Z., Lee L.Y., Lee X.J., Thangalazhy-Gopakumar S., Gan S., Lim S.S., Pan G.-T., Yang T.C.-K., Chiu W.S., Khiew P.S., Review on synthesis of 3D graphene-based configurations and their adsorption performance for hazardous water pollutants, *Process Safety and Environmental Protection*, 2018, **116**:262 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [2]. Bilal M., Iqbal H.M.N., Barceló D., Perspectives on the feasibility of using enzymes for pharmaceutical removal in wastewater, *Removal and Degradation of Pharmaceutically Active Compounds in Wastewater Treatment*, 2020, **108**:119 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [3]. Lu F., Astruc D., Nanocatalysts and other nanomaterials for water remediation from organic pollutants, *Coordination Chemistry Reviews*, 2020, **408**:213180 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [4]. Itodo A.U., Ande S., Audu M.O., Detoxification of acetaminophen overdose using formulated carbo tablets, *Journal of Medicinal and Chemical Sciences*, 2020, **3**:183 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [5]. Alkherraz A., Ali A., Elsherif K., Equilibrium and thermodynamic studies of Pb (II), Zn (II), Cu (II) and Cd (II) adsorption onto mesembryanthemum activated carbon, *Journal of Medicinal and Chemical Sciences*, 2020, **3**:1 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [6]. Rahimian R., Zarinabadi S., A review of studies on the removal of methylene blue dye from industrial wastewater using activated carbon adsorbents made from almond bark, *Progress in Chemical and Biochemical Research*, 2020, **3**:251 [[Google Scholar](#)]
- [7]. Tian C., Feng C., Wei M., Wu Y., Enhanced adsorption of anionic toxic contaminant Congo Red by activated carbon with electropositive amine modification, *Chemosphere*, 2018, **208**:476 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [8]. Tai C., Bouissil S., Gantumur E., Carranza M.S., Yoshii A., Sakai S., Pierre G., Michaud P., Delattre C., Use of anionic polysaccharides in the development of 3D bioprinting technology, *Applied Sciences*, 2019, **9**:2596 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [9]. Stachowiak N., Kowalonek J., Kozłowska J., Mechanical properties of polymer beads after immersion in solutions of different pH., *Engineering of Biomaterials*, 2021, **24**:163 [[Google Scholar](#)]
- [10]. Kuznetsova T.A., Andryukov B.G., Besednova N.N., Zaporozhets T.S., Kalinin A.V., Marine algae polysaccharides as basis for wound dressings, drug delivery, and tissue engineering: A review, *Journal of Marine Science and Engineering*, 2020, **8**:481 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [11]. Wu L., Zhang Z., Yang M., Yuan J., Li P., Men

- X., Graphene enhanced and in situ-formed alginate hydrogels for reducing friction and wear of polymers, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2020, **589**:124434 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [12]. [12]. Hamidi M., Jafari H., Siminska-Stanny J., Okoro O.V., Fatimi A., Shavandi A., Anionic exopolysaccharide from *Cryptococcus laurentii* 70766 as an alternative for alginate for biomedical hydrogels, *International journal of biological macromolecules*, 2022, **12**:370 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [13]. [13]. Smith A.M., Senior J.J., Alginate Hydrogels with Tuneable Properties, *Tunable Hydrogels*, 2021, **178**:37 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [14]. Lopez-Sanchez P., Assifaoui A., Cousin F., Moser J., Bonilla M.R., Ström A., Impact of Glucose on the Nanostructure and Mechanical Properties of Calcium-Alginate Hydrogels, *Gels*, 2022, **8**:71 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [15]. Youssef A.M., Abdel-Aziz M.E., El-Sayed E.S.A., Abdel-Aziz M.S., Abd El-Hakim A.A., Kamel S., Turkey G., Morphological, electrical & antibacterial properties of trilayered Cs/PAA/PPy bionanocomposites hydrogel based on Fe₃O₄-NPs, *Carbohydrate polymers*, 2018, **196**:483 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [16]. Qi X., Zeng Q., Tong X., Su T., Xie L., Yuan K., Xu J., Shen J., Polydopamine/montmorillonite-embedded pullulan hydrogels as efficient adsorbents for removing crystal violet, *Journal of Hazardous Materials*, 2021, **402**:123359 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [17]. Moharrami P., Motamedi E., Application of cellulose nanocrystals prepared from agricultural wastes for synthesis of starch-based hydrogel nanocomposites: Efficient and selective nanoadsorbent for removal of cationic dyes from water, *Bioresource Technology*, 2020, **313**:123661 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [18]. Sharma G., Kumar A., Naushad M., Dhiman P., Thakur B., García-Peñas A., Stadler F.J., Gum Acacia-Crosslinked-Poly (Acrylamide) Hydrogel Supported C₃N₄/BiOI Heterostructure for Remediation of Noxious Crystal Violet Dye, *Materials*, 2022, **15**:2549 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [19]. Pashaei-Fakhri S., Peighambaroust S.J., Foroutan R., Arsalani N., Ramavandi B., Crystal violet dye sorption over acrylamide/graphene oxide bonded sodium alginate nanocomposite hydrogel, *Chemosphere*, 2021, **270**:129419 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [20]. Li K., Yan J., Zhou Y., Li B., Li X., β -cyclodextrin and magnetic graphene oxide modified porous composite hydrogel as a superabsorbent for adsorption cationic dyes: Adsorption performance, adsorption mechanism and hydrogel column process investigates, *Journal of Molecular Liquids*, 2021, **335**:116291 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [21]. Malatji N., Makhado E., Modibane K.D., Pandey S., Hato M.J., Sequestration of Organic Dyes from Wastewater Using Hydrogel Nanocomposites, In *Functional Polymer Nanocomposites for Wastewater Treatment*, Springer, Cham, 2022, **323**:201 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [22]. Elbedwehy A.M., Atta A.M., Novel superadsorbent highly porous hydrogel based on arabic gum and acrylamide grafts for fast and efficient methylene blue removal, *Polymers*, 2020, **12**:338 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [23]. Kongseng P., Amornpitoksuk P., Chantarak S., Development of multifunctional hydrogel composite based on poly (vinyl alcohol-g-acrylamide) for removal and photocatalytic degradation of organic dyes, *Reactive and Functional Polymers*, 2022, **172**:105207 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [24]. Baghbadorani N.B., Behzad T., Etesami N., Heidarian P., Removal of Cu²⁺ ions by cellulose nanofibers-assisted starch-g-poly (acrylic acid) superadsorbent hydrogels, *Composites Part B: Engineering*, 2019, **176**:107084 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [25]. Pandey S., Son N., Kang M., Synergistic sorption performance of karaya gum crosslink poly (acrylamide-co-acrylonitrile)@ metal nanoparticle for organic pollutants, *International Journal of Biological Macromolecules*, 2022, **210**:300 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [26]. Sharma B., Thakur S., Mamba G., Prateek, Gupta R.K., Gupta V.K., Thakur V.K., Titania modified gum tragacanth based hydrogel

- nanocomposite for water remediation, *Journal of Environmental Chemical Engineering*, 2021, **9**:104608 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [27]. Pavithra S., Thandapani G., Sugashini S., Sudha P.N., Alkhamis H.H., Alrefaei A.F., Almutairi M.H., Batch adsorption studies on surface tailored chitosan/orange peel hydrogel composite for the removal of Cr (VI) and Cu (II) ions from synthetic wastewater, *Chemosphere*, 2021, **271**:129415 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [28]. Xu Q., Liu R., Yang H., Effect of acid and alkali solutions on micro-components of coal, *Journal of Molecular Liquids*, 2021, **329**:115518 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [29]. Baig N., Chauhan D.S., Saleh T.A., Quraishi M.A., Diethylenetriamine functionalized graphene oxide as a novel corrosion inhibitor for mild steel in hydrochloric acid solutions, *New Journal of Chemistry*, 2019, **43**:2328 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [30]. Sharma S., Sharma G., Kumar A., AlGarni T.S., Naushad Mu., AlOthman Z.A., Stadler F.J., Adsorption of cationic dyes onto carrageenan and itaconic acid-based superabsorbent hydrogel: Synthesis, characterization and isotherm analysis, *Journal of Hazardous Materials*, 2022, **421**:126729 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [31]. Nakhjiri M.T., Marandi G.B., Kurdtabar M., Poly (AA-co-VPA) hydrogel cross-linked with N-maleyl chitosan as dye adsorbent: Isotherms, kinetics and thermodynamic investigation, *International journal of biological macromolecules*, 2018, **117**:152 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

HOW TO CITE THIS ARTICLE

Hadeel K. Albdairi, Aseel M. Aljeboree. Crystal Violet Dye Removal by Low-Cost Nano-Superabsorbent Hydrogel: Thermodynamic and Isotherm Model. *J. Med. Chem. Sci.*, 2023, 6(2) 186-194

<https://doi.org/10.26655/JMCHMSCI.2023.2.2>

URL: http://www.jmchemsci.com/article_154868.html