

## The evaluation of removal efficiency of phenol from aqueous solutions using *Moringa Peregrina* tree shell ash

Amin Zarei.<sup>1</sup> \*Edris Bazrafshan.<sup>2</sup> Hamed Faridi<sup>1</sup> Razieh Khaksefidi.<sup>1</sup> Mostafa Alizadeh.<sup>1</sup>

- 1- Student Scientific Research Center of Zahedan University of Medical Sciences, Zahedan, Iran
- 2- Health Promotion Research Center, Zahedan University of Medical Sciences, Zahedan, Iran

\*ed\_bazrafshan@yahoo.com

### Abstract

**Background and purpose:** Phenol is one of prevalent contaminants found in many industrial wastewaters. The combination with special features, such as high toxicity, carcinogenic properties, vitality gathering ability, low biodegradation potentiality and others, based on the U.S Environmental Protection Agency, classified as a priority pollutant. The purpose of this study was to determine the efficiency of *Moringa Peregrina* tree shell ash for the removal of phenol from aqueous solutions.

**Materials and Methods:** This study is experimental and pilot scale. To determine the efficiency of *Moringa Peregrina* tree shell ash for the removal of phenol from aqueous solutions; the examination was carried out in a batch system. To achieve the aim of this study, the effect of each of the parameters affecting the adsorption process, such as initial pH of solution, contact time, adsorbent dose and initial concentration of phenol in solution were studied.

**Results:** The results showed that the highest percentage of phenol removal by the ash occurred at pH 6, initial concentration 100 mg.L<sup>-1</sup> and adsorbent dose 0.4 g/l in which the 79.96% phenol was removed. For the analysis of the absorption constant, the Freundlich and Langmuir isotherm were used. The results showed that the experimental data fit the Langmuir ( $R^2=0.9833$ ) much better than the Freundlich model ( $R^2=0.9373$ ).

**Conclusion:** According to the results of this study, it was found that the *Moringa Peregrina* tree shell ash is not only a low-cost adsorbent but also has a high performance in the removal of phenol from aqueous solutions.

[Zarei A. \*Bazrafshan E. Faridi H. Khaksefidi R. Alizadeh M. *The evaluation of removal efficiency of phenol from aqueous solutions using Moringa Peregrina tree shell ash.* IJHS 2013; 1(1): 65-74] <http://jhs.mazums.ac.ir>

**Key words:** Phenol Removal, Adsorption, Aqueous Solutions

## Archive of SID

### 1. Introduction

One of the major forthcoming challenges of human being is providing healthy water for the large population all over the world. This need is an important issue especially in the developing countries. Water resources are always prone to different contaminations due to anthropogenic and natural actions, which we should rapidly return them into the usage cycle regards to the shortage of water resources (1,2).

Phenol has an especial importance among the contaminating materials of water (3). Phenol is one of the most frequent contaminators in waste water of producing resin, plastic, yarn, petrochemical, coal, ceramic, glue, iron, steel, aluminum, leather, food process and etc. Furthermore, phenol is used as a solvent, disinfectant and an additive to increase the effectiveness of disinfectant (2-9).

Phenol is an inflammable composition with a high solubility in water and many other organic solvent (10). The presence of phenol in water causes malodor and bad taste. Also entrance of phenol in drinking water resources disinfected by chlorinated compositions cause's chlorophenol combinations. These materials cause medicinal taste and smell in water and make it inappropriate to use and revealed to protest of users. Also, phenol is potential human carcinogen and is of considerable health concern, even at low concentration. Owing to their toxic effects, including permeabilisation of cellular and cytoplasmic coagulation, phenolic contaminants can damage sensitive cells and thus cause profound health and environmental problems (7, 11-13). According to the classification of United State Environmental Protection Agency (USEPA), phenol compositions are among the prior combinations. This agency considered a concentration of less than 1 mg/L in the output of the filtered waste water to the superficial water, due to the potential effects of contacts to phenol (14). Institute of Standard and Industrial Research of Iran (ISIRI) considered the maximum allowed concentration of phenol introducing to the superficial water as 1 mg/L. Also according to the guides of World Health Organization (WHO), the

maximum allowance of phenol in drinking water is 0.002 mg/L (15).

So, diagnosis, determination and measurement of the phenol combinations in waste water containing these materials and eliminating them from industrial waste water before introducing into the water resources seem necessary. Up to know different methods are applied to eliminate phenol combinations from the water environmental like biologic filtration by ultrasound waves, photocatalytic destruction, membranous filtration, enzymatic filtration, and extraction by solvent, chemical oxidation, light oxidation, photochemical destruction and wet oxidation (11-16,29).

Most of these techniques have especial failures like high operative and device costs, needs for additive chemical substrate, high energy consumption, needs to further space and producing mug and toxins (30,31).

Adsorption process is one of the most common methods widely used for elimination of organic and non-organic contaminations from the water resources. Adsorption process is one of the most simple, effective and cost benefit alternative methods to phenol removal from aqueous environments (32-35). Active carbon, silica and active aluminum are used as the absorbent (36) but problems like high costs and the possibilities of activation and reclamation of the absorbent which are important from economic point of view, provoke investigators to search for new absorbents (37). At the present time, biomass draws increasing interest all over the world because it is a renewal material which is available widely with low costs and no damage to the environment (38). Moringa Peregrina seed is one of the desert type restricted growth in the southeast of Sistan and Balouchestan in Iran, and North Africa and southwest of Asia. Moringa oleifera seed usually grows in the upper mountain slopes where the surface is covered by rocks rubble (39). So, in this study the effective removal of phenol from aqueous solutions with the activated carbon from Moringa Peregrina tree shell was evaluated.

## Archive of SID

### 2. Methods

#### 2.1. Preparing phenol solution

All chemicals used for this study are of Analytical grade (AR) and are obtained from Merck Company. Stock solutions of phenol were prepared by dissolving the required amount of phenol (99.9% purity) in deionized water without pH adjustment. Working solutions of the desired concentrations (10, 20, 30, 40, 50, 80 and 100 mg/L) were obtained by successive dilutions.

#### 2.2. Method of measuring Phenol concentration

The residual phenol concentration in the solutions was determined using UV-spectrophotometer (Model T80 UV/VIS) by analyzing the color resulting from the reaction of phenol with 4-aminoantipyrine at maximum wavelength  $\lambda = 500$  nm (41). Solutions with concentration higher than that detected by spectrophotometer were determined by dilution. The pH of solution was measured using a pH-meter (WTW, Germany).

#### 2.3. Adsorbent preparation

Dry Moringa Peregrina tree shells were collected around the vicinity of Nikshahr city, Sistan and Baluchestan province, Iran. This natural wastes were firstly washed with distilled water to remove impurity such as sand and leaves and soluble and colored components, dried at 110 °C for 2 h, crushed in a domestic grinder and sieved to obtain particle size in the range of 60–200 mesh. Then a mixture of 250 g of powdered adsorbent, 110 g of ZnCl<sub>2</sub> and 110 g of water was kept overnight, and then the mixture was calcinated at 350°C. Then, chemically prepared activated carbon was washed with water and dried. The activated carbon was then used in adsorption experiments. No other chemical or physical treatments were used prior to adsorption experiments.

#### 2.4. Batch adsorption experiments

For the phenol removal activated carbon obtained from Moringa Peregrina tree shell was used in a closed environment in Shaker 250 ml Erlenmeyer flask and magnetite shaker. Each test consisted of 100 ml of desired phenol concentration and pH of the dilution of phenol

stock solution prepared with distilled water. To adjust the pH, the concentration of phenol solution was then poured into the pH meter by using solutions of HCl and NaOH 0.1 N.

A known mass of Moringa Peregrina tree shell ash (adsorbent dosage) was then added to the solution, and the obtained suspension was immediately stirred for a predefined time. After the desired contact time, the samples were withdrawn from mixture by using a micropipette and the mixtures were then filtered through Whatman 42 filter paper and the concentration of phenol in the filtrates was analyzed. Then the amount of phenol adsorbed,  $q_e$  (m/g), was obtained as follows:

$$(1) \quad q_e = \frac{(C_0 - C_e)V}{M}$$

Which  $C_0$  and  $C_e$  are primary phenol concentration and secondary one after the tests and reaching to the balance.  $V$  is the volume of solution (L) and  $M$  is the used amount of adsorbent (g). The following equation shows the rate of phenol elimination as percent:

$$(2) \quad \% = \frac{(C_0 - C_f)}{C_0} \cdot 100$$

In the above equation  $C_0$  and  $C_f$  respectively show the initial and final concentrations (after adsorption) of phenol. All experiments were performed at room temperature  $23 \pm 2$  °C and for sure repeated twice. Final results are reported as the average of the two measurements.

#### 2.5. The effect of initial pH

The effect of initial pH on the removal of phenol from synthetic solutions was examined. The adsorbent used was 0.04 g in 100 mL of test solution and the initial phenol concentration in all samples was 50 mg/L. The initial pH of samples in each set of experiments was in the range of 2–12. Samples were put on magnetic shaker of 120 rpm for 60 min to make sure of balance. After the elapse time, they were filtrate by Whattman filter paper and the phenol concentration was measured

## Archive of SID

by spectrophotometer and results were analyzed. The above test was done in temperature between  $23 \pm 2$  °C and repeated twice then the Final results are reported as the average of the two measurements.

### 2.6. The effect of absorbent dosage

Adsorption experiments to determine the effect of adsorbent dose on the removal of phenol from gaz ashes oily skin adsorption dose was done in a range of 0.01 to 0.07 g per 100 mL of a solution containing 50 mg/L at the optimal pH of 6 and contact time of 60 minutes at  $23 \pm 2$  °C. Samples were taken after the shaking and the elapsed time as smooth and level were analyzed.

### 2.7. The effect of exposure time


To measure the effect of exposure time on adsorption process, tests were done in different times (15, 30, 60, 90, 120, 150, 180 and 210 min) for the primary phenol concentration of 50 mg/L in pH=6 and  $23 \pm 2$  °C. 0.03 mg of adsorbent dissolved in 100 mL of the present solution in Erlenmeyer 250 mL flask and mixes the samples after exposure to the Shaker and the elapsed time then it was filtered as mentioned earlier and analyzed. Adsorption experiments continued to determine the effect of initial phenol concentration at pH =6 and  $23 \pm 2$  °C. In this stage 0.03 grams of adsorbent were mixed in 100 mL of solution containing different phenol concentrations (10, 20, 30, 40, 50, 80 and 100 mg/L) and solutions exposed to the absorbent for 60 min with a rate of 120 rpm on the shaker. Then samples were filtered and analyzed as mentioned before.

## 3. Results

### 3.1. The effect of initial pH on adsorption effectiveness

PH of the solution is one of the most critical parameters that affect the chemical properties of absorbing and adsorbing (42). This parameter is directly appropriate with the competition ability of hydrogen ions with pollutants on the active surface of absorbent. So, phenol adsorption was studied as a function of hydrogen ion concentration to determine the optimal pH for phenol adsorption by ash.


Figure 1 shows the effect of initial pH value of the solution (in the range of pH=2-12) on the efficiency of adsorption of phenol by Ash with a concentration of 0.4 g/L initial phenol concentration of 50 mg/L respectively.

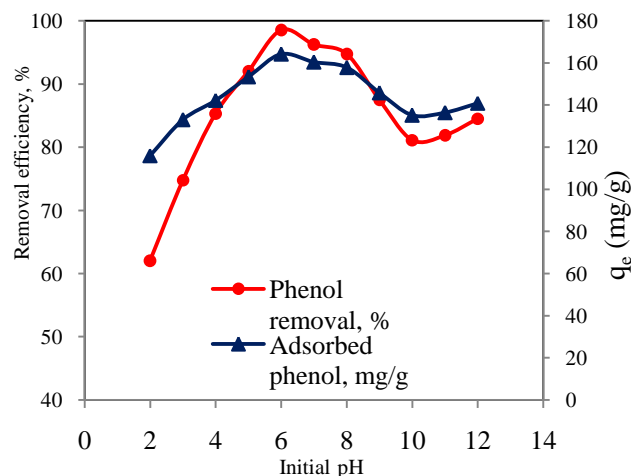

**Figure 1.** Effect of initial pH on the adsorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell (Phenol concentration = 50 mg/L; adsorbent dose = 0.4 g/L; contact time = 60 min)

### 3.2. Effect of adsorbent dose on the phenol removal

The absorptive capacity of the adsorbent dose is one of the most important parameter for determining the initial phenol concentration; therefore, to determine the effect of adsorbent dosage on the adsorption process, the adsorbent dose in the range of 0.7 to 1 g/L and the initial phenol concentration of 50 mg/L, in pH =6 and  $23 \pm 2$  °C temperature in 60 minute time period considered.

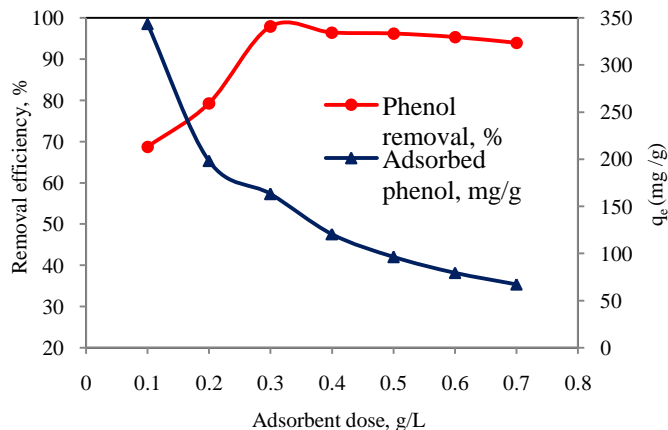


**Figure 2.** Effect of adsorbent dose on the adsorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell (Phenol concentration = 50 mg/L; pH= 6; contact time = 60 min)

## Archive of SID

### 3.3. The effect of exposure time on efficiency of adsorption process

Exposure time is one of the most important parameters for the adsorption process to reach equilibrium. Effect of contact time on the adsorption process at a temperature of  $23 \pm 2$  °C, initial phenol concentration, adsorbent dose of 50 mg/L and 0.3 g, were studied for a contact time 15-210 minutes.


Figure 3 shows the effect of exposure time on the adsorption capacity and the percentage of phenol elimination in primary phenol concentration of 50 mg/L. The adsorption capacity and percentage of phenol elimination is increased significantly at the first stages of adsorption and reached to a balance after 45 minutes. The elimination percentage reached to 98.04% and adsorption capacity to 163.4 mg/g, so it was chosen as the equilibrium time.

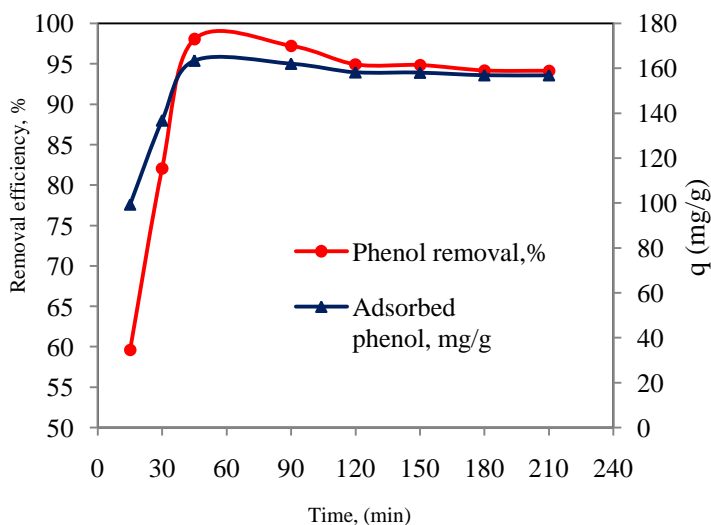

**Figure 3.** Effect of contact time for the adsorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell (Phenol concentration: 50 mg/L, pH: 6, adsorbent dosage: 0.3 g/L)

### 3.4. The effect of primary phenol concentration on the effectiveness of adsorption process

The effect of primary phenol concentration on the efficiency of adsorption in temperature  $23 \pm 2$  °C and adsorbent dose of 0.3 g/L for 45 min exposure time. As shown in figure 4, phenol adsorption rate will be increased by phenol concentration, so phenol elimination depends on its concentration.

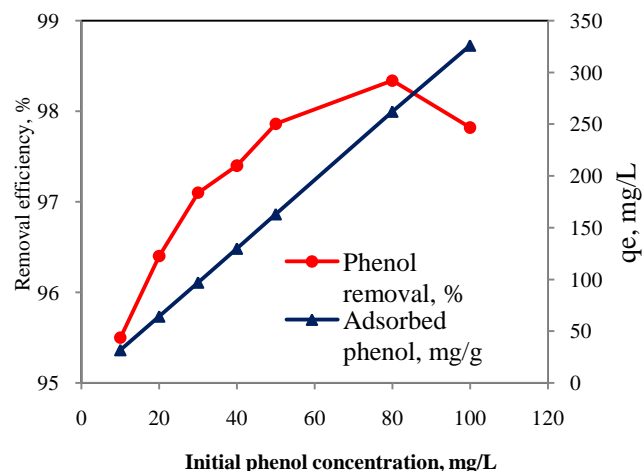

**Figure 4.** Effect of initial phenol concentration for the adsorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell (pH=6, adsorbent dosage: 0.3 g/L and contact time=45 min)

### 3.5. Adsorption isotherms

Studying of isotherms could explain the reactions between adsorbent and adsorptive. Isotherm shows the relation between soluble phenol concentration and the rate of adsorbed phenol by the solid phase, when the two phase are in balance. Figures 5 and 6 show the balanced isotherms for phenol adsorption by Moringa Peregrina and data of balanced adsorption analyzed with Freundlich and Langmuir isotherms. Langmuir isotherm model is valid for monolayer adsorption onto surface containing finite number of identical sorption sites which is presented by the following equation:

$$(3) \quad q_e = \frac{q_m K_L C_e}{1 + K_L C_e}$$

In the above equation,  $q_e$  stands for the adsorbed phenol in a certain amount of adsorbent (mg/g),  $C_e$  is for the balance concentration of solution (mg/L) and  $q_m$  is the maximum amount of phenol needed to form a layer (mg/g). Langmuir equation could change to linear model to facilitate drawing and achieving Langmuir constant ( $K_L$ ) and the maximum adsorption of a layer of Moringa Peregrina ( $q_m$ ).  $K_L$  and  $q_m$  could be achieved by linear drawing of  $\frac{1}{q_e}$  in contrast to  $\frac{1}{C_e}$ .



Archive of SID

(4)

$$\frac{1}{q_e} = \frac{1}{q_m} + \frac{1}{q_m K_L} + \frac{1}{C_e}$$

The Freundlich equation is purely empirical based on sorption on heterogeneous surface, which is commonly described by the following equation:

(5)

$$q_e = K_f C_e^{\frac{1}{n}}$$


$K_f$  and  $\frac{1}{n}$  are the constant of Froondlich and respectively are dependent to the adsorption capacity and the severity of adsorption. Evaluating the constant of Froondlich equation is obtained from crushing the slope of linear figure,  $\log q_e$  in contrast to  $\log C_e$  based on tests. Below equation could be written as a linear logarithm to mention Freundlich constant.

(6)


Isotherms are shown in figures 5 and 6 based on laboratory data and measured parameters due to non linear regression for both models. Also all parameters are shown in Table 1. The correlation coefficient of Langmuir ( $R^2=0.9672$ ) was higher than Freundlich model ( $R^2=0.9448$ ) which shows that the Langmuir model is more appropriate to conclude the balanced adsorption of phenol on the adsorbent.

**Table 1.** Isotherm parameters for phenol adsorption onto activated carbon obtained from

Langmuir isotherm			Freundlich isotherm		
$q_m$ ( $mg\ g^{-1}$ )	$K_L$ ( $L\ mg^{-1}$ )	$R^2$	$K_f$	$n$	$R^2$
122.17	0.48	0.9672	122.69	0.63	0.9448

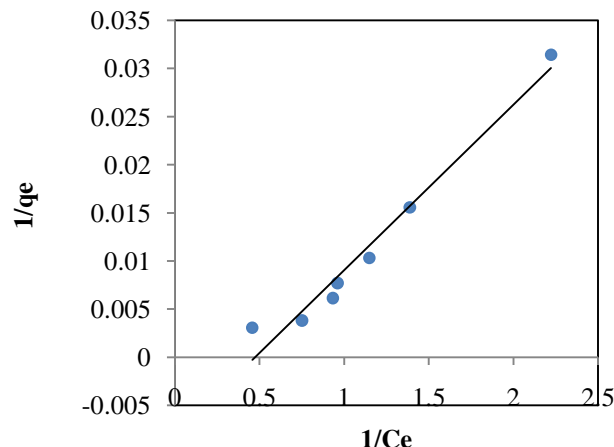

**Figure 5.** Langmuir isotherm for sorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell ( $R^2=0.9672$ )

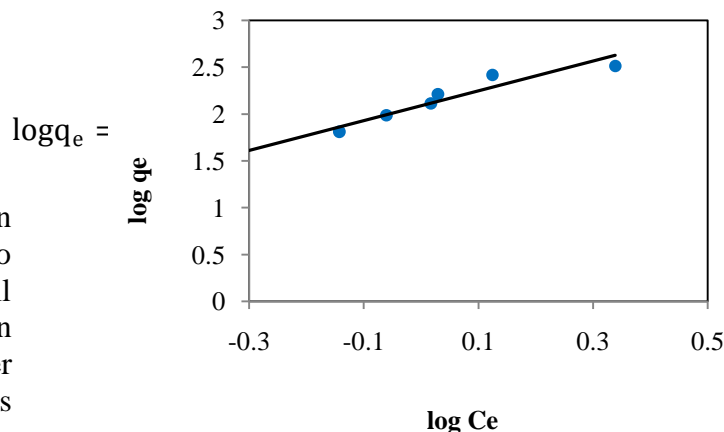

**Figure 6.** Freundlich isotherm for sorption of phenol onto activated carbon obtained from Moringa Peregrina tree shell ( $R^2=0.9448$ )

4. Discussion

PH of solution is one of the most effective parameter on the effectiveness of adsorption process which could lead to better or worse effectiveness of contamination elimination. As shown in figure 1, evidences show that after increasing pH to higher than 6, the effectiveness of phenol elimination will increase up to 98.54% and will be constant up to pH=7, then it will decrease. The most adsorption capacity of activated carbon obtained from Moringa Peregrina

## Archive of SID

tree shell was 164.23 mg/g in pH=6. pH of phenol containing solution is effective on their adsorption via active carbon and in higher pH the adsorption rate will decrease (pH>7) because phenol is in the salty form which lose its negative load and phenol adsorption would be difficult. In addition OH<sup>-</sup> ion presentation will inhibit the adsorption of phenol ions by adsorbent. In lower pH and the presence of H<sup>+</sup> ions will neutralize phenol ions and the adsorption on polar adsorption will decrease (43).

As it is shown in figure 2, phenol elimination depends on the adsorbent amount in solution and will increase with increasing adsorbent dose. It means that the phenol elimination percent will increase with a slight slope up to 0.3 g/L of adsorbent dose. It would seem that there will be areas on the adsorbent surface remained unsaturated during the adsorption process but the adsorption locations could be increased by increasing the adsorbent dosage. The optimal elimination rate of phenol is 97.86 % (163.1 mg/g) which is achieved by 0.3 g/L of adsorbent.

As shown in figure 2, when adsorbent dose reached more than 0.3 mg/L, a dramatic increase would not seen in the elimination rate of phenol by adsorbent. So it seems that after increasing the adsorbent dose to a certain dose, the highest rate of adsorption would be achieved and after that the remaining contamination amount will be constant even after increasing dose (44). Although the elimination rate of phenol will be increased with increasing dose of adsorbent, but the amount of absorbed phenol for each gram of adsorbent will be decreased, because phenol concentration in the solution (50 mg/L) will be decreased due to adsorption by activated unsaturated areas of adsorbent surface and increasing adsorption also causes aggregation of particles (45). So the amount of 0.3 g/L adsorbent was considered as the optimal dose of adsorbent for the next tests. Among other effective parameters on the adsorption process is the exposure time of adsorbent and adsorbate. According to the results of present study, totally the elimination rate of adsorptive substance was rapid at first but decreased until the equilibrium time. This could be explained that at the first stage of adsorption the numbers of free spaces available on the adsorbent surface are more, and then due to the

repulsion force between the adsorptive molecules and the remained free surface of soluble phase, it would be harder. On the other hand, at first the percentage of phenol elimination is high due to available surfaces of adsorbent to adsorb contaminations. As the surface adsorption sites become exhausted, the rate of uptake is controlled by the rate of transport from the exterior to the interior sites of the adsorbent particles (44). Similar findings are reported by Cengiz and Cavas (46) and SenthilKumar et al (47).

The initial concentration of pollutants is an important driving force to overcome the deterrent mass transfer between liquid and solid materials adsorb provides (48). Actually, the primary phenol concentration is an important activator to overcome the inhibitory force of phenol germ between liquid and solid phase, so increasing the primary concentrations could increase the phenol adsorption capacity. These results are in concordance with other investigations (46, 48).

For example, when the initial phenol concentration increases from 10 to 100 mg/L adsorption equilibrium concentration of adsorbent increases from 31.83 mg/g (95.5%) to 326.07 mg/g (97.82%). The increase in the rate of phenol removal is probably due to balance changes during the adsorption process. Similar findings for the adsorption of methylene blue on activated carbon, bamboo, cotton waste and escaped ash is achieved. In addition, a similar result has also been recorded for adsorption of Congo red from aqueous solution onto calcium-rich fly ash (49-52). In this study it was observed that this adsorbent can be used effectively for the removal of phenol from aqueous solutions. Removal rate depends on pH, amount of adsorbent, contact time and initial concentration of phenol exposed to the adsorbent. The adsorbent can remove more than 97% of phenol from aqueous solutions with an initial concentration of 10 to 100 mg/L. Phenol adsorption Freundlich and Langmuir isotherms on adsorbents can be interpreted. The results showed that the Langmuir adsorption equilibrium of phenol on the adsorbent is more suitable for interpretation. Removal of phenol from aqueous solutions at low concentrations of phenol by adsorption on active surfaces of the adsorbent and the high concentrations of phenol by adsorption on surfaces and internal transactions occur.

*Archive of SID***Acknowledgements**

The authors are grateful for the financial support of this project by the health research deputy of Zahedan University of Medical Sciences (Project number: 5499).

**References**

- Girelli AM, Mattei E, Messina A. Phenols removal by immobilized tyrosinase reactor in on-line high performance liquid chromatography. *Analytica Chimica Acta*, 2006;580, 271-277.
- Pan G, Kurumada KI. Hybrid gel reinforced with coating layer for removal of phenol from aqueous solution. *Chern Eng*, 2008;138:194-199.
- Akbal F, NurOnar A. Photocatalytic degradation of phenol. *Environmental monitoring and assessment*, 2003;83:295-302.
- Busca G, Berardinelli S, Resini C, Arrighi L. Technologies for the removal of phenol from fluid streams: a short review of recent developments. *J Hazard Mater*, 2008;160:265-288.
- Rivas FJ, Beltran FJ, Gimeno O, Alvarez P. Treatment of brines by combined Fenton's reagent-aerobic biodegradation II Process modeling. *J Hazard Mater*, 2003;96:259-276.
- Gernjak W, Krutzler T, Glaser A, Malato S, Caceres J, Bauer R, Fernandez-Alba AR. Photo-Fenton treatment of water containing natural phenolic pollutants. *Chemosphere*, 2003;50:71-78.
- Rengaraj S, Moon SH, Sivabalan R, Arabindoo B, Murugesan VJ. Removal of phenol from aqueous solution and resin manufacturing industry wastewater using an agricultural waste: rubber seed coat. *J Hazard Mater*, 2002;89(2-3):185-196.
- Huang J, Wang X, Jin Q, Liu Y, Wang Y. Removal of phenol from aqueous solution by adsorption onto OTMAC-modified attapulgite. *Environ Manage*, 2007;84:229-236.
- Tepe O, Dursun AY. Combined effects of external mass transfer and biodegradation rates on removal of phenol by immobilized *Ralstonia eutropha* in a packed bed reactor. *J Hazard Mater*, 2008;15:16-19.
- Ahmaruzzaman M. Adsorption of phenolic compounds on low-cost adsorbents: a review *Adv Colloid Interface. Sci*, 2008;143:48-67.
- Bodalo A, Gomez E, Hidalgo AM, Gomez M, Murcia MD, Lopez L. Nanofiltration membranes to reduce phenol concentration in wastewater. *Desalination*, 2009;245:680-686.
- Aksu Z, Yener J.A comparative adsorption and biosorption study of mono-chlorinated phenols onto various sorbent. *Waste Manage*, 2001;21(8):695-702.
- Viraraghavan T, De Maria Alfaro F. (1998) Adsorption of phenol from wastewater by peat fly ash and bentonite. *J Hazard Mater*, 1998;57(1-3):59-70.
- Balasubramanian A, Venkatesan S. Removal of phenolic compounds from aqueous solutions by emulsion liquid membrane containing Ionic Liquid [BMIM]<sup>+</sup>[PF6]<sup>-</sup> in Tributylphosphate. *Desalination (In press)* doi: 10.1016/j.desal.2011.12.027.
- Zeng X, Fan Y, Wu G, Wang C, Shi R. (2009) Enhanced adsorption of phenol from water by a novel polar post-crosslinked polymeric adsorbent. *J Hazard Mater*, 2009;169:1022-1028.
- Li HQ, Han HJ, Du MA, Wang W. Removal of phenols thiocyanate and ammonium from coal gasification wastewater using moving bed biofilm reactor. *Bioresource Technol*, 2011;102:4667-4673.
- Bajaj M, Gallert C, Winter J. Biodegradation of high phenol containing synthetic wastewater by an aerobic fixed bed reactor. *Bioresource Technol*, 2008;99:8376-8381.
- Annadurai G, Juang R, Lee DJ. Microbial degradation of phenol using mixed liquors of *Pseudomonas putida* and activated sludge. *Waste Manage*, 2002;22:703-710.
- Pandit AB, Gogate PR, Mujumdar S. Ultrasonic degradation of 2,4,6 trichlorophenol in presence of TiO<sub>2</sub> catalyst. *Ultrason Sonochem*, 2001;8:227-231.
- Agrios A, Gray K, Weitz E. Photocatalytic transformation of 2,4,6 trichlorophenol on TiO<sub>2</sub> under sub-band-gap illumination. *Langmuir*, 2003;19:1402-1409.
- Bodalo A, Gomez JL, Gomez M, Leon G, Hidalgo AM, Ruiz MA. Phenol removal from water by hybrid processes: study of the membrane process step. *Desalination*, 2008;223:323-329.
- Mao X, Buchanan LD, Stanley SJ. Phenol



## Archive of SID

- removal from aqueous solution by fungal peroxidases. *J Environ Eng Sci*,2006;5(1):103-109.
23. Juang RSh, Kao HCh, Tseng KJ. Kinetics of phenol removal from saline solutions by solvent extraction coupled with degradation in a two-phase partitioning bioreactor *Sep Purif Technol*,2010;71 (3):285-292.
24. Bazrafshan E, Biglari H, Mahvi AH. Phenol removal by electrocoagulation process from aqueous solutions. *Fresen Environ Bull*,2012;21(2):364-371.
25. BelhadjTahara N, Savall A. Electrochemical removal of phenol in alkaline solution Contribution of the anodic polymerization on different electrode materials. *Electrochimica Acta*,2009;54:4809-4816.
26. Yavuz Y, Koparal AS. (2006) Electrochemical oxidation of phenol in a parallel plate reactor using ruthenium mixed metal oxide electrode. *J Hazard Mater*,2006;136:296-302.
27. Mahvi AH, Maleki A, Alimohamadi M, Ghasri A. Photo-oxidation of phenol in aqueous solution: Toxicity of intermediates. *Korean Journal of Chemical Engineering*,2007;24(1)79-82.
28. Maleki A, Mahvi AH, Alimohamadi M, Ghasri A. Advanced oxidation of phenol by ultraviolet irradiation in aqueous system. *Pakistan Journal of Biological Sciences*,2006;9(12):2338-2341.
29. Yang S, Zhu W, Wang J, Chen Z. Catalytic wet air oxidation of phenol over CeOrTiO<sub>2</sub> catalyst in the batch reactor and the packed-bed reactor. *J Hazard Mater*,2008;153(3):1248-1253.
30. Dizgea N, Keskinlera B, Barlas H. Sorption of Ni(II) ions from aqueous solution by Lewatit cation-exchange resin. *J Hazard Mater*,2009;167:915-926.
31. Zouboulis AI, Matis KA. Removal of metal ions from dilute solutions by sorptive flotation. *Crit Rev SciTech*,1997;27(3):195-235.
32. Rodrigues LA, Pinto Da Silva MLC, Alvarez-Mendes MO, Reis Coutinho AD, Thim GP. (2011) Phenol removal from aqueous solution by activated carbon produced from avocado kernel seeds. *Chem Eng*,2011;174:49- 57.
33. Suresh S, Srivastava VC, Mishra LM. Adsorptive removal of phenol from binary aqueous solution with aniline and 4-nitrophenol by granular activated carbon. *Chem Eng*,2011;17:1997-1003.
34. El-Naas MH, Al-Zuhair S, Abu Alhaija M. Removal of phenol from petroleum refinery wastewater through adsorption on date-pit activated carbon. *Chem Eng*,2010;162:997-1005.
35. Senturk HB, Ozdes D, Gundogdu A, Duran C, Soylak M. Removal of phenol from aqueous solutions by adsorption onto organomodified Tire bolubentonite: equilibrium kinetic and thermodynamic study. *J Hazard Mater*,2009;172:353-362.
36. Roostaei N, Handan TF. Removal of phenol from aqueous solutions by adsorption. *EnvionManag*,2004; 70: 157-164.
37. Kitis M, Karakaya E, Yigit NO, Civelekoglu G, Akcil A. Heterogeneous catalytic degradation of cyanide using copper-impregnated pumice and hydrogen peroxide. *Water Res*,2005;39:1652-1662.
38. Karagoz S, Tay T, Ucar T, Erdem M. Activated carbons from waste biomass by sulfuric acid activation and their use on methylene blue adsorption. *BioresourceTechnol*,2008;99:6214-6222.
39. Hegazy AK, Hammouda O, Lovett-Doust J, Gomaa NH. Population dynamics of *Moringa peregrina* along altitudinal gradient in the northwestern sector of the Red Sea *J Arid Environ*,2008;72: 1537-1551.
40. Saeedi M, Pazhoheshfar S P. Adsorption of phenol from contaminated water using activated carbon and carbon-skinned almond sand walnuts. *J Environ Sci & Tech*,2008;10(4):218-231(persian).
41. Greenberg AE. Standard methods for the examination of water and wastewater. 19th ed. Washington: American Public Health Association; 1995.
42. Liu TZ, QS, Wang P, Jiang JP, Li N. Adsorption isotherm kinetic and mechanism studies of some substituted phenols on activated carbon fibers. *Chern Eng*,2010;157:348-356.
43. Rengaraj S, Moon SH, Sivabalan R, Arabindoo B, Murugesan V. Agricultural solid waste for the removal of organics: adsorption of phenol from water and wastewater by palm seed coat activated carbon. *Waste Manage*,2002;22(5):543-548.

*Archive of SID*

44. Chakravarty P, Sarma NS, Sharma HP. Removal of Pb (II) from aqueous solution using heartwood of *Areca catechu* powder. *Desalination*,2010;256:16-21.
45. Calvete T, Lima EC, Cardoso NF, Dias SLP, Pavan FA. Application of carbon adsorbents prepared from the Brazilian-pine fruit shell for removal of Procion Red MX 3B from aqueous solution-kinetic equilibrium and thermodynamic studies. *Chem Eng*,2009;155:627-636.
46. Cengiz S,Cavas L. Removal of methylene blue by invasive marine seaweed: *Caulerparacemosavarcyclindracea*. *Bioresource Technol*,2008;99:2357-2363.
47. SenthilKumar P,Ramalingam S,Sathyaselvabala V, Dinesh Kirupha S, Sivanesan S. Removal of copper(II) ions from aqueous solution by adsorption using cashew nut shell. *Desalination*,2011;266:63-71.
48. Anbia M, Asl Hariri S. Removal of methylene blue from aqueous solution using nanoporous SBA-3. *Desalination*,2010;261:61-66.
49. Hameed BH, Din ATM, Ahmad AL. Sorption of methylene blue onto bamboo based activated carbon: kinetics and equilibrium studies. *J Hazard Mater*,2007;141:819-825.
50. Ertas M, Acemioglu B, Hakki Alma M, Usta M. Removal of methylene blue from aqueous solution using cotton stalk cotton waste and cotton dust. *J Hazard Mater*,2010;183:421-427.
51. Basava Rao VV, Ram Mohan Rao S. Adsorption studies on treatment of textile dyeing industrial effluent by fly ash. *Chem Eng*,2006;116:77-84.
52. Acemioglu B. (2004) Adsorption of Congo red from aqueous solution onto calcium-rich fly ash. *Colloid Interf Sci*,2004;269:303-309.