

## Preparation and characterization of terbium oxide doped sodium tetraborate glasses

A . A .Aleml , L.Kafi –Ahmadi, sh. Karamipour

*Department of Inorganic Chemistry, Faculty of Chemistry, University of Tabriz, Tabriz, IRAN*  
*Email: abdolalialeml@Yahoo.com*

(Received: 6/4/2008, in revised form: 5/12/2008)

**Abstract:** Terbium oxide doped tetraborate glasses were prepared from the reaction of  $Tb_2O_3$  and  $Na_2B_4O_7 \cdot 10 H_2O$  on reagent grade. At first, the base borate glass of  $Na_2B_4O_7$  was prepared by melting dehydrated borax at  $1000\text{ }^\circ C$  for 30 min and then the obtained base glass was crushed and powdered. Appropriate amounts of  $Tb_2O_3$  (5-20 mol %) and  $Na_2B_4O_7$  powdered glass were mixed and melted at  $1200\text{ }^\circ C$  for 15 min. By transferring the melt in a cold steel sample holder and pressing, the final glasses were obtained. To avoid self crushing of the obtained glass samples, they were annealed at  $300\text{ }^\circ C$  for 1h. The density of the samples, measured by using Archimedes's principle, showed that the doping of  $Tb_2O_3$  in  $Na_2B_4O_7$  increases the density of the glass. The infrared spectra of the glasses in the range of  $4000 - 400\text{ cm}^{-1}$  shows that the addition of  $Tb_2O_3$  did not introduce any new absorption band in the infrared spectrum of pure sodium tetraborate glass. Comparing of the IR spectral features of the  $Tb^{+3}$  doped glasses with undoped glass show that the evolution of the IR spectral bands is related to the structural changes produced by varying of  $Tb^{+3}$ . UV Spectroscopic study of such glasses shows that the addition of terbium oxide shifts the optical absorption edges towards lower energies. The fluorescence properties of  $(1-x) Na_2B_4O_7 \cdot xTb_2O_3$  glass system were investigated by means of the emission Spectroscopy with excitation by 377 nm light. The glass presented intense  $\sim 550\text{ nm}$  green luminescence.

**Keywords:** *Tetraborate glass; Terbium oxide; Infrared spectroscopy.*

### 1. Introduction

Glasses are useful materials with potential applications in fabrication of switching and memory devices, transducers, superiors insulators, dielectrics and ordinary electronic material [1-2]. In recent years investigation of the properties of glasses have been the object of materials researchers in electronic terms rather than simply from the chemical point of view [3]. Boron oxide form the basis for many low melting glasses and are characterized by a covalently linked boron-oxygen network. Their network structures have the form of macro-anion with boron-oxygen chains,

segments of such chains (including highly branched ones), two – dimensional layers, three – dimensional networks, and their fragments. Structural studies show that sodium borate glasses contain boroxol, tetraborate, and metaborate groups. Borate glasses have been known to be an excellent host matrices for the rare – earth oxides because of their good glass forming nature compared to other conventional systems [4]. They have attracted much attention because of their electrochemical and optical applications, namely as solid–state batteries, optical waveguides and luminescent materials [5]. Such glasses are suitable

as optical materials with high transparency, low melting point, easily – shaped, high thermal stability and good rare – earth ions solubility [6, 7]. The rare – earth ion in glass occupies the centre of a distorted cube which is made of four tetrahedr of borate and each tetrahedron contributes two oxygen's to the coordination of rare earth ions. The overall coordination number is 8 as a common coordination of rare – earth oxides [8]. The optical properties of RE ions in glasses depend on the chemical composition which determines the structure and nature of the bonds in glass matrix [9]. Traditional spectroscopic studies of lanthanide salts have been reported and traditional glasses doped with small amounts of such elements have been investigated. The difference in the spectral behavior shown by ions of d- block transition elements, is due to the fact that electrons responsible for the spectral properties of rare – earth ions are 4f electrons, and the 4f orbital are very effectively shielded from the effect of external forces by the overlying 5s<sup>2</sup> and 5p<sup>6</sup> shells. The states arising from the 4f orbital configurations are only slightly affected by the surroundings of the ions and remain particularly invariant for a given ion various compounds [10]. Sodium tetraborate is a type of sodium borate glasses that consists of one – third of sodium oxide and two – third of boron oxide. This type of borate glasses drawn great attention due to their enhanced electrical and optical properties when modified by phthalocyanine or by rare - earth cations [11]. In order to extend the available information on borate glasses containing terbium ions, we prepared the xTb<sub>2</sub>O<sub>3</sub>. (1-x) Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub> glass system with 0 ≤ x ≤ 0.2. We studied the products by UV-V is, Infrared and fluorescence spectroscopy and density measurements.

## 2. Experimental

### 2.1. Sample preparation

Samples of the x Tb<sub>2</sub>O<sub>3</sub>. (1-x) Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub> glass system with x =0.00, 0.05, 0.1, 0.15, 0.2 were prepared from the reaction of Tb<sub>2</sub>O<sub>3</sub> and Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub> .10 H<sub>2</sub>O on reagent grade. At first, the base borate glass of Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub> composition was prepared by melting dehydrated borax at 1000 °C for 30 min.

Then it was quenched on a refractory steel block. The obtained base glass was crushed and powdered by agate ball mill. Then appropriate amounts of Tb<sub>2</sub>O<sub>3</sub> and Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub> glass were mixed and melted at 1200 °C for 15 min. The glass samples were obtained by pouring the melts on stainless steel. For avoid self crushing of obtained glass sample they were annealed at 300°C for 1h.

### 2.2. X-Ray diffraction

The glassy nature of the samples, were confirmed by XRD studies using D5000 Siemens diffractometer with Cu – K<sub>α</sub> line of wavelength λ = 1.5406 Å at the scanning rate of 1 °/min. and 2θ was varied from low angle to 70°.

### 2.3. Infrared Spectra

Infrared spectroscopic studies were used to get essential information about the arrangement of the structural units of glass samples. The FT-IR transmission spectra in the region 4000 – 400 cm<sup>-1</sup> were recorded for all samples using Shimadzu Tensor 27 by KBr pellet technique.

### 2.4. Density measurement

The density of glass samples were measured using Archimedes's Law. The measurements were carried out using Shimadzu Aw 200 balance and xylene as an inert immersion liquid. The density was obtained from the relation  $d \text{ (g/cm}^3\text{)} = [a/a-b]x$  (density of xylene), where a is the weight of the glass sample in air, b is the weight of the glass sample when immersed in xylene. The density of xylene is 0.865(g/cm<sup>3</sup>) [12].

### 2.5. Optical spectram

The optical spectra were recorded using Shimadzu UV-1650 PC spectrometer in the wavelength range of 200 – 1000 nm at room temperature.


### 2.6. Flurescence measurements

The flurescence spectra was measured using Shimadzu Rf-5301PC spectrophotometer at room temperature.

## 3. Results and discussion

### 3.1. X-ray diffraction studies

The X – ray diffraction patterns of the samples confirm the amorphous nature of the glasses. Fig.1. shows the x- ray diffraction pattern of the glass sample prepared with x = 0.05 as an example.

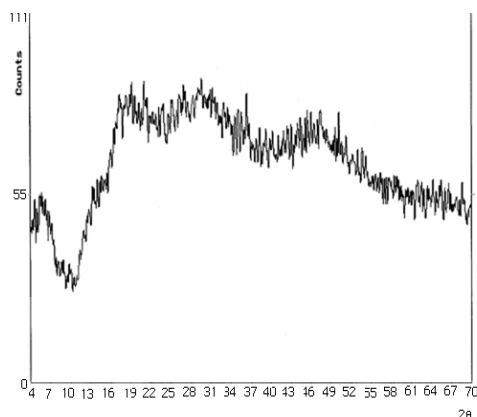

**Fig 1:** X-ray diffraction pattern of the sample with  $x = 0.05$ .

### 3.2. FT-IR analysis


The FT-IR spectra of  $Tb^{+3}$  doped sodium tetraborate glasses were obtained using KBr pellet technique in the range of  $4000 - 400 \text{ cm}^{-1}$ . Fig.2. shows the IR spectra recorded for the  $Tb^{+3}$  doped tetraborate glasses. The IR spectral features of the  $Tb^{+3}$  doped glasses are very broad due to the vitreous nature of the samples [13]. The main spectroscopic features evidenced by these spectra are characteristic of the base  $Na_2B_4O_7$  glass and were previously reported and assigned [14-15]. The weak bond around  $3400 \text{ cm}^{-1}$  is assigned to the O-H stretching which may be associated with water trapped in glasses during experiment [8].

The IR spectroscopy of borate containing compounds showed that the vibrational modes of the present network are mainly active in three infrared spectral regions [16]:

- (i) The first group of bands which occur at  $1200 - 1600 \text{ cm}^{-1}$  is due to the asymmetric stretching relaxation of the B-O bond of trigonal  $BO_3$  units.
- (ii) The second group lies between  $800$  and  $1200 \text{ cm}^{-1}$  is due to the B-O bond stretching of the tetrahedral  $BO_4$  units.
- (iii) The third group is observed around  $700 \text{ cm}^{-1}$  is due to bending of B-O-B linkages in the borate networks.

In the present glass system, it appears that all  $Tb^{+3}$  doped glasses show great similarity to the sodium tetraborate glass in their general shape of absorption spectra without the appearance of any new peaks. The vibrational absorption peaks at  $\sim 450, 720, 850$  to  $1050 \text{ cm}^{-1}$  in glasses could be due to bridging and non bridging oxygen ions which are doubly or singly bonded to high - state  $BO_4$  group and low-state  $BO_3$  groups, also to sodium ions. In the wave number region over  $800$

$\text{cm}^{-1}$  two very broad absorption bands were observed at about  $1000$  and  $1350 \text{ cm}^{-1}$ . The absorption band around  $1000 \text{ cm}^{-1}$  results as a superposition of the absorption bands from about  $850 \text{ cm}^{-1}$  (observed at  $890 \text{ cm}^{-1}$  in the vitreous  $B_2O_3$  and assigned to the boroxol rings) and at  $1050 \text{ cm}^{-1}$  (observed at  $1070 \text{ cm}^{-1}$  in borate glasses and assigned to the B-O stretching of the  $BO_4$  structural units). The broad absorption bands at about  $1350 \text{ cm}^{-1}$  results as the envelope of two important bands, the first one at  $\sim 1260 \text{ cm}^{-1}$  (typical of  $BO_3$  units[14]), the second one at  $\sim 1370 \text{ cm}^{-1}$  (characteristic of the B-O stretching mode in borate glasses, its presence confirming the vitreous nature of the  $Tb^{+3}$  doped glasses [15]). The increase of  $x$  produces a slight decrease of the absorption band from  $\sim 850 \text{ cm}^{-1}$ , mainly for  $x \geq 0.15$ , and increase of the absorption band at  $1050 \text{ cm}^{-1}$ . Also, the increase of  $x$  determines a decrease of the absorption band at  $1260 \text{ cm}^{-1}$  which becomes a shoulder for  $0.01 \leq x \leq 0.15$  and disappears for  $x = 0.20$ . The evolution of the IR spectral features of the  $Tb^{+3}$  doped glasses by modifying their  $Tb_2O_3$  content,  $x$ , is related to the structural changes produced by varying  $x$ . These structural changes consist mainly in a decrease of the amount of boroxol structural groups and  $BO_3$  structural units (converted in  $BO_4$  structural units) with increasing  $x$  up to  $0.20$ . This increase may be due to the behavior of terbium ions as glass modifier. The structural changes are studied by the IR investigation of  $Tb^{+3}$  doped glasses. We note that the mentioned structural changes lead to a more compact structure. Such behavior was previously reported for other rare - earth ions (Gd[17], Ho[18], Dy[19], Eu[13]), too, but was not reported for the terbium ions so far.

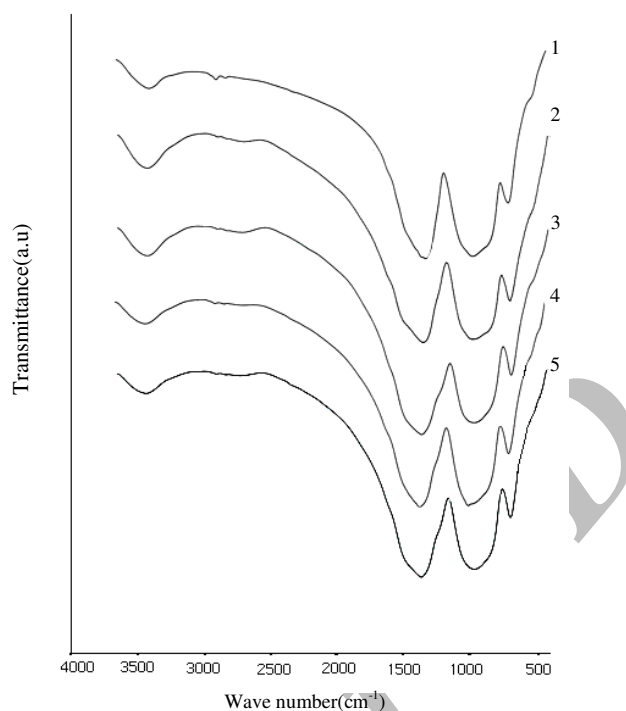

**Fig 2:** The infrared absorption spectra of  $\text{Na}_2\text{B}_4\text{O}_7$  glasses. (1) pure  $\text{Na}_2\text{B}_4\text{O}_7$  glass. (2) glass containing 5 mol%  $\text{Tb}_2\text{O}_3$ , (3) 10 mol%  $\text{Tb}_2\text{O}_3$ , (4) 15 mol%  $\text{Tb}_2\text{O}_3$ , (5) 20 mol%  $\text{Tb}_2\text{O}_3$ .

### 3. 3. Density measurement

The density of the glass and its value is important and stands on its own as intrinsic property capable of casting the light on the short range structure. Also, boron oxide in its glassy form is a laminar network consisting of boron atoms 3- fold coordinated with oxygen which can form 6-membered boroxol rings ( $\text{B}_3\text{O}_6$ ), as reported earlier by Krogh – Moe [20]. When an alkali oxide modifies the pure boron oxide, the additional oxygen, obtained by the oxide dissociation, causes a conversion from the trigonal boron atoms  $\text{BO}_3$  into 4- fold coordinated boron atoms as  $\text{BO}_4$ . Each  $\text{BO}_4$  structural group is negatively charged and the four oxygen's are included in the network as bridging oxygen. These units are responsible for the increase in the connectivity of the glass network. As a result , the degree of the structural compactness and modification of the geometrical configuration in the glass network can vary with a change in the composition[11]. Fig.3. and Table 1. show that the general trend of the density of  $\text{Tb}^{+3}$ -doped glasses is to increase with increasing terbium ion content. This behavior is due to the

higher number of terbium ions accommodated in the vitreous matrix. Note that the density vs x increase is not linear and the increase of the density is slower for the (10 = x = 15) mol% composition range. This behavior suggests that a more complicated mechanism, also implying the structural changes determined by varying x, must be considered to explain the density – composition relation. Taking into account that for (10 = x =15) mol % the IR data indicates the conversion of  $\text{BO}_3$  into  $\text{BO}_4$  structural units leading to a less compact structure of the glass matrix and consequently to a decrease of its density, we obtain a reasonable explanation of the density – x relation in the composition range mentioned.

### 3.4. Optical absorption and fluorescence measurements

Judd – ofelt theory is the most suitable theory to characterize the intensities of forced electric dipole transitions between 4f states of lanthanide ions. Since the absorption and emission probabilities for an ion matrix combination are given as a function of a set of there parameters, i. the intensity or judd – ofelt parameters [21-22].

According to the Judd-ofelt theory, the oscillator strength,  $P_{cal}$  (a J; b J'), of an electric dipole absorption transition from the initial state  $|aJ\rangle$  to the final state  $|bJ'\rangle$  depends on three parameters ( $\lambda = 2, 4, 6$ ) as given by :

$$P_{cal}(aJ; bJ') = \frac{8\pi^2 mc}{3h} \frac{\tilde{\nu}_p}{2J+1} \frac{(n^2+2)^2}{9n} \sum_{\lambda=2,4,6} \Omega_{\lambda} |\langle aJ || U^{(\lambda)} || bJ' \rangle|^2$$

Where  $\tilde{\nu}_p$  is the barycenter of the transition,  $n$  is the refractive index,  $m$  is the electron mass,  $c$  is the velocity of light,  $h$  is the Plank constant and  $\langle || U^{(\lambda)} || \rangle$  are the double reduced matrix elements of the unit Tensor operators [23]. The optical absorption measurements were made at room

temperature for the pure ( $\text{Na}_2\text{B}_4\text{O}_7$ ) glasses doped with  $\text{Tb}_2\text{O}_3$  as indicated in Table 1. Fig. 4 shows the absorption as a function of wavelength for  $\text{Na}_2\text{B}_4\text{O}_7$  glass containing 10 mol%  $\text{Tb}_2\text{O}_3$ . It is clear that the region of high absorption is in the ultraviolet range and seems to move to longer wavelengths as  $\text{Tb}_2\text{O}_3$  content increases. Furthermore, it is noted that there is a single absorption peak due to  $\text{Tb}^{3+}$  around 300 nm for all glass samples doped with  $\text{Tb}_2\text{O}_3$  due to the transition  $4f^8$  to  $4f^75d$  and the f-f transitions within  $\text{Tb}^{3+} 4f^8$  configuration have not been seen clearly due to their weak intensity.


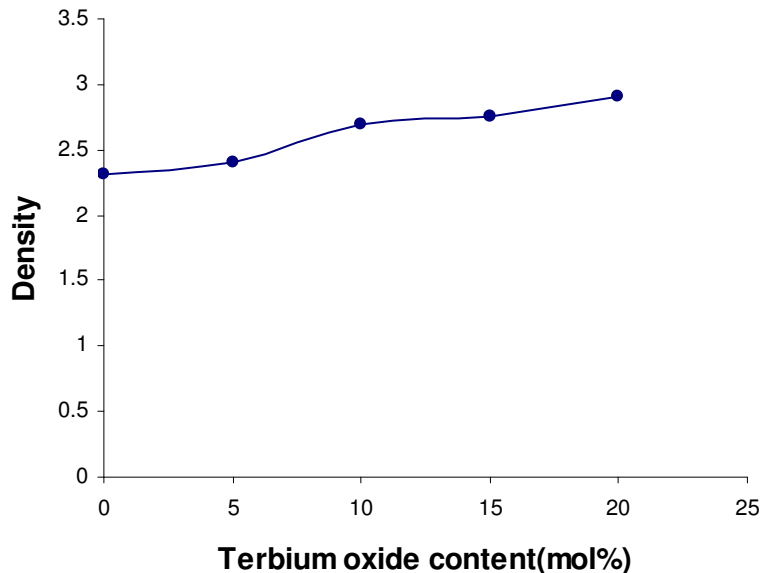


Fig.3: Variation of density with terbium oxide content.

Table 1 Chemical composition and density of glasses in the system ( $\text{Na}_2\text{B}_4\text{O}_7$ - $\text{Tb}_2\text{O}_3$ ).

Glass sample	Composition(%mol)		Density( g / cm <sup>3</sup> )
	$\text{Na}_2\text{B}_4\text{O}_7$	$\text{Tb}_2\text{O}_3$	
1	100.00	0.00	2.310
2	95.00	5.00	2.40
3	90.00	10.00	2.70
4	85.00	15.00	2.76
5	80.00	20.00	2.90

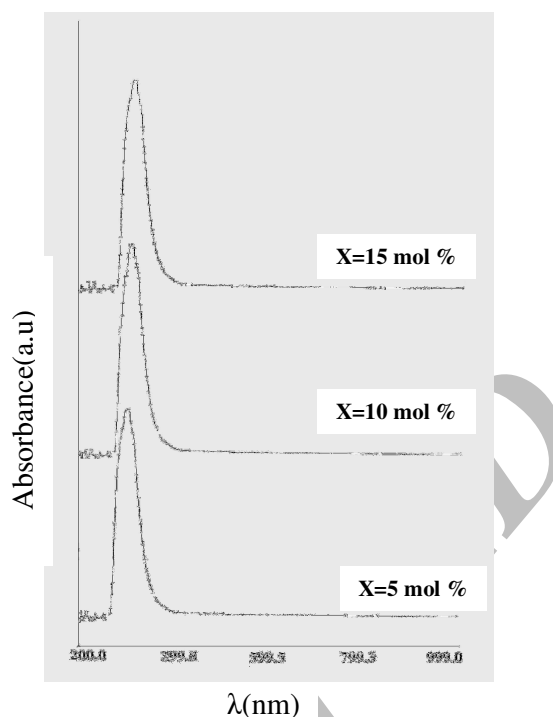

**Fig. 4:** UV spectrum of  $\text{Na}_2\text{B}_4\text{O}_7$  glass containing 5 , 10 15 mol %  $\text{Tb}_2\text{O}_3$

When  $\text{Tb}^{+3}$  ion is excited to  $^5\text{D}_3$  or a higher level, the radiative transition from  $^5\text{D}_3$  to  $^7\text{F}_j$  ( $j = 0 - 6$ ) results in a series of  $^5\text{D}_3$  emission in the blue region, while that from  $^5\text{D}_4$  to  $^7\text{F}_j$  yields another series of  $^5\text{D}_4$  emission in the green region. Since the energy difference between  $^5\text{D}_3$  and  $^5\text{D}_4$  matches with that between  $^7\text{F}_0$  and  $^7\text{F}_6$ , the excited ion at  $^5\text{D}_3$  (energy donor) relaxes its state to  $^5\text{D}_4$ , releasing the energy to resonantly excite the nearest unexcited ion (energy acceptor) from  $^7\text{F}_6$  to  $^7\text{F}_0$ . This process is called resonant energy transfer, whose probability is proportional to  $(R_0/R)^s$ , where  $R$  stands for inter-ionic distance and  $R_0$  for the critical distance. The value of  $R_0$  for typical multipolar interaction is in the range of 10-20 Å and  $s = 6$  for dipole – dipole and  $s = 8$  for dipole–quadrupole interactions [24].

Terbium – activated phosphors are excellent emitters of green light. Furthermore,  $\text{Tb}^{+3}$  ion luminescence under uv excitation usually consists of four main emission lines around 490 (blue), 545 (green), 580 (yellow) and 620 (red) nm. These emission lines correspond to the  $^5\text{D}_4 \rightarrow ^7\text{F}_j$  ( $j = 6, \dots, 3$ ) transitions as shown in Fig.5 for  $\lambda_{\text{ex}} = 360$  nm[25]:

In addition to these emission lines, a considerable contribution from the higher- level emission  $^5\text{D}_3 \rightarrow ^7\text{F}_j$  is often observed in the luminescence.

The typical luminescence of  $\text{Tb}^{+3}$  appears to be green to the human eye, because the emission due to the  $^5\text{D}_4 \rightarrow ^7\text{F}_5$  transition ( $\approx 545$  nm) usually dominates overall emissions. The fluorescence intensity is considered to be dependent on the host lattice through the crystal field [26].

The fluorescence spectra were measured by using a fluorospectrometer at room temperature. Fig.6. shows the fluorescence spectra of  $x\text{Tb}^{+3}$  in  $\text{Na}_2\text{B}_4\text{O}_7$  glass sample ( $x = 0.15$ ). Fluorescence spectra and intensity of RE ions are dependent on the symmetry and strength of crystal field, because the optical radiation of RE ion is mainly due to forced electric dipole transition. Kuboniwa and Hoshina reported a good agreement between observed fluorescence and calculated values for  $\text{Tb}^{+3}$  in some oxides such as  $\text{YPO}_4$ ,  $\text{YBO}_3$  and  $\text{ScBO}_3$ . Their theoretical calculation along the Judd – ofelt [21] approximation showed that the  $^5\text{D}_4 \rightarrow ^7\text{F}_5$  transition has the largest probability in the  $^5\text{D}_4 \rightarrow ^7\text{F}_j$  ( $j = 3, 4, 5, 6$ ) transitions for all these matrices. It was also pointed out that the intensity of  $^5\text{D}_4 \rightarrow ^7\text{F}_3$  transition can become comparable to that of  $^5\text{D}_4 \rightarrow ^7\text{F}_5$  when the crystal field is very strong, where the  $^7\text{D}$  state of the  $4f^7$  ( $^8\text{S}$ )  $5d$  configuration was assumed to be admixed into the  $4f^8$  configuration [26].

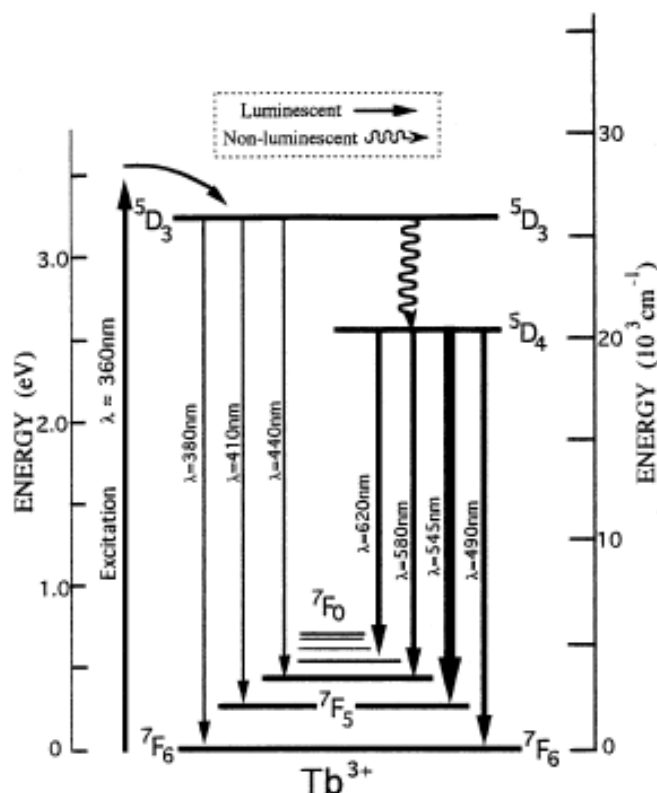


Fig.5 Energy levels and emission processes of  $Tb^{+3}$  ion at  $\lambda_{ex}= 360$  nm.

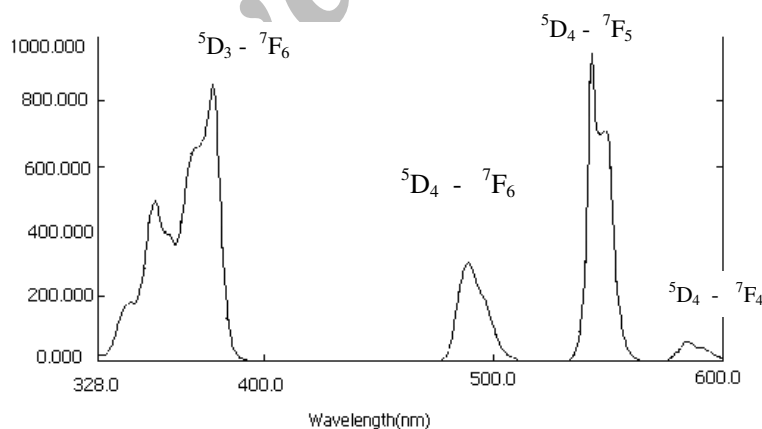


Fig. 6. Fluorescence spectra of  $Tb^{+3}$  in  $Na_2B_4O_7$  glass sample( $x =0.15$ )

#### 4. Conclusions

Glasses in the system  $(1-x)Na_2B_4O_7 \cdot xTb_2O_3$  ( $0.00 \leq x \leq 0.20$ ) were prepared using the press - quenching technique from the glasses melts. The FT-IR spectroscopy of the glasses were measured and evaluated to confirm the internal structure

arrangements of the building units of such glasses as a result of the progressive replacement of  $Na_2B_4O_7$  by  $Tb_2O_3$ . IR measurements suggests that  $Tb^{+3}$  ions play a network modifier role in  $Tb^{+3}$  doped glasses. Increase of  $x$  up to 0.15 determines important structural changes, but only slight ones

for higher x values. Density measurements support this assumption. The study of the optical absorption of sodium tetraborate glasses containing  $Tb_2O_3$  in the wavelength range from 200-1000 nm revealed an absorption peak in the ultraviolet range that seems to move to longer wavelength as  $Tb_2O_3$  content increase. IR spectroscopic and density measurements performed on  $xTb_2O_3$ . (1 - x.) $Na_2B_4O_7$  glasses show that modifying the terbium ion content of samples leads to structural changes in the host vitreous matrix. These data show that the terbium ions play a network modifier role in the studied glasses. The fluorescence properties of (1-x)  $Na_2B_4O_7$  . $xTb_2O_3$  glass system were investigated by means of the emission spectra with excitation by 377 nm light, the glass presented intense ~ 550 nm green luminescence.

#### Acknowledgements

The authors acknowledge the financial support from the research council of University of Tabriz.


#### Reference

- [1] Meckenzie. J. D, "Vitreous state encyclopedia of physics", Reinhold, New York (1966) 769.
- [2] El .Desoky .M. M, Al – Shahrani .A, "Iron doping of semiconducting bismuth alkali borate glasses", Physica B, 383(2006) 163-170
- [3] Kutub .A. A, Bargawi .A.Y, Maghrabi .K.A, "Optical and DSC studies of the  $Na_2B_4O_7$ - $Pb_3O_4$  glass system", J. Mater. Sci.22 (1987)3607- 3610
- [4] Alemi .A. A, Sedghi. H, Mirmohseni. A. R and Golsanamlu .V, "Synthesis and characterization of Holmium oxide doped Cadmium Lead borate glasses", Bull. Mater. Sci., 29(2006) 55–58
- [5] Pisarski .W.A, Goryczka .T, Wodecka – Dus .B, Plonska. M, Pisarska ."Structure and properties of rare – earth doped Lead borate glasses", J. Mater. Sci and Eng. B 122(2005) 94-99
- [6] Huang. L , Wang. X, Lin .H and Liu .X , "Luminescence properties of  $Ce^{+3}$  and  $Tb^{+3}$  doped rare earth borate glasses", J. Alloys and Compounds , 316(2001),256-259
- [7] Lin. H , Yue – Bun pun .E, Wang .X , Liu. X, J. "Intense visible fluorescence and energy transfer in  $Dy^{+3}$ ,  $Tb^{+3}$ ,  $Sm^{+3}$  and  $Eu^{+3}$  doped rare-earth borate glasses", Alloys and compounds 390(2005)197-201
- [8] Babateen .M.O, Kutub .A.A , "A study of the optical properties of sodium tetraborate glasses containing ytterbium", Umm Al – Qura univ.J.Sci.Med.Eng. 17 (2005), 155- 165
- [9] Venkatramu. V, Babu.P, Jayasankar. C.K , "Fluorescence properties of  $Eu^{+3}$  ions doped borate and fluoroborate glasses containing lithium , zinc and lead", Spectrochimica Acta part A 63(2006)276-281
- [10] Kutub. A. A , Shawoosh .A.S, "Optical and differential scanning calorimetry studies of the ( $Na_2B_4O_7$ )-(CuO)-(CeO<sub>2</sub>) glass system" , J. Mater. Sci., 32(1997)5491-5495
- [11] Saddeek .Y.B, Abd. El Latif .L, "Effect of TeO<sub>2</sub> on the elastic moduli of sodium borate glasses" , Physica B, 348( 2004)475-484
- [12] Karthikeyan. B, Mohan .S, "Structural, optical and glass transition studies on  $Nd^{+3}$  – doped Lead bismuth borate glasses", Physica B, 334(2003)298
- [13] Culea. E , Ristoiu .T, Bratu . I , Ristoiu. D, "Structural and magnetic behavior of some borate glasses containing europium ions", Mater. Sci. Eng B, 75(2000)82-84
- [14] Sharma .B.K, Dube .D.C, Mansingh. A, "Preparation and characterization of  $V_2O_5$ - $B_2O_3$  glasses" J.Non-Cryst.solids 65(1984)39
- [15] Quan .Y.T, Adams .C.E , "Vapor pressure measurements and a structural interpretation in the liquid system rubidium monoxide- Boron oxide", J.Phys.Chem, 70(1966)331
- [16] Ghoneun .N.A, Batul .E.I, Abdel Shafi. H.A, Azooz. M.H, "Proceeding of Egyption conference of chemistry" ,1996,162
- [17] Ristoiu.T, Culea.E, Bratu.I, "Spectroscopic and magnetic behaviour of some borate glasses containing gadolinium ions", Materials Let. , 41(1999) 135-138
- [18] Culea .E, Ristoiu.T, Bratu. I, "Magnetic and structural behaviour of some borate glasses containing holmium ions", Mat.Sci.Eng.B 57(1999) 259-261
- [19] Culea .E, Bratu. I, "Structural and magnetic behaviour of some borate glasses containing



- dysprosium ions*", J.Non-Cryst.Solids262(2000) 287-290
- [20] Krogh-Moe .*"The crystal structure of lithium diborate,  $Li_2O-2B_2O_3$ "*, J, Acta Crystallogr. 15(1962) 190
- [21] Judd .B.R, *"Optical absorption intensities of rare-earth ions"*, Phys. Rev. 127 (1962) 750
- [22] Ratnakaram .Y. C, Vijaya kumar. A, Chakradhar. R. P.S, *"Optical absorption and emission properties of  $Pr^{+3}$  and  $Er^{+3}$  in lithium cesium mixed alkali borate glasses"*, J. lumin, 118(2006) 227-237
- [23] Speghini. A, Peruffo. M, Casarin. M, Ajo. D, Bettinelli. M,*"Electronic spectroscopy of trivalent lanthanide ions in lead zinc borate glasses"*, J.Alloys and compounds 300-301(2000)174-179
- [24] Hayakawa .T, Kamata. N, Yamada. K ,*"Visible emission characteristics in  $Tb^{+3}$  doped fluorescent glasses under selective excitation"*, J.Lumin.G8,1996,179
- [25] Tonooka. K, Shimokawa. K, Nishimura. O, *"Influence of surface treatment on the Li doping /undoping reaction at a mesophase low temperature carbon fiber"*, Solid state Ionics, 151(2002)105-110
- [26] Tonooka. K, Nishimura .O ,*"Spectral changes of  $Tb^{+3}$  fluorescence in borosilicate glasses"*, J. Lumin , 87-89 (2000) 679-681 .

Archive of SID



## تهیه و مطالعه شیشه های سدیم تترابورات دوپه شده با اکسید تریوم

عبدالعلی عالمی، لیلا کافی احمدی، شهناز کرمی پور

گروه شیمی معدنی، دانشکده شیمی، دانشگاه تبریز  
پست الکترونیکی: [abdolalialemi@yahoo.com](mailto:abdolalialemi@yahoo.com)

(دریافت مقاله ۱۸/۱/۸۷، نسخه نهایی ۱۵/۹/۸۷)

**چکیده:** شیشه های تترابورات دوپه شده با اکسید تریوم از واکنش  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10 \text{H}_2\text{O}$  و  $\text{Tb}_2\text{O}_3$  سنتز شدند. ابتدا شیشه بوراته  $\text{Na}_2\text{B}_4\text{O}_7$  با ذوب بوراکس آبزدایی شده در  $1000^\circ\text{C}$  درجه سانتیگراد به مدت ۳۰ دقیقه تهیه بعد از سرد شدن شیشه حاصل را به صورت پودر کاملا نرم در آورده آن را با مقادیری از (۵-۲۰ مول در صد) از اکسید تریوم مخلوط و در دمای  $1200^\circ\text{C}$  درجه سانتیگراد به مدت ۱۵ دقیقه حرارت داده ضمن انتقال مذاب شیشه ای به قالب استیلی پرس شدند. برای جلوگیری از خرد شدن خودبخودی در دمای  $300^\circ\text{C}$  درجه سانتیگراد به مدت ۱ ساعت تنش زدایی و مورد مطالعه قرار گرفتند. دانسیته نمونه های شیشه ای با استفاده از قانون ارشمیدس اندازه گیری شده و مشخص شد که دوپه کردن  $\text{Tb}_2\text{O}_3$  در  $\text{Na}_2\text{B}_4\text{O}_7$  منجر به افزایش دانسیته می شود. طیف مادون قرمز شیشه ها در ناحیه  $400-4000 \text{ cm}^{-1}$  نشان می دهد که با افزایش  $\text{Tb}_2\text{O}_3$  هیچ باند جذبی جدیدی نسبت به شیشه  $\text{Na}_2\text{B}_4\text{O}_7$  خالص ظاهر نمی شود. مقایسه طیف مادون قرمز شیشه های دوپه شده با تریوم با شیشه بدون دوپه نشان می دهد که تغییر تدریجی باندهای IR به تغییرات ساختاری ایجاد شده با تغییر مقدار تریوم مربوط می شود. طیف ماورای بنفش شیشه ها نشان می دهد که افزایش اکسید تریوم لبه جذب نوری را به سمت انرژی های پایین تر جابجا می کند. خواص فلورسانس شیشه های  $(1-x)\text{Na}_2\text{B}_4\text{O}_7 \cdot x\text{Tb}_2\text{O}_3$  از طریق تحریک آنها توسط نوری با طول موج ۳۷۷ نانومتر مورد بررسی قرار گرفت و مشاهده شد که لومینسانس سبز شدیدی در طول موج تقریباً ۵۵۰ نانومتر ظاهر می شود.

**واژه های کلیدی:** شیشه تترابورات، اکسید تریوم، اسپکتروسکوپی مادون قرمز.