

Microbiological Leaching of Al from the Waste of Bayer Process by Some Selective Fungi

Ghorbani, Yousef*⁺

Department of Mining Engineering, Sahand University of Technology, Tabriz, I.R. IRAN

Oliazadeh, Manouchehr

Department of Mining Engineering, Faculty of Engineering, University of Tehran, Tehran, I.R. IRAN

Shahverdi, Ahmad Reza

Department of Pharmaceutical, Biotechnology School of Pharmacy, University of Tehran, Tehran, I.R. IRAN

ABSTRACT: In present investigation the biological leaching of aluminum by isolated fungi from red mud, the main waste product of the alkaline extraction of Al from bauxite was studied. Biological leaching experiments were carried out using indigenous, date and orange specimen fungi, *Aspergillus Niger*, *Penicillium simplicissimum notatum*. Savored Dextrose chloramphenicol Agar (SDA) was used as medium for the selected fungi. All microorganisms were tested for acid-production and leaching capabilities of aluminum from red mud. Leaching tests were performed in 250 mL Erlenmeyer flasks at 28 °C and at 150 rpm under aseptic conditions. Preheating of red mud and its impact on leaching process was investigated. Indigenous specimen fungi were the most efficient of the fungal cultures; 2082 mg of Al_2O_3/l was solubilized at 15 % pulp density of red mud. The metal content of leaching solution was determined by using wet chemical and atomic absorption spectrophotometer.

KEY WORDS: Biological leaching, Red mud, Waste, Bayer process, *Aspergillus niger*, *Penicillium simplicissimum*, Fungi.

INTRODUCTION

Red Mud is the main waste waste produced by the alkaline extraction of Al from bauxite (Bayer process). Bauxite is an ore with a high concentration of aluminium compounds. This high aluminium content makes bauxite a useful raw material for the extraction of aluminium [1]. To produce primary aluminium, the aluminium compounds

in the bauxite is first dissolved chemically, using caustic soda, in an alumina refinery. This produces aluminium oxide. Red mud, which is a slurry containing natural substances originally present in the bauxite. The ore residues with a residual amount of alkali - is left over from the process. The high concentration of iron compounds

* To whom correspondence should be addressed.

+ E-mail: ghorbani@sut.ac.ir

1021-9986/09/1/109

7/\$2.70

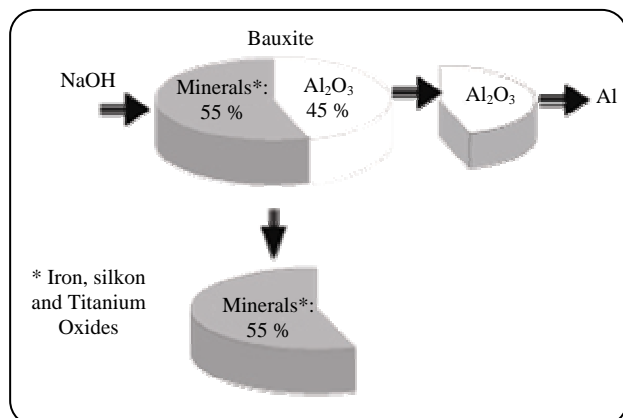


Fig. 1: Aluminium oxide is dissolved out of the bauxite and processed further to aluminium. The residue containing a mixture of naturally occurring minerals is then transferred to a disposal site.

gives the waste product its characteristic red colour. The amount of red mud produced depends on the aluminium content of the bauxite. Bauxite ores with a high aluminium content result in lower ore residues than bauxite ores with a lower aluminium content, see Fig. 1 [2].

Typical compositions for industrially used bauxite are Al₂O₃ (40-60) %, combined H₂O (12-30) %, Fe₂O₃ (7-30) %, SiO₂ free and combined (1-15) %, TiO₂ (3-4) %, F, P₂O₅, V₂O₅, etc.(0.0-5-0.2) % [3], the caustic insoluble bauxite minerals composing the red muds are typically hematite, that gives the characteristic colour to red mud, and aluminium goethite, along with titanium dioxides and occasionally some boehmite [4].

Many attempts have been made to find environmentally safe methods to dispose of or use red mud. *Thakur* and *Sant* [5,6], have listed a number of uses for this waste, such as absorbents to remove H₂S from industrial emissions; constituents in building materials such as bricks, ceramics, cement, concrete, and road materials' coagulants to remove phosphate in wastewater treatment; catalysts in coal hydrogenation or in the preparation of anticorrosive materials and pigments particularly useful in marine environments [6]; as a pH modifier in heap leaching of gold bearing ores and as a neutralizing agent for acid wastes such as those obtained from the production of gypsum or titanium dioxide. Finally, some workers have also tried to recover reusable substance and/or valuable metals from red mud by using different chemical extraction processes but, due to their high complexity and/or their elevated cost, none have

been feasible on an industrial scale [7]. The use of bioleaching process under these conditions seems promising.

The metabolic process of fungi is similar to a great extent to those of higher plants with the exception of carbohydrate synthesis. The glycolytic pathway converts the glucose into variety of products including organic acids [8]. Bioleaching processes are mediated due to the chemical attack by the extracted organic acids on the ores. The acids usually increase metal dissolution by lowering the pH and increasing the load of soluble metals by complexation/chelating into soluble organic-metallic complexes [9]. The main objective of this study was to utilize indigenous specimen fungi, *A. Niger* and *P. Simplicissimum* notatum for alumina solubilization from red mud, Jajarm Alumina Plant (Iranian Alumina Co.) main waste.

The relevant objectives are mineralogical and elemental analysis of red mud sample, characterization of organic acids in fermented media by HPLC, shake flask leaching studies of red mud and chemical analysis of leach liquor. This work will open up a new era to beneficiate red mud through biotechnological route in Iran.

MATERIALS AND METHODS

Red mud

Red mud samples were obtained from Jajarm Alumina Plant (Iranian Alumina Co.). The red mud was dried to constant weight, and after blending, divided for chemical and mineralogical analysis. The chemical analysis of red mud sample was carried out by X-ray fluorescence (XRF) and X-ray diffraction technique (XRD) was used to determine the mineralogical composition of red mud, see table 1.

Fungi

Strains of indigenous fungi (*A. Niger* and *P. Simplicissimum Simplicissimum*) were isolated from soil and water samples of Jajarm Alumina Plant region by using Sabouraud dextrose chloramphenicol agar (SDA) as a solid nutrient media. The media composition was as follows (g/L): peptone, 10; D (+) Glucose, 45; chloramphenicol, 0.5; and agar, 15. Growth of strains was studied in static condition as *Pry*, second and slant strain culture. The strains were characterized by the colored

Table 1: Chemical and mineralogical composition of red mud.

Chemical composition	Wtight (%)	Mineralogical composition	Wtight (%)
Al ₂ O ₃	17	Katoite	38
Fe ₂ O ₃	29.19	Hematite	22
CaO	15.14	Sodium Aluminum Silicate	30
SiO ₂	14.52	Anatase	8
TiO ₂	9.24		

methods using methylene blue (C₁₆H₁₈ClN₃SXH₂O) and isolated cultures were fungi, was confirmed by Institute Pasteur, Iran. *A. Niger* isolated from soil sempsum (Dilutions:1/100) was named PTCC 1001 and the *P. Simplicissimum* *Simplicissimum* fungi isolated from water sempsum PTCC 1002.

Acid production process

The ability of fungi to produce acid was tested. The medium for kinetic studies of *A.Niger* is (%) glucose, 50; sodiums nitrate, 1.5; potassium de hydrate phosphate, 0.5; potassium chlorate, 0.025; magnesium sulfate.7H₂O, 0.025; and yeast extraction, 1.6. For *P. Simplicissimum* it is (%) glucose, 50; sodiums nitrate, 1.5; potassium dihydrate phosphate, 0.5; potassium chlorate, 0.025; magnesium sulfate, 0.025; and yeast extrac, 0.1. All the salts were of analytical grade mineral salt solution was sterilized by autoclaving at 121 °C for 15 min and glucose solution was sterilized at same temperature for 5 min. The pH of mineral medium was adjusted to 5.4 with sodium hydroxide (NaOH) using digital pH meter. Inoculums of *A. Niger* and *P.Simplicissimum* were made in the shake flasks containing growth media. These flasks were incubated at 30 °C and 150 rpm for 15 days.

Characterization of organic acids in fermented media

The concentration of organic acids produced by *A. Niger* and *P. Simplicissimum* strains was determined by high performance Liquid chromatography (HPLC). Separation of citric and oxalic acids was carried out in an CLC-C825 CM caption exchange column; mobile phase, 90 % H₂O and 10 % CH₃OH; flow rate, 1 mL/min and temperature 35 °C.

Pry heating of red mud

Researches have showed Aluminum solubilization is increased considerably by heating the clays at 600 to

650 °C for 1 to 2 h. The treatment caused amotphication of the raw material due to the separation of water form the hydroxylic groups in the crystalline structures of the clay minerals. The heat treatment not only enhances the aluminum leaching also inhibits the iron leaching. The latter effect is considered very important, as iron impedes the subsequent extraction of aluminum from the pregnant solution [10], in this investigation pry heating of red mud and its impact on bioleaching process was studied and red mud was heated at 650 °C for 1.5 h.

Bioleaching studies of red mud

Metabolite of fungal growth medium was used for shake flaske bioleaching studies of red mud. Bioleaching experiment was carried out in 250 mL Erlenmeyer flasks containing 100 mL of metabolite having red mud pulp density of 5 %. The initial pH of metabolite was in range of 2-2.5. In contrast, chemical sterile control flasks were also included in leaching experiment, in the strile control flasks, 5 mL of a methanol solution containing 2 % thymol were added instead of th inoculum. All flasks were incubated on shaker at 150 rpm for 24 h. In the time course, samples were removed at intervals and centrifuged to remove solid suspension elements. Soluble content of metal were determined by using atomic absorption spectrophotometer and wet chemical methods. In the bioleaching experiment, the mixture of chlorate and nitrate acids with metabolite was tested.

RESULTS AND DISCUSSION

Fungal growth characteristics

Light yellow colored and tiny beads appeared after about 20 h of incubation in shaking flasks. Size and number of beads increased in both pencillum and *A. Niger* on 7th day of incubation, In the flasks containing *Penicillum* the hyphae were branched, scale-like with knobby ends. On the condensed mass, small hyphae

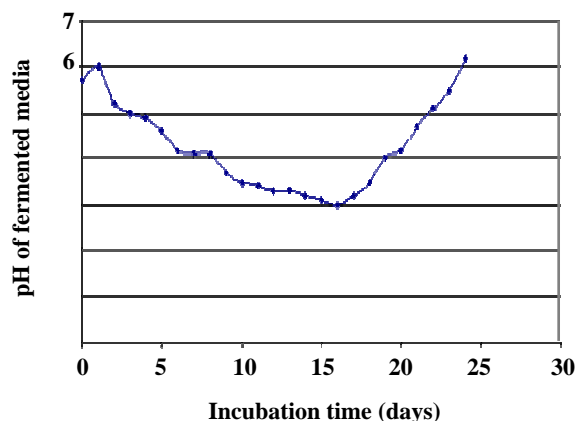


Fig. 2: pH profile glucose fermented media by *P. Simplicissimum*.

appeared and the color of hyphae was changed from white to bluish green after three days. This bluish green color was of conidia because the hyphae of *P. Simplicissimum* are colorless [4-11]. Changes in fungal morphology during growth of *A. Niger* was also observed. On 12th day, a delicate physiological change of mycelium is reflected in its morphology characterized by appearance of abnormally short, multiply branched, bulbous hyphae in both cases which remained persistent up to 16th day of incubation. Subsequently citric acid formation under these conditions proceeds rapidly [4].

pH Changes during fungal growth

The growth of fungus was followed by noting the pH of media from time to time. In *P. Simplicissimum* decrease in pH from day 12-18 was observed in the range of 3.6-3.2, see Fig. 2. Citric and oxalic acids were mainly produced by the fungi using glucose as energy source [4]. Decrease in pH was observed due to the organic acid production via incomplete oxidation of glucose by *P. Simplicissimum* species which can be formulated as Eqs. (1) and (2):



The accumulation of organic acids by *A. Niger* is markedly influenced by pH. Periodic decrease in pH was observed during these studies. pH decreased up to 16th day of incubation from 5.5 to 2.2 in case of *A. Niger*, see Fig. 3. The equation for production of organic acids by *A. Niger* proceeds through the same mechanism of

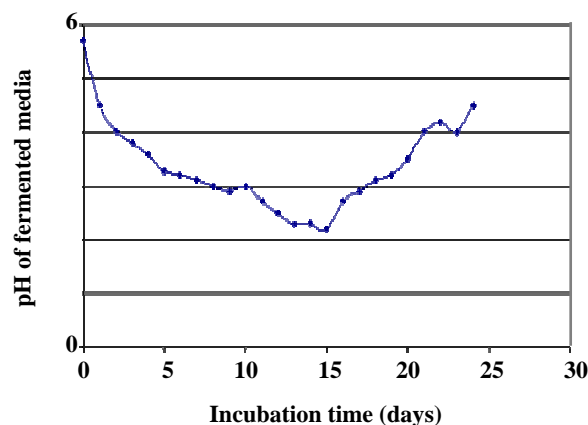


Fig. 3: pH profile glucose fermented media by *A. Niger*.

P. Simplicissimum. After maximum decrease of pH for about 15-16 days, increase in pH was observed (Figs. 2 and 3). This was due to the reason that after complete utilization of glucose, the fungi started to use its own metabolite.

The High results for the determination of organic acid concentration in fungal metabolite is shown in Figs. 4 and 5.

Bioleaching studies of red mud

pH progressively increased during bioleaching due to alumina solubilization and became maximum at 8 h. After 8 h, decrease in pH was observed. Such an effect can be justified that increase in pH results in the ability of metabolite to dissolve alumina. Thus after 8 h, no complexation reaction occurred between aluminum and organic acids, and protons of organic acid produced as result of acidolysis were free to cause decrease in pH after 8 h. *P. Simplicissimum* produced oxalic acid than citric acid.

It is proposed that reduced glucose flux through glycolysis cause of shift from citrate to oxalate accumulation. The reason for this shift remains unclear but is currently being studied. For the two strains employed, the alumina solubilization increased with time and reached at its maximum values after 8 h of shaking. The result of maximum alumina solubilization is consistent with pH change observed during bioleaching experiment.

The fungi are able to leach metals by acidolysis and complexation phenomena. Citric acid is a tricarboxylic acid and contains three carboxylic groups and one hydroxyl group as possible donor of protons (H^+) at 25 °C.

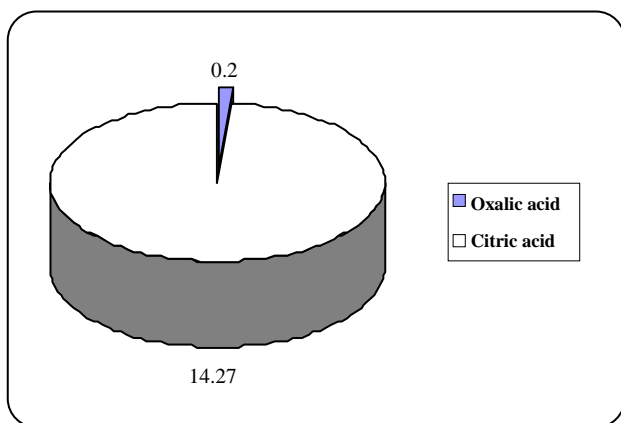


Fig. 4: HPLC analysis data for Organic acid characterization in metabolite of *A. Niger* (g/L).

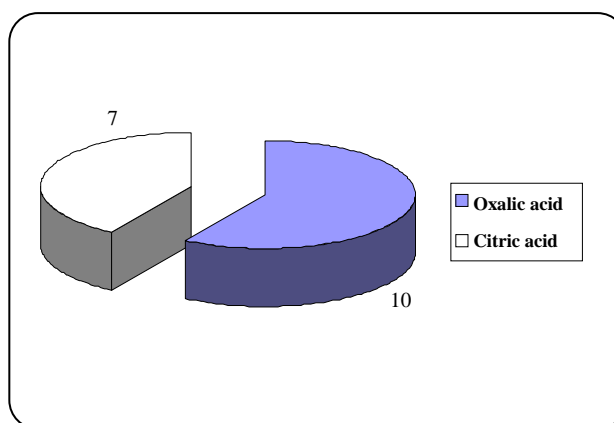


Fig. 5: HPLC analysis data for Organic acid characterization in metabolite of *P. Simplicissimum* (g/L).

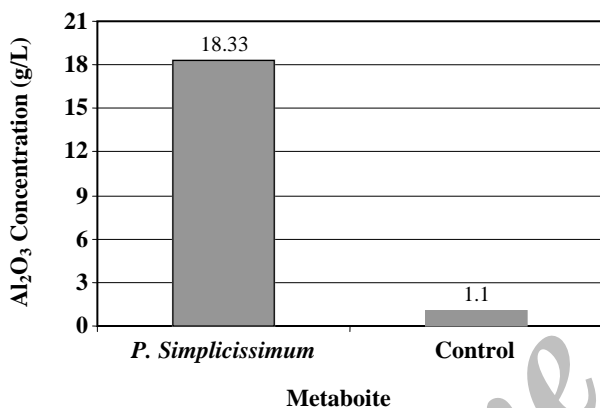


Fig. 6: Concentration of Al₂O₃ during bioleaching of red mud by *P. Simplicissimum* (g/L).


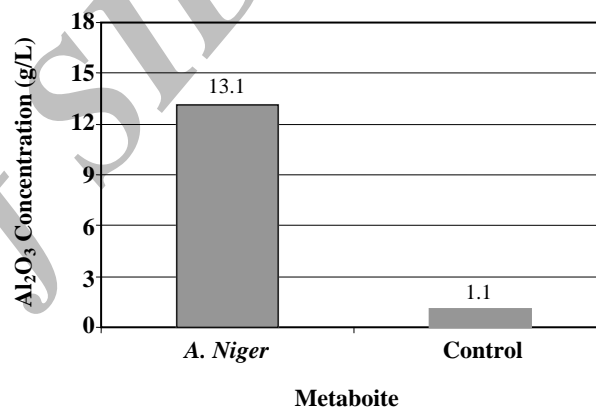



Fig. 7: Concentration of Al₂O₃ during bioleaching of red mud by *A. Niger* (g/L).

When aluminum cations (Al³⁺) are present in system and citric acid is fully dissociated in aqueous solution, a complexation reaction may take place can be formulated as Eqs. (3) and (4):




Aluminum citrate complex

Similarly oxalic acid contains two carboxylic groups (pK_{a1}=1.20 and pK_{a2}=4.20) at 25 °C. So the possible complexes of aluminum action with oxalate anion can be formulated as Eqs. (5) and (8):



Aluminum oxalate complex and



Citric and oxalic acids have proved to be good leaching agents for the alumina solubilization (Figs. 6 and 7).

The individual strain differences in the amount of alumina solubilization (g/L) were due to their variability caused by different environmental adaptations or difference in their typical properties. Among other elements analyzed by atomic absorption spectroscopic method are iron (Fe), titanium (Ti) and silicon (Si). Comparison of different fungal strains after 24 h of leaching and aluminum (Al) solubilization is presented in tables 2 to 5.

Table 2: Result of Aluminum dissolved in bioleaching of Red mud. Leaching Conditions: Weight of Red mud sample=5 g (5 % pulp density), Volume of metabolite=100 mL, Temperature=22-25 (room temperature), Leaching time= 24 hours (with shaking).

Strain	Organic acids (g/L)		Al ₂ O ₃ (g/L)			
	Citric acid	Oxalic acid	Common	Pry heating	Mixture with nitric acid	Mixture with choleric acid
<i>A. Niger</i>	14.27	0.2	13.1	13.44	2.15	19.17
<i>P. Simplicissimum</i>	10	7	18.33	13.95	7.21	20.82

Table 3: Result of Titanium dissolved in bioleaching of Red mud. Leaching Conditions: Weight of Red mud sample=5 g (5 % pulp density), Volume of metabolite=100 mL, Temperature=22-25 (room temperature), Leaching time= 24 hours (with shaking).

Strain	Organic acids (g/L)		TiO ₂ (g/L)			
	citric acid	Oxalic acid	Common	Pry heating	Mixture with nitric acid	Mixture with choleric acid
<i>A. Niger</i>	14.27	0.2	0.43	0.27	0.13	3.9
<i>P. Simplicissimum</i>	10	7	6.8	0.67	0.38	4.44

Table 4: Result of Silicon dissolved in bioleaching of Red mud. Leaching Conditions: Weight of Red mud sample=5 g (5 % pulp density), Volume of metabolite=100 mL, Temperature=22-25 (room temperature), Leaching time= 24 hours (with shaking).

Strain	Organic acids(g/L)		SiO ₂ (g/L)			
	Citric acid	Oxalic acid	Common	Pry heating	Mixture with nitric acid	Mixture with choleric acid
<i>A. Niger</i>	14.27	0.2	0.14	0.29	0.1	0.22
<i>P. Simplicissimum</i>	10	7	0.35	0.18	0.3	0.14

Table 5: Result of iron dissolved in bioleaching of Red mud. Leaching Conditions: Weight of Red mud sample=5 g (5 % pulp density), Volume of metabolite=100 mL, Temperature=22-25 (room temperature), Leaching time= 24 hours (with shaking).

Strain	Organic acids (g/L)		F ₂ O ₃ (g/L)			
	Citric acid	Oxalic acid	Common	Pry heating	Mixture with nitric acid	Mixture with choleric acid
<i>A. Niger</i>	14.27	0.2	1.25	0.38	0.09	12.69
<i>P. Simplicissimum</i>	10	7	5.93	0.99	0.4	19.74

CONCLUSIONS

The following major Conclusions could be made based on this study. The high concentration of aluminum (20.82 g of Al₂O₃ /l) was obtained in bioleaching with mixture choleric acid and fungi metabolites. Dissolution of titanium in bioleaching of red mud was about (4 g/L). The latter effect of pry heating is considered very important in conceitration and purification section, as iron

impedes the subsequent extraction of aluminum from the pregnant solution. Mixture choleric acid with fungi metabolites increases the aluminum solubilizationbut mixture nitrate acid with fungi metabolites decreases the aluminum solubilization.

Received : 11th September 2007 ; Accepted : 5th August 2008

REFERENCES

- [1] B., Joiret, S., Keddou, M., Nóvoa, X. R., Pérez, M. C. and Takenouti, H., Passivity of Iron in Red Mud's Water Solutions, *Electrochemical Acta*, **49** (17-18), p. 3039 (2004).
- [2] Yunus Çengelolu, Esengul Kir and Mustafa Ersöz, Recovery and Concentration of Al (III), Fe (III), Ti (IV), and Na (I) from Red Mud, *Journal of Colloid and Interface Science*, **244**, p. 342 (2001).
- [3] Josnamayee Pradhan, Yasobanta Das, Suren Dranath Das and Rarindra Singh Thakur, Adsorption of Phosphate from Aqueous Solution Using Activated Red Mud, *Journal of Colloid Interface Science*, **204**, p. 169 (1998).
- [4] Maria Th. Ochsenkuhn- Petropubu, Konstantions, S. Hatzily Beris, Leonidas, N. Mendrinos, Constantion E. Salmas, Pilot- Plant Investigation of the Leaching Process from the Recovery of Scandium from Red Mud, *Indy. Egg. Chew*, **41**, p. 5794 (2002).
- [5] Hulya Geno and Jens Christoin, Absorption of Arsenate from Water Using Neutralized Red Mud, *Journal of Colloid and Interface Science*, **264**, p. 327 (2003).
- [6] Tsakiridis, P.E., Agatzini-Leonardou, S., Oustadakis, P., Red Mud Addition in the Raw Material Production of Portland Cement Clinker, *Journal of Hazardous Material*, **116** (1-2), p. 103 (2004).
- [7] Nalini, J. and Sharama, D.K., Biohydrometallurgy for Nansulfidic Minerals, *Geomicrobiology Journal*, **21**, p. 135 (2004).
- [8] Vasan, S.S., Jayant, Modak, M., Natarajan, K.A., Some Recent Advances in the Bioprocess of Bauxite, *Int. J. Miner Process*, p. 173 (2001).
- [9] Kawatra, S.K. and Natarajan, K.K., Microbial Aspect of Mineral Beneficiation, Metal Extraction and Environmental Control, *Mineral Biotechnology*, p. 37 (2001).
- [10] Rezza, I., Salinas, E., Elorza, M., Sanz de Tosetti, M., Donati, E., Mechanism Involved in Bioleaching of an Aluminosilicate by Heterotrophic Microorganisms, *Journal of Process Biochemistry*, **36**, p. 495 (2004).
- [11] Amir, I., Sikander, A., Ikram, U., Qadeer, M. A., Time Course Profile of Citric Acid Fermentation by *Aspergillus Niger* and its Kinetic Relations, *Journal of Biological Sciences*, p. 760 (2004).