

# Batch Equilibrium and Kinetics Studies of Cd (II) Ion Removal from Aqueous Solution Using Porous Chitosan Hydrogel Beads

**Mohammad Beigi, Saeed; Babapoor, Aziz**

*Department of Chemical and Petroleum Engineering, Sharif University of Technology, Tehran, I.R. IRAN*

**Maghsodi, Vida\*<sup>+</sup>**

*Biochemical and Bioenvironmental Engineering Research Centre (BBRC), Sharif University of Technology, Tehran, I.R. IRAN*

**Mousavi, Sayyed Mohammad**

*Biotechnology Group, Chemical Engineering Department, Trbiat Modares University, Tehran, I.R. IRAN*

**Rajabi, Narges**

*Department of Chemical and Petroleum Engineering, Sharif University of Technology, Tehran, I.R. IRAN*

**ABSTRACT:** *In this study chitosan hydrogel beads with porosity ~ 0.86 and diameter ~  $2 \pm 0.07$  mm were prepared from 85 % deacetylated chitosan for removal of  $Cd^{2+}$  ions from aqueous solutions. Chitosan powder was dissolved into dilute acetic acid as solvent and formed into spherical beads using a phase inversion technique. The effect of temperature, initial concentration of  $Cd^{2+}$  ions, and the period of agitation were perused to achieve the best isotherm model. Freundlich model was better fitted than Langmuir model ( $R^2 > 0.99$  and  $R^2 > 0.93$  respectively, at pH of 6.3, and shaker speed of 200 rpm), the constants of Langmuir and Freundlich models were calculated, which  $R_L$  value and  $q_{max}$  (mg/g wet weight) at 30 °C, 40 °C, 50 °C showed maximum uptake capacity of 61.35 (mg/g wet weight) obtained at 30 °C. The calculated heat of adsorption was -8.69, -7.051, -5.513 kJ mol<sup>-1</sup> at 30, 40, 50 °C respectively which verified an exothermic process. Kinetic studies of the adsorption phenomena were conducted in a batch system by initial concentrations from 100 to 500 mgL<sup>-1</sup> until the equilibrium concentration  $C_e$  (mgL<sup>-1</sup>) was reached. First-order, and second-order kinetic models were used; the experimental data were in reliable compliance with second-order kinetic model with  $R^2$  value greater than 0.97. The rate constants of the kinetic models were also calculated and tabulated. To investigate the surface morphology of the chitosan beads before and after adsorption process, they were observed by the use of Scanning Electron Microscopy (SEM). The surface characterization of the beads in both cases showed metal ions binding toward the surface of porous chitosan beads. All of the experiments carried out at pH of 6.3 and agitation rate of 200 rpm, which were opted according to optimum status of previous researcher's reports*

**KEY WORDS:** *Chitosan, Hydrogel beads, Adsorption,  $Cd^{2+}$ , Kinetic.*

---

\* To whom correspondence should be addressed.

+ E-mail: maghsodi@sharif.edu

1021-9986/09/3/81

9/\$/2.90

## INTRODUCTION

Cadmium is one of the toxic heavy metal which is extremely used in industry, including electroplating and battery industries. The chronic toxicity of cadmium to human and its environmental concerns have been well documented. In the U.S., the safety level of cadmium in drinking water has been set at  $0.01 \text{ mgL}^{-1}$  [1]. So far, different methods have been used for the removal of trace heavy metals from aqueous solutions, such as ion exchange, reverse osmosis, adsorption, complexation and chemical precipitation [2]. Adsorption has been shown to be an economically feasible alternative method to remove pollutants from wastewater [3].

Chitosan is a partially deacetylated form of Chitin by thermo-chemical deacetylation in concentrated sodium hydroxide or enzymatic deacetylation. Chitin is a substance found naturally in the exoskeletons of insects, shells of crustaceans such as crab, shrimp, crawfish and fungal cell walls. Chitin and Chitosan, as biopolymers, are used in a wide range of fields such as biotechnology (enzyme immobilization), food and nutrition (emulsifying, thickening and stabilizing agent, packaging membrane, antioxidant and dietary supplement), water engineering (flocculent, metals chelating agents), and medical applications (artificial skins, drug-delivery systems, blood anticoagulant and recently in gene therapy too) [4].

Metal cations can be adsorbed by chelation on amine groups of chitosan in near neutral solutions [5]. The increasing demand for new and economic processes for the recovery of metal ions from industrial effluents has encouraged many research groups to investigate the possibility of using biomaterials like chitosan for metal uptake [6]. One of the key properties of chitosan is its ability to complex strongly with heavy metal ions, particularly with Hg, Cu, Cd, Zn, Pb, Ni, Cr, and so on, several proposed applications are in water purification for removing toxic metals by complexation [7]. Chitosan is just one of the most representative biopolymers, receiving considerable interest in recent years for heavy metals removal due to its excellent metal-binding capacities and its low cost. It has been reported that heavy metal ions could be effectively removed by chitosan hydrogel beads or flakes [3]. The maximum uptake capacity that is;  $q_{\text{max}}$  (mg/g dry), of  $\text{Cd}^{2+}$  by raw chitosan as adsorbent (flakes/beads) at pH 7 has been reported in range of 67.44 to 146.12 mg/g dry (Eric Guibal) [6].

The objective of this research was to focus on removal of cadmium ions from aqueous solutions using biomaterials like chitosan which has not been surveyed yet regarding to its kinetics and equilibrium. In this research, chitosan hydrogel beads were prepared using phase inversion technique. After analyzing the diameter, porosity and morphology of hydrogel beads; it was examined for adsorptive removal of  $\text{Cd}^{2+}$  in batch experiments. The effects of some effective parameters such as initial concentration of metal, temperature, and contact time on cadmium removal were also studied by isotherm curves and the best kinetic model and equilibrium system were chosen for the adsorption experiments.

## MATERIALS AND METHOD

### Materials

The powder of chitosan (CS) was purchased from Sigma Co.; Minimum 85 % deacetylated Chitosan from Crab Shells. Acetic acid (HAC), Sodium Hydroxide (NaOH), and Cadmium Sulphate Octahydrate ( $3\text{CdSO}_4 \cdot 8\text{H}_2\text{O}$ ), (min. 99 %), were supplied from MERK. All other reagents used in the experiments were of analytical grade.

### Chitosan Hydrogel Beads Preparation

According to former investigations by Zhao *et al.*, 2007 [8]; it was concluded that weight percentage of HAC solution, weight percentage of chitosan in CS-HAC solution, and NaOH concentration would affect the porosity of beads. Therefore HAC and NaOH solution concentration (3 % wt HAC, NaOH 1 N) were adapted similar to that study to obtain the hydrogel with high adsorptive characteristics. Weight percentage of chitosan in CS-HAC solution was also set at 3 % wt [8].

In order to prepare the hydrogel beads by the phase inversion technique, 1.5 g of chitosan powder was dissolved into 50 mL acetic acid solution (3 % wt); the chitosan-acetic acid solution was continuously stirred in  $50^\circ\text{C}$  for about 4 h to ensure that the suitable dissolution has occurred. Then, it was left for nearly 4 h, to approach ambient temperature. Viscous solution (CS-HAC) was dripped into a precipitation bath containing 200 mL of aqueous NaOH 1N, by a syringe, and stirred using a magnetic stirrer, which neutralized the acetic acid within the chitosan gel and therefore coagulated the chitosan to

spherical uniform gel beads. The falling down rate of drops controlled at approximately one drop per second with a fixed distance from needle to the surface of the NaOH solution. After a few moments, the hydrogel beads emerged and the solution became opaque. They were finally solidified; then the wet chitosan hydrogel beads were collected by vacuum filter and rinsed with distilled water extensively to remove any alkaline solution, and afterwards stored in distilled water for the future use [3,9,10].

### Batch Equilibrium Investigations

Cadmium Sulphate, Octahydrate ( $3\text{CdSO}_4 \cdot 8\text{H}_2\text{O}$ ) was used to make cadmium ion solution. 2.28 g of Cadmium Sulphate was dissolved in 1 L distilled water to make  $1000 \text{ mgL}^{-1}$  stock solution. By frequent dilution, predetermined initial concentrations, that is;  $100\text{-}500 \text{ mgL}^{-1}$  were prepared, afterwards 50 mL of aqueous solutions of Cadmium Sulphate in different concentrations were taken in 250 mL Erlenmeyer flasks, at pH of nearly 6.3, regarding the literatures, as it seemed to be an optimum pH considered. Acidic solutions have negative impact on chitosan beads by dissolving them. Also at alkaline mediums a trifle precipitation occurs, which results in experimental error. Since overcoming the problem of chitosan gel bead dissolution in low pH, as a bottleneck, was not the aim of this study the chosen pH 6.3 was considered suitable. 1g of chitosan gel beads, having water content of 92.8 percent, weighted and added to each flask. The flasks were agitated, at 200 rpm and  $30 \pm 1 \text{ }^\circ\text{C}$  for 50 h, in accordance with kinetic studies to ensure that the equilibrium state has reached. Gel beads, after equilibrium obtained, were separated by vacuum filtration and concentration of  $\text{Cd}^{2+}$  in the solution was measured with an atomic adsorption spectrophotometer (German, Model AAS 5EA). Other experiments were repeated at two different temperatures, that is;  $40 \text{ }^\circ\text{C}$  and  $50 \text{ }^\circ\text{C}$  in compliance with above mentioned procedure. The amount of  $\text{Cd}^{2+}$  adsorbed on the beads,  $q$  (mg/g wet weight), was calculated using the following relation:

$$q = \frac{V(C_0 - C)}{W_c} \quad (1)$$

Where  $V$  (l) is the volume of  $\text{Cd}^{2+}$  solutions,  $W_c$  (g) is the weight of the wet gel beads,  $C_0$  ( $\text{mg L}^{-1}$ ) is the

initial  $\text{Cd}^{2+}$  concentrations, and  $C$  ( $\text{mg/L}$ ) is the  $\text{Cd}^{2+}$  concentrations at definite time

### Chitosan Beads Characterization

Chitosan beads were characterized and presented a porosity of 0.86, with moisture content of 92.8% and an average diameter of  $2 \pm 0.07 \text{ mm}$ .

### Gel Beads Morphological Studies

The surface morphology of prepared dried chitosan hydrogel bead before and after metal binding (cadmium ion adsorption) was recorded by scanning electron microscopy (SEM) (JEOL, JXA-840A, Tokyo, Japan), as depicted in Fig. 1. For SEM observation, the porous beads were kept at  $-4 \text{ }^\circ\text{C}$  for a month; since quick dehumidification would have had a devastating impact on surface morphology due to fast evaporation. Samples were made ready for SEM by coating with a golden thin layer ( $200 \text{ }^\circ\text{A}$  thick.), and then attached to the support plates with special silver paste (see Fig. 1, Cd ion binding to chitosan surface with different magnitudes is presented in Fig. 1 (b), (c), (d), (e)).

## RESULTS AND DISCUSSION

### Effect of temperature on metal adsorption

As shown in Fig. 2, cadmium ion uptake capacity at  $30 \text{ }^\circ\text{C}$  among other temperatures has reached the highest value. It signifies that by increasing temperature the amount of adsorption capacity of cadmium ions decreases. The magnitude of the heat of adsorption can provide useful information concerning the nature of the surface and the adsorbed phase. It has been reported that the formation of coordination complexes between metal cations and amine ligands was exothermic [11]. Clausius-Clapeyron equation, equation (2), has been used to calculate the heat of adsorption ( $\Delta H_{\text{ads}}$ ) in the following form [11]:

$$\Delta H_{\text{ads}} = R \left[ \frac{d(\ln C_e)}{d\left(\frac{1}{T}\right)} \right] \quad (2)$$

Where  $R$  is the universal gas constant,  $C_e$  ( $\text{mg/L}$ ) is the equilibrium concentration at constant amount of adsorbed  $\text{Cd}^{2+}$  obtained from the adsorption experimental data at various temperatures.  $\Delta H_{\text{ads}}$  is calculated from the


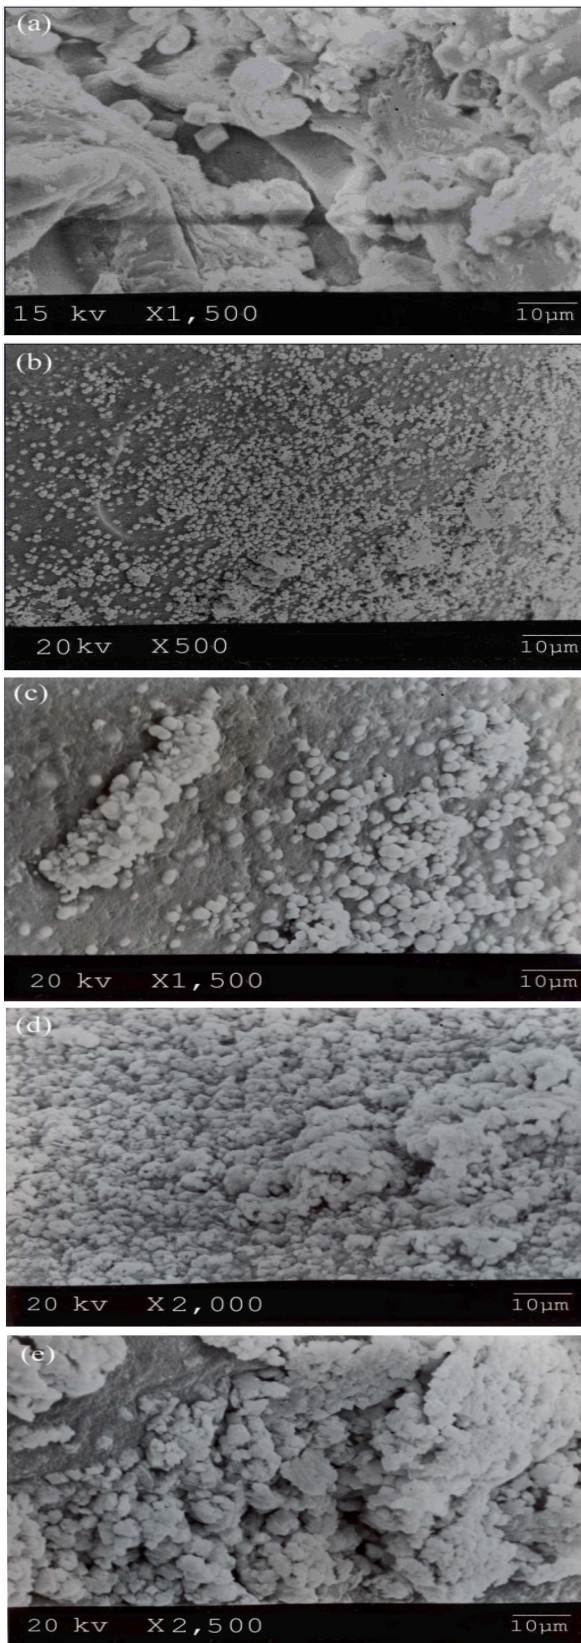


Fig. 1: SEM micrographs of Chitosan hydrogel beads×2500, after adsorption.

slope of the correlated straight line with  $R^2$  value 0.97 by drawing  $\ln(C_e)$  versus  $1/T$ , as shown in Fig. 3. The calculated heat of adsorption per one mol of  $Cd^{2+}$  was -8.69, -7.051, -5.513  $\text{kJ mol}^{-1}$  at 30, 40, 50 °C respectively. In previous studies by Trimukhe, it was recognized that presence of metal ions on the surface of chitosan can be detected with decrease in metal ion binding, in the following sequence [7]:



With respect to the reported heat of adsorption -12.3  $\text{kJ/mol}$  per one mol of mercury ion [11], and different metal ions binding sequence (as shown above) [7], it was seen that calculated heat of adsorption per one mol of  $Cd^{2+}$  ion (-7.051  $\text{kJ/mol}$ ) is a proper result.

#### Effect of Cd (II) Concentration on the amount of binding

Adsorption batch experiments were performed with different initial concentrations of metal ions (200, 300, 400, and 500  $\text{mg/L}$  at pH of 6.3), and sufficient time was given to achieve equilibrium concentrations. It is well known that by increasing the concentration of metal ions, the adsorbed amount increases (Fig. 4).

#### Adsorption Isotherms

The equilibrium relationships between adsorbent and adsorbate are described by adsorption isotherms, usually the ratio between the quantity adsorbed and that remaining in solution at a fixed temperature at equilibrium. There are basically two well established types of adsorption isotherms: Langmuir adsorption isotherm and Freundlich adsorption isotherm. The simplest theoretical model that can be used to describe monolayer adsorption is the Langmuir equation. The Langmuir isotherm model assumes a monolayer adsorption on a surface with a finite number of identical sites, which all sites are energetically equivalent and there is no interaction between adsorbed molecules [12]. This model is useful when there is a strong specific interaction between the surface and the adsorbate so that a single adsorbed layer is formed and no multi-layer adsorption occurs [13]. The Langmuir model is described by the following equation:

$$\frac{C_e}{q_e} = \frac{1}{K_L q_{\max}} + \frac{C_e}{q_{\max}} \quad (3)$$

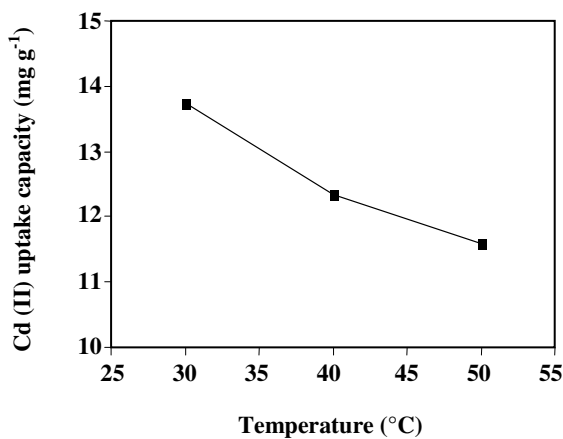


Fig. 2: Cd (II) adsorption capacity ( $q_e$ ) vs. Temperature ( $^{\circ}\text{C}$ ),  $C_0=500$  mg/l, pH 6.3, agitation rate=200 rpm, wet basis: one gram chitosan hydrogel bead.

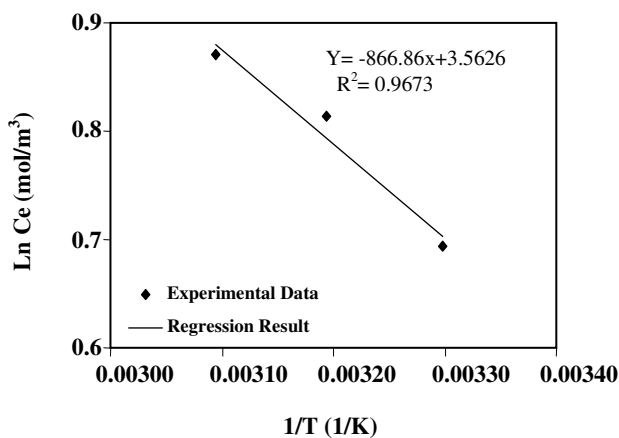


Fig. 3:  $\text{Ln}(C_e)$  versus  $1/T$  for Cd (II) adsorption on chitosan hydrogel bead in calculation of adsorption heat.

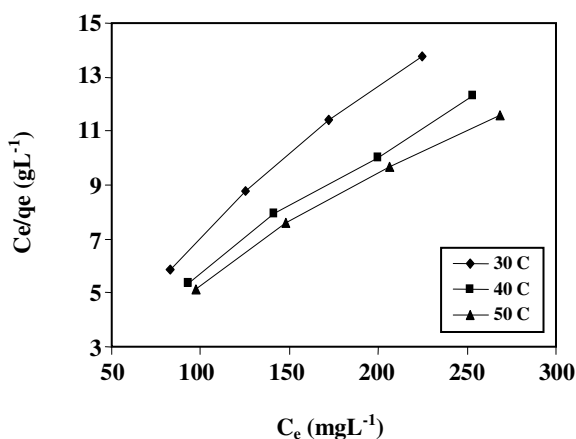


Fig. 4: Cd (II) adsorption capacity  $q_e$  (mg/g) vs.  $C_e$  (ppm).

Where  $C_e$  (mg/l) and  $q_e$  (mg/g) are the equilibrium concentrations in solution, and in adsorbed phase, respectively,  $q_{\max}$  (mg/g) is the maximum adsorption capacity, and  $K_L$  (l/mg) is the Langmuir binding constant which is related to the energy of adsorption [11].

The maximum adsorption capacity is determined by Plotting  $C_e/q_e$  versus  $C_e$  that yields a straight line with slope and intercept equal to  $1/q_{\max}$  and  $1/K_L q_{\max}$ , respectively (Fig. 6). The values of  $K_L$  and  $q_{\max}$  at several temperatures for adsorption of  $\text{Cd}^{2+}$  are presented in table 1. The Freundlich model is an empirical equation based on the distribution of solute between the solid phase and the aqueous phase at equilibrium. The Freundlich expression is an empirical equation based on adsorption on a heterogeneous surface [13]. The Freundlich model is expressed of the following form:

$$q_e = K_F C_e^{1/n} \quad (4)$$

where  $K_F$  is the equilibrium constant indicative of adsorption capacity (mg/g), and the larger the value of  $K_F$  the greater the adsorption capacity. 'n' is the adsorption equilibrium constant whose reciprocal ( $1/n$ ) is indicative of adsorption intensity. The reciprocal of 'n' is called heterogeneity factor and its value ranges from 0 to 1; the more the surface is heterogeneous, the value of  $1/n$  is closer to zero (see table 2).

The monitored  $R^2$  value at  $30^{\circ}\text{C}$  indicates that adsorption of  $\text{Cd}^{2+}$  is properly correlated with the Freundlich model (Fig. 5). It is also seen that as the temperature increases, the correspondence of adsorption of  $\text{Cd}^{2+}$  with Langmuir model increases (see  $R^2$  values in table 2). This may be attributed to the thermal rearrangement of active sites and  $\text{Cd}^{2+}$  ions to give a monolayer adsorption.  $R_L$  which is known as separation factor constant gives indication for the possibility of the adsorption process to proceed.  $R_L > 1.0$  unsuitable;  $R_L = 1$  linear;  $0 < R_L < 1$  suitable;  $R_L = 0$  irreversible. The value of  $R_L$  can be calculated from the following relation:

$$R_L = \frac{1}{1 + K_L C_0} \quad (5)$$

Where  $K_L$  (L/ mg) is the Langmuir equilibrium constant and  $C_0$  (mg/l) is the initial concentration of metal ion. The values of  $R_L$  lie between 0.56 and 0.79 indicating the suitability of the prepared chitosan hydrogel beads as adsorbent for cadmium ions from their

Table 1: Langmuir Constants.

T (°C)	q <sub>max</sub> (mg/g wet weight)	K <sub>L</sub> (L mg <sup>-1</sup> )	R <sup>2</sup>
30	61.35	0.00131	0.936
40	45.45	0.00138	0.950
50	39.84	0.00155	0.939

Table 2: Freundlich Constants.

T (°C)	K <sub>F</sub> (mg/g)	n	R <sup>2</sup>
30	0.138	1.171	0.995
40	0.135	1.225	0.995
50	0.131	1.242	0.992

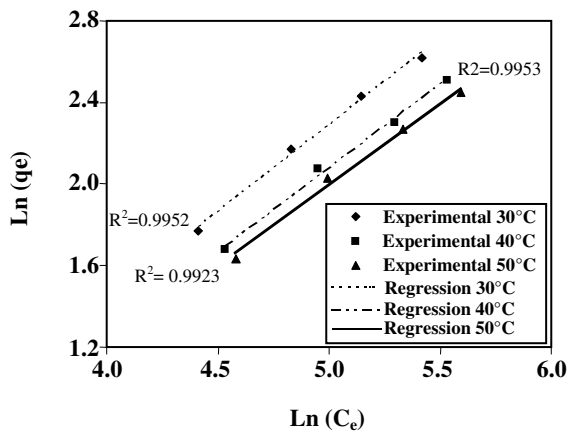


Fig. 5: Relationship of Ln (q<sub>e</sub>) and Ln (C<sub>e</sub>) in Freundlich isotherm in three different temperatures.

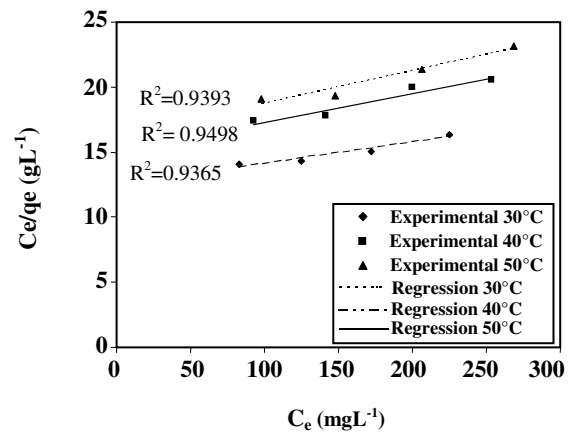


Fig. 6: Relationship of C<sub>e</sub>/q<sub>e</sub> and C<sub>e</sub> in Langmuir isotherm in three different temperatures.

aqueous solutions (table 3). The observed decrease in values of q<sub>max</sub> and at elevated temperatures indicates the exothermic nature of the adsorption process. The values of K<sub>L</sub> at different temperatures were used to calculate thermodynamic properties according to van't Hoff equation [14]:

$$\text{Ln}K_L = \frac{-\Delta H^0}{RT} + \frac{\Delta S^0}{R} \quad (6)$$

Where ΔH<sup>0</sup> (J mol<sup>-1</sup>) and ΔS<sup>0</sup> (J/mol K<sup>-1</sup>) are the enthalpy and entropy changes, respectively, R is the universal gas constant and T is the absolute temperature (K). Plotting Ln (K<sub>L</sub>) against 1/T gives a straight line with slope and intercept equal to ΔH<sup>0</sup>/R and ΔS<sup>0</sup>/R, respectively. The values of ΔH<sup>0</sup> and ΔS<sup>0</sup> were calculated from Fig. 7, and presented in table 4, the negative values of ΔH<sup>0</sup> show the exothermic nature of adsorption process. Gibbs free energy of adsorption (ΔG<sup>0</sup>) was calculated from the following relation:

$$\Delta G^0 = \Delta H^0 - T\Delta S^0 \quad (7)$$

The values of ΔG<sup>0</sup> at different temperatures were calculated and presented in table 4. The negative value

of ΔG<sup>0</sup> indicates that the adsorption reaction is spontaneous. The observed decrease in negative values of ΔG<sup>0</sup> with increasing temperature implies that the adsorption becomes less favourable at higher temperatures [14]. A minor change in the value of TΔS<sup>0</sup> at all temperatures and ΔH<sup>0</sup> > TΔS<sup>0</sup> indicate that the adsorption process is dominated by enthalpic rather than entropic changes.

### Kinetics Studies

The change in Cd<sup>2+</sup> concentrations in metal solutions via adsorption onto chitosan hydrogel beads in five different initial concentrations are depicted in Fig. 8. In order to examine the controlling mechanism of adsorption processes such as mass transfer and chemical reaction, the pseudo-first-order and pseudo-second-order kinetic models were used to check the experimental data. The pseudo-first-order kinetic model is given by equation (8):

$$\text{Ln}(q_e - q_t) = \text{Ln}(q_e) - k_1 t \quad (8)$$

Where q<sub>e</sub> and q<sub>t</sub> are the amounts of Cd ion adsorbed on adsorbent (mg/g) at equilibrium and at definite time t,

**Table 3:  $R_L$  Value at different temperature.**

T (°C)	$R_L$	Initial concentration $C_0$ (mg/l)
30	0.61	500
	0.66	400
	0.72	300
	0.79	200
40	0.59	500
	0.64	400
	0.71	300
	0.78	200
50	0.56	500
	0.62	400

**Table 4: Thermodynamic Properties.**

T (K)	$\Delta G^\circ$ (KJ/mol)	$\Delta H^\circ$ (kJ/mol)	$\Delta S^\circ$ (J/ molK <sup>-1</sup> )
303.15	-8.893	-6.878	6.646
313.15	-8.959		
323.15	-9.025		

**Table 5: Second-order kinetic model parameters for Cd (II) adsorption on chitosan beads.**

Initial concentration(ppm)	$k_2 \times 10^{-4}$ (g mg <sup>-1</sup> min <sup>-1</sup> )	$R^2$
100	7.69	0.998
200	5.19	0.997
300	1.46	0.990
400	0.50	0.973
500	2.94	0.998

**Table 6: First-order kinetic model parameters for Cd (II) adsorption on chitosan beads.**

Initial concentration(ppm)	$k_1 \times 10^{-4}$ (min <sup>-1</sup> )	$R^2$
100	2.13	0.795
200	1.33	0.610
300	3.17	0.904
400	3.62	0.932
500	1.35	0.539

respectively, and  $k_1$  is the rate constant of pseudo-first-order adsorption ( $h^{-1}$ ). The change in  $q_e$  at different contact times is also depicted in Fig. 9. With the increase of time, the amount of adsorbed Cd ion increased, and reached an equilibrium value after nearly 48 h (Fig. 9).

The straight-line plots of  $\ln(q_e - q_t)$  versus  $t$  were used to determine the rate constant,  $k_1$  ( $h^{-1}$ ) and regression coefficient value ( $R^2$ ) of the  $Cd^{2+}$  ion over different concentrations were calculated using these plots. The following pseudo-second-order equation was used as equation (9):

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \quad (9)$$

Where  $k_2$  is the rate constant of pseudo-second-order adsorption ( $g/mg \ h^{-1}$ ). The straight-line plots of  $t/q_t$  against  $t$  have been tested to obtain rate parameters and it suggests the applicability of this kinetic model to fit the experimental data. The validity of second order kinetic model was checked (Fig. 10) which showed a reliable agreement with second-order kinetic model. On the contrary, the first-order kinetic model poorly correlates the experimental data. The results of the kinetic parameters for  $Cd^{2+}$  ion adsorption are shown in table 5 and Table. 6. The pseudo- first-order kinetic model has been used for reversible reaction with an equilibrium being established between liquid and solid phases. Whereas, the second-order kinetic model assumes that the rate-limiting step may be chemical adsorption [3]. In many cases, the second-order equation correlates well to the adsorption studies [3, 9].

## CONCLUSIONS

The ability of biopolymers like chitosan for heavy metals adsorption is concluded via SEM analysis. The surface of dried chitosan bead, before adsorption, has large porous structures which are obviously seen by SEM. SEM studies indicated that Cd metal ion has a good complexation and binding to chitosan surfaces. The exothermic nature of adsorption process of heavy metal cations discloses that the optimum temperature occurs at 30 °C. The calculated maximum uptake capacity reach to 61.35 (mg/g wet weight) at 30 °C. The maximum uptake capacity has appropriate agreement with previous studies. Subsequent studies were focused on kinetic study and

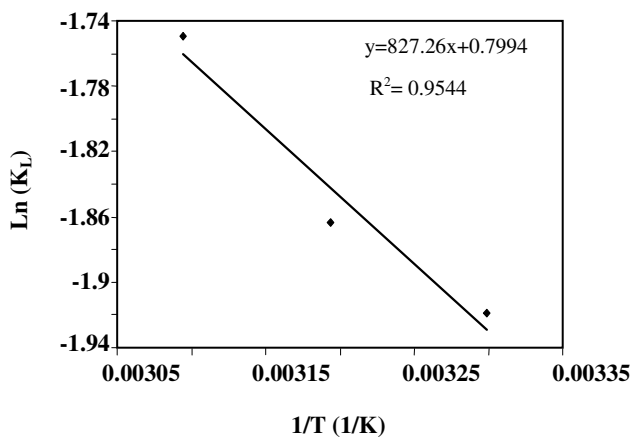


Fig. 7:  $\ln(K_L)$  vs.  $1/T$ .

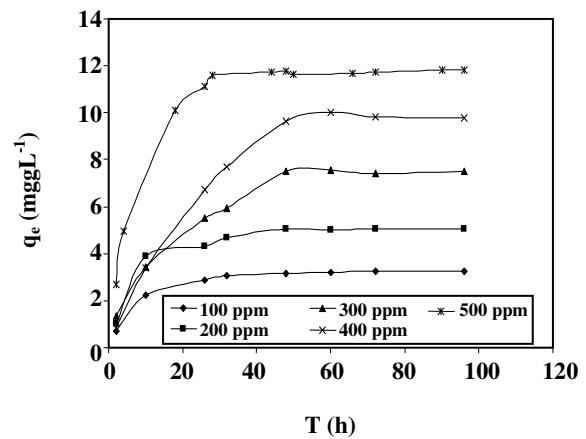


Fig. 9:  $Cd(II)$  adsorption capacity  $q_e$  vs. time.

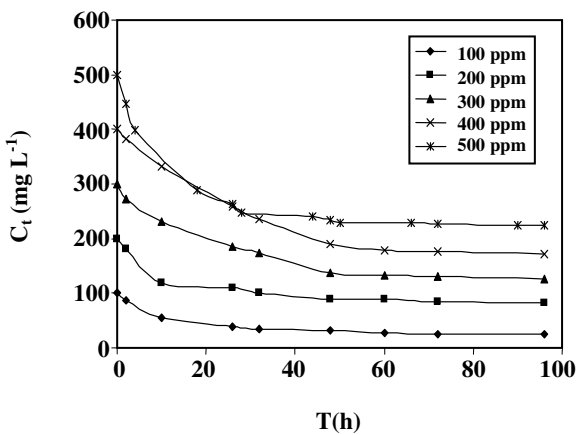


Fig. 8:  $Cd(II)$  concentration vs. time.

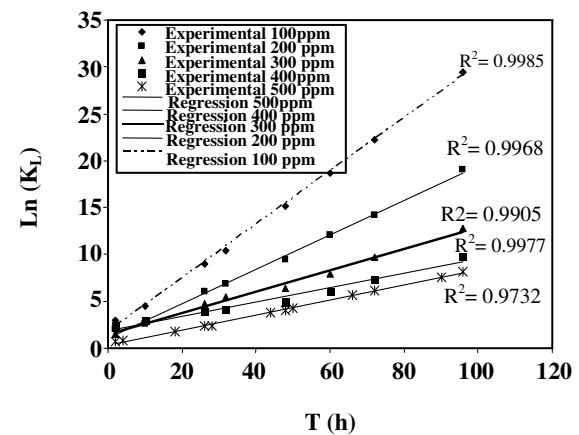


Fig. 10: The validity of second order kinetic model.

isotherm considerations of the  $Cd(II)$  ion uptake. The best kinetic model was pseudo-second-order model and Freundlich isotherm model was correlated with  $R^2$  value greater than 0.99.

**Acknowledgements**

The authors wish to acknowledge the technical support and assistance of BBRC staff, and Technology Development Institute, Materials Research Centre Division, Sharif University of Technology, Tehran, Iran.

**Nomenclatures**

- T Time(h)
- W Weight of chitosan hydrogel beads (g)
- C Concentration of  $Cd(II)$  solution (mg/L)
- $C_0$  Initial concentration of  $Cu(II)$  solution (mg/L)
- V Volume of the  $Cd(II)$  solution (L)

- R Universal gas constant ( $J/mol K^{-1}$ )
- $R^2$  Correlation coefficient (regression coefficient)
- T Temperature (K)
- $\Delta H_{ads}$  Heat of adsorption per one mol of metal ion ( $kJ mol^{-1}$ )
- q The amount of metal adsorbed on the beads ( $mg/g$  wet weight)
- $K_L$  Langmuir binding constant ( $l/mg$ )
- $q_{max}$  Maximum adsorption capacity ( $mg/g$ )
- $K_F$  Freundlich coefficient ( $mg/g$ )
- $\Delta H^\circ$  Enthalpy change ( $J/mol$ )
- $\Delta S^\circ$  Entropy change ( $J/mol K^{-1}$ )
- $\Delta G^\circ$  Gibbs free energy of adsorption ( $KJ/mol$ )
- $k_1$  Rate constant of pseudo-first-order kinetic model ( $h^{-1}$ ) or ( $min^{-1}$ )
- $k_2$  Rate constant of pseudo-second-order kinetic model ( $g/mg h^{-1}$ ) or ( $g/mg min^{-1}$ )



$R_L$	Dimensionless constant separation factor or equilibrium parameter
rpm	Round per minute
A	Angstrom
n	Freundlich adsorption Equilibrium constant

### Subscripts

e	Equilibrium
c	Chitosan gel bead
ads	Adsorption
F	Freundlich
L	Langmuir
t	Time

Received : 11<sup>th</sup> May 2008 ; Accepted : 10<sup>th</sup> March 2009

### REFERENCES

- [1] Yin, P., Yu, Q., Jin, B., Ling, Z., Biosorption Removal of Cadmium from Aqueous Solution by using Pretreated Fungal Biomass Cultured from Starch Wastewater, *J. Water Res.*, **33**, 1960 (1999).
- [2] Wan Ngah, W.S., Endud, C.S., Mayanar, R., Removal of Copper (II) Ions from Aqueous Solution onto Chitosan and Cross-Linked Chitosan Beads, *Reactive and Func. Polym.*, **50**, 181 (2002).
- [3] Wan Ngah, W.S., Ghani, S.A., Kamari, A., Adsorption Behavior of Fe (II) and Fe (III) Ions in Aqueous Solution on Chitosan and Cross-Linked Chitosan Beads, *Biores. Technol.*, **96**, 443 (2005).
- [4] Maghsoodi, V. et al., Influence of Different Nitrogen Sources on Amount of Chitosan Production by *Aspergillus niger* in Solid State Fermentation, *Iran. J. Chem. Chem. Eng.*, **27** (1), (2008).
- [5] Harish Prashanth, K.V., Tharanathan R.N., Chitin/Chitosan: Modifications and Their Unlimited Application Potential-an Overview, *Trends in Food Sci. & Technol.*, **17**, 1 (2006).
- [6] Guibal E., Interactions of Metal Ions with Chitosan-Based Sorbents: A Review, *Sep. and Purification Technol.*, **38**, 43 (2004).
- [7] Trimukhe, K.D., Varma, A.J., A Morphological Study of Heavy Metal Complexes of Chitosan and Crosslinked Chitosans by SEM and WAXRD, *Carbohydr. Polym.*, **62** (1), 57 (2005).
- [8] Zhao, F., Yu, B., Yue, Z., Wang, T., Wen, X., Liu, Z., Zhao, C., Preparation of Porous Chitosan Gel Beads for Copper (II) Ion Adsorption, *J. of Hazard. Mater.*, **147**, 67 (2007).
- [9] Wan Ngah, W.S., Kamari, A., Koay, Y.J., Equilibrium and Kinetics Studies of Adsorption of Copper (II) on Chitosan and Chitosan/PVA Beads, *Int. J. of Biol. Macromolecules*, **34**, 155 (2004).
- [10] Cestari, A.R., Vieira, E.F.S., Oliveira, I.A.D., Bruns R.E., The Removal of Cu (II) and Co (II) from Aqueous Solutions using Cross-Linked Chitosan-Evaluation by the Factorial Design Methodology, *Biotechnol. and Bioeng.*, **50**, 207 (1996).
- [11] Jeon, C., Park, K.H., Adsorption and Desorption Characteristics of Mercury (II) Ions using Aminated Chitosan Bead, *J. Water Res.*, **39**, 3938 (2005).
- [12] Baroni, P., Vieira, R.S., Meneghetti, E., Dasilva, M.G.C., Beppu, M.M., Evaluation of Batch Adsorption of Chromium Ions on Natural and Crosslinked Chitosan Membranes, *J. of Hazard. Mater.*, **152** (3), 1155 (2008).
- [13] Chilton, N.G., Losso, J.N., Marshall Wayne, E., Rao Ramu, M., Freundlich Adsorption Isotherms of Agricultural By-Product-Based Powdered Activated Carbons in a Geosmin-Water System, *Biores. Technol.*, **85**, 131 (2002).
- [14] Donia, A.M., Atia, A.A., Elwakeel, K.Z., Recovery of Gold (III) and Silver (I) on a Chemically Modified Chitosan with Magnetic Properties, *J. Hydrometallurgy*, **87**, 197 (2007).