

## RESEARCH PAPER

## Synthesis of Cobalt Oxide Nanoparticles Through Chemical and Biological Pathways for Antibacterial Activity

Abu Tollosa Adino, Gemechu Deressa Edosa, Bedasa Abdisa Gonfa, Eneyew Tilahun Bekele\* and Fedlu Kedir Sabir \*

Department of Applied Chemistry, School of Applied Natural Science, Adama Science and Technology University

### ARTICLE INFO

#### Article History:

Received 04 April 2021

Accepted 19 June 2021

Published 01 July 2021

#### Keywords:

Antibacterial activity

Biological method

Chemical method

Cobalt oxide nanoparticles

Phytolacca dodecandra

### ABSTRACT

Green synthesis of nanoparticles (NPs) using different parts of plant extracts is a novel and environmentally benign method that can be used in numerous biomedical applications. In this study, cobalt oxide nanoparticles were synthesized through biological method using 0.2 M cobalt nitrate hexahydrate as a precursor salt and leaf extract of indigenous plant of Ethiopia called Phytolacca dodecandra as a reducing and capping agent. In addition to this, cobalt oxide nanoparticles were synthesized chemically by co-precipitation method from cobalt nitrate hexahydrate in the presence of sodium hydroxide as a precipitating agent. The synthesized  $\text{Co}_3\text{O}_4$  NPs were characterized using X-Ray diffraction (XRD), scanning electron microscopy (SEM) coupled with energy dispersive spectroscopy (EDX), Ultraviolet-Diffuse Reflectance spectroscopy (UV-Vis-DRS) and Fourier transform infrared (FT-IR) spectroscopy. The average crystal size  $\text{Co}_3\text{O}_4$  NPs were found to be 10.79 nm and 11.9 nm, having band gap energy of 3.35 eV and 3.18 eV for the biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs, respectively. The shape and morphology of  $\text{Co}_3\text{O}_4$  NPs synthesized in the two methods were found to be spherical. XRD and FT-IR analyses have confirmed the formation of  $\text{Co}_3\text{O}_4$  NPs from its precursor salt in the presence of Phytolacca dodecandra leaf extract. The antibacterial activity of both the calcined and un-calcined biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs were found in the range of 8.3-12.5 mm. As compared to the chemically synthesized  $\text{Co}_3\text{O}_4$  NPs, biologically synthesized  $\text{Co}_3\text{O}_4$  NPs shows high antibacterial activity due to the production of high reduced reactive oxygen species (ROS) because of the presence of Phytolacca dodecandra leaf extract and due to the relatively small average crystalline size as compared to chemically synthesized  $\text{Co}_3\text{O}_4$  NPs.

### How to cite this article

Tollosa Adino A, Deressa Edosa G, Abdisa Gonfa B, Tilahun Bekele E and Kedir Sabir F. Synthesis of Cobalt Oxide Nanoparticles Through Chemical and Biological Pathways for Antibacterial Activity. J Nanostruct, 2021; 11(3):577-587. DOI: 110.22052/JNS.2021.03.015

### INTRODUCTION

Nowadays, the industries of water treatment, cosmetics, medicine, energy and pharmaceuticals have been using nanoparticles largely for their suitability and multi-functionalities [1]. Due to the

widespread applications of those different types of nanoparticles in different technologies and biotechnological aspects; currently the synthesis of different kinds of nanoparticles via different protocols became very essential [2]. Nanoparticles

\* Corresponding Author Email: [fedlu.kedir@astu.edu.et](mailto:fedlu.kedir@astu.edu.et)



This work is licensed under the Creative Commons Attribution 4.0 International License. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

with various compositions and applications can be prepared by physical, chemical and biological methods [3]. The physical synthesis methods include evaporation, sputtering, laser ablation, ion ejection and electron- beam lithography [4]. The chemical synthesis methods include salt reduction, reverse micelles, electrochemical, sol-gel, gas-liquid interface, thermolysis, co-precipitation and decomposition on ultrasonic treatment [5]. However, such mentioned methods involve the use of expensive and toxic chemicals as a capping agent, reducing agent, and as solvent during the synthesis process. Those synthesis protocols by themselves require high temperature, expensive and complicated instruments; and the method also involves the releasing of by products that affect the natural environment. Instead, green synthesis method is an environment-friendly approach to synthesize different types of nanoparticles for various applications. This method involves the use of biological available and cheap resources in nature such as extracts of green plants, algae, fungi, yeast, bacteria and viruses for the formation of stable nanoparticles for various novel applications [3].

Cobalt oxide is a transition metal oxide and has special characteristics such as high surface area: due to their small size; high magnetic behavior, and unique catalytic properties. It is widely used in industrial applications such as magnetic tape, chemical catalysis, gas sensing equipment, coating, and light absorbance as well as in medical biotechnology such as magnetic resonance imaging [6]. Cobalt Oxide nanoparticles have been using in wide range of applications from energy through water treatment to biomedical and as antimicrobial agent [6].

Nowadays, one of the global health concerns is the increasing antimicrobial resistance of many microorganisms against drugs, because some pathogens which were curable in past now are becoming untreatable such as Methicillin-resistant staphylococcus aureus (MRSA) [7]. To win this battle and to overcome this frightening situation of microbial resistance to antibiotics, using metal oxide nanoparticles synthesized via easily achievable cost with easy techniques are becoming as the best alternative options worldwide [8]. Cobalt oxide nanoparticles are one of the inorganic nano materials which can be used for such antimicrobial activities because of its interesting various physio-chemical properties [9].

Towards this end, cobalt oxide nanoparticles were synthesized via green method in the presence of the leaf extract of *Phytolacca dodecandra* as capping and reducing agent and chemical (coprecipitation) method; and then the nanoparticles synthesized in these two methods were evaluated against selected drug resistance human pathogen bacteria species of *Staphylococcus aureus* and *Escherichia coli* followed by comparing their antimicrobial potential applications.

Of course, synthesis of cobalt oxide nanoparticles through different methods for different potential applications has been already reported previously [10]. However, up to the knowledge of the authors of this study, synthesis of nanoparticles using the leaf extract of *Phytolacca dodecandra* as capping and reducing agent for antibacterial applications has not been reported before. In addition to this, cobalt oxide nanoparticles never synthesized via co-precipitation method and a comparative study of antibacterial never done yet. Therefore, the present study aims to synthesize cobalt oxide NPs in co-precipitation and green method using leaf extract of *Phytolacca dodecandra* and studying its application for antibacterial activity; comparing the efficiency of the synthesized cobalt oxide NPs prepared using these two methods on both gram negative and gram-positive bacteria strains.

## MATERIALS AND METHODS

### Chemicals

Chemicals, reagents, and solvents used during this work includes distilled water, absolute ethanol (99.9%, LabTech Chemicals), ethanol reagent (97%, LabTech Chemicals), Cobalt nitrate hexahydrate (98%, Sigma Aldrich), acetone (Sigma Aldrich), Dimethyl sulfoxide (DMSO, Sigma Aldrich) and Müller-Hinton agar (Sigma Aldrich). All these chemicals and reagents are of analytical grades and as a result were used without performing any further purification. Instruments Used

Different instruments such as FT-IR spectrophotometer (PerkinElmer 65), XRD (XRD-7000, Shimadzu Co., South Korea), UV-Vis spectrophotometer (JASCO V-78 UV-Vis spectrophotometer equipped with a diffuse reflectance attachment for powder samples), field emission scanning electron microscopy-SEM-EDX (FESEM, JEOL-JSM 804081F, Japan) were used for characterizing of functional groups, crystallinity nature, optical property, surface morphology and elemental analysis of green and chemically

synthesized  $\text{Co}_3\text{O}_4$  NPs, respectively.

#### *Leaf Collection and Extraction (Broth Solution Preparation)*

The leaves of *Phytolacca dodecandra* were collected from Digelu and Tijo district in Arsi Zone, Oromia Regional State, Ethiopia. The collected leaves of *Phytolacca dodecandra* were thoroughly washed with distilled water to remove the unwanted impurities such as dust and other particulates followed by drying under shaded at room temperature to remove all residual moisture content. The dried leaves of *Phytolacca dodecandra* were grinded using plant grinding machine followed by packing the powder within a plastic bottle. Extraction of the leaves was done by mixing 16 grams of powder of *Phytolacca dodecandra* and 250 mL of distilled water in a 500 mL Erlenmeyer flask.

The Erlenmeyer flask containing the mixture was placed on to a hot plate with magnetic stirrer and boiled at  $80^\circ\text{C}$  for about 35 minutes. Then the boiled suspension was allowed to cool for about 35 minutes and was filtered using Whatman number one filter paper. The extracted solution of *Phytolacca dodecandra* leaves was stored in a refrigerator at  $4^\circ\text{C}$  for the biosynthesis of  $\text{Co}_3\text{O}_4$  nanoparticles [11]. Fig.1 shows picture of *Phytolacca dodecandra* plant.

#### *Biosynthesis of $\text{Co}_3\text{O}_4$ Nanoparticles*

The solutions of leave extracts of *Phytolacca dodecandra* prepared in section 2.3 and that of cobalt nitrate hexahydrate [ $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ], were used for synthesis of  $\text{Co}_3\text{O}_4$  nanoparticles. So, to compare the antibacterial activities of  $\text{Co}_3\text{O}_4$  nanoparticles prepared in the two methods, synthesis of  $\text{Co}_3\text{O}_4$  NPs was done through chemical and green method in the presence of the leaf extract of *Phytolacca dodecandra*. For synthesis, 0.2 M solutions of  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  was mixed with the leave extract of *Phytolacca dodecandra*. The resulting solution of *Phytolacca dodecandra* and  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  were left under stirring for about 1 hour and then the pH values of the solution were monitored using a pH meter. Then to the solution mixture, 2.0 M sodium hydroxide solution was added in dropwise manner to facilitate the formation of precipitation. The resulting suspension in the solution flask was precipitated with help of centrifugation at 1000 rpm for 15 minutes and followed by washing with distilled

water and absolute ethanol sequentially. The formed  $\text{Co}_3\text{O}_4$  NPs were collected using a crucible dish and then were dried using drying oven for 5 hours at  $80^\circ\text{C}$ . The particles were store in an air tight container for further analysis and characterization [12].

#### *Synthesis of $\text{Co}_3\text{O}_4$ NPs Using Co-precipitation Method*

Cobalt oxide nanoparticles were synthesized without the addition of any capping/stabilizing agents through co-precipitation method using  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  in the presence sodium hydroxide as a precipitating agent. For this procedure 2.0 M of NaOH was taken and added step wise into a solution of 200 mL of 1.0 M  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  precursor under constant magnetic stirring for about 2 hours at room temperature. Then the pH value of the resulting suspension was monitored using a pH meter. The suspension was left overnight at room temperature. Then after the formed precipitate of hydroxide was settled down with the excess and clear solution found on top. The clear solution was discarded very carefully from the formed precipitate. The formed precipitate was then separated from the rest of solution by centrifugation at 1000 rpm for 15 minutes three times separately. The black color  $\text{Co}_3\text{O}_4$  precipitate was washed with distilled water followed by absolute ethanol repeatedly and then the precipitate was collected using crucible ceramic dish, and dried in oven at temperature at  $80^\circ\text{C}$  for about 5 hours [13].

#### *Characterization of Synthesized $\text{Co}_3\text{O}_4$ NPs*

The crystalline structure of the synthesized  $\text{Co}_3\text{O}_4$  nanoparticles was analyzed using X-ray diffraction measured by X-ray diffractometer (XRD-7000, Shimadzu Co., South Korea). The average crystalline size of the synthesized  $\text{Co}_3\text{O}_4$  nanoparticles were calculated from XRD data. The morphology and shape of the synthesized cobalt oxide NPs was confirmed using scanning electron microscopy coupled with energy dispersive X-ray spectroscopy (SEM-EDX) (Carl Zeiss Model: Neon-40, FESEM/FIB, SMT, AG, Germany). Optical band gap of the synthesized  $\text{Co}_3\text{O}_4$  NPs were characterized using UV-Vis-Diffuse Reflectance Spectrophotometer (Elico SL-150 spectrophotometer, UV-Vis spectrophotometer equipped with a diffuse reflectance attachment for powder samples). Information about the

functional groups was obtained by characterizing both green and chemically synthesized NPs using FTIR techniques (Perkin Elmer65, PerkinElmer, Inc., Waltham, USA).

#### Antibacterial Activity Studies

##### Preparation of Inoculum

First 2.5 mg nutrient broth was taken followed by dissolving it within 100 mL of distilled water and then was prepared within two conical flasks and sterilized. In one conical flask clinically isolated strain of *Staphylococcus aureus*, was inoculated. In the other conical flask clinically isolated strain of *Escherichia coli* was added. These bacterial cultures were inoculated in nutrient broth and were kept on rotary shaker for about 24 hours at 100 rpm [14].

##### Disc diffusion method

Antibacterial tests were carried out by disc diffusion method using the suspension of bacteria spread on nutrient agar followed the modified method [15]. Then the swab was dipped into the broth culture of the bacteria. The swab was gently squeezed against the inside of the tube to remove excess fluid. The swab was used to streak agar plate or a nutrient agar plate for a lawn of growth. This was best accomplished by streaking the plate in one direction then streaking at right angles to

the first streaking and finally streaking diagonally. After that the swab was used to streak the outside diameter of the agar. The inoculated plates were incubated at 37 for 24 hours. Antibiotic discs were placed on the surface of the agar using a dispenser that dispenses multiple discs at the correct distance apart or by obtaining individual discs and placing them on the surface of the agar using flame sterilized forceps. Then the antimicrobial activity was evaluated by measuring the diameter of zone of inhibition against the tested bacteria of *Staphylococcus aureus* and *Escherichia coli* and was measured using a ruler and calipers [15].

## RESULTS AND DISCUSSION

### X-Ray Diffraction (XRD) Analysis

Fig.2 shows the XRD pattern of  $\text{Co}_3\text{O}_4$  NPs biosynthesized from cobalt nitrate hexahydrate precursor salt and *Phytolacca dodecandra* leaf extracts (through biological method) and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs obtaining (co-precipitation method). Effects of calcination on  $\text{Co}_3\text{O}_4$  NPs were manifested by XRD patterns between Fig.2 A and Fig.2 B. The sharp and intense peaks of XRD in Fig.2A demonstrated that calcined samples were highly crystalline for both  $\text{Co}_3\text{O}_4$  NPs synthesized in green and chemical methods. The XRD patterns labeled by (a) and b) in Fig.2B



Fig. 1. Photo of the plant *Phytolacca dodecandra*.



shows that  $\text{Co}_3\text{O}_4$  NPs were less crystalline (both for chemically and green methods of synthesis) in uncalcined samples.

The peaks observed at  $2\theta$  values of 19, 31.22, 37, 44.9, 59.22 and 65.18 for biologically for and 18.90, 31.26, 36.78, 45.02, 59.50, and 65.26 for chemically synthesized  $\text{Co}_3\text{O}_4$  NPs, respectively along with miller indices values of (111), (220), (311), (222), (400) and (422). The average crystalline size of biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs were found to be 10.79 nm and 11.9 nm, respectively. Sharp diffraction peaks were observed in chemically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles whereas the intensity of diffraction peaks of biologically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles is less with slight broadening. Those results reveal that biosynthesized  $\text{Co}_3\text{O}_4$  NPs have possessed good crystallinity in nature and also diffraction peaks related to impurities were not observed in the green synthesized XRD pattern of  $\text{Co}_3\text{O}_4$  NPs; confirming the high purity of the biosynthesized nanomaterials. Thus, broadening of XRD peak of biologically synthesized  $\text{Co}_3\text{O}_4$  NPs observed in the present study confirms the size reduction; due to the presence of *Phytolacca dodecandra* leaf extract that plays great role as both capping and reducing agent and thus prevents  $\text{Co}_3\text{O}_4$  NPs over growth formation. As it can be observed, the XRD peak of chemically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles is sharp, this indicating that their size is still larger than the biologically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles. As it can be revealed under the XRD spectra, chemically synthesized  $\text{Co}_3\text{O}_4$  NPs are free of impurities as no

additional and foreign peaks are not observed like that of green mediated synthesized  $\text{Co}_3\text{O}_4$  NPs. As compared to the green calcined  $\text{Co}_3\text{O}_4$  NPs, uncalcined green synthesized  $\text{Co}_3\text{O}_4$  NPs shows vibrations due to the existence of some bioactive molecules from the leaf extract of *Phytolacca dodecandra*.

#### SEM-EDX Analysis

The morphology and the chemical composition of both biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles were viewed through the high-resolution field emission scanning electron microscopy (SEM) coupled with energy dispersive spectroscopy (EDX). Fig. 3(a) and (b) shows the SEM images of biologically and chemically synthesized cobalt oxide nanoparticles, respectively. The SEM image (Fig.3) and SEM-EDS (Fig.4) reveal that shape and morphology of  $\text{Co}_3\text{O}_4$  nanoparticles were found to be spherical in shape. The image also elucidates the decrease of particle size for the biologically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles as compared to the chemically synthesized  $\text{Co}_3\text{O}_4$  NPs ; implies the well association of biomolecules obtained from the leave extract with that of  $\text{Co}_3\text{O}_4$  precursor salt during the biosynthesis process and the presence of the leaves extract coats the surface of  $\text{Co}_3\text{O}_4$  NPs, thus preventing from aggregation and agglomeration and so results in a relatively homogenized morphonology.

The energy dispersive X-ray analysis of biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs was shown in Fig. 4. It is evident from the X-ray patterns of all the samples in which Co and O are

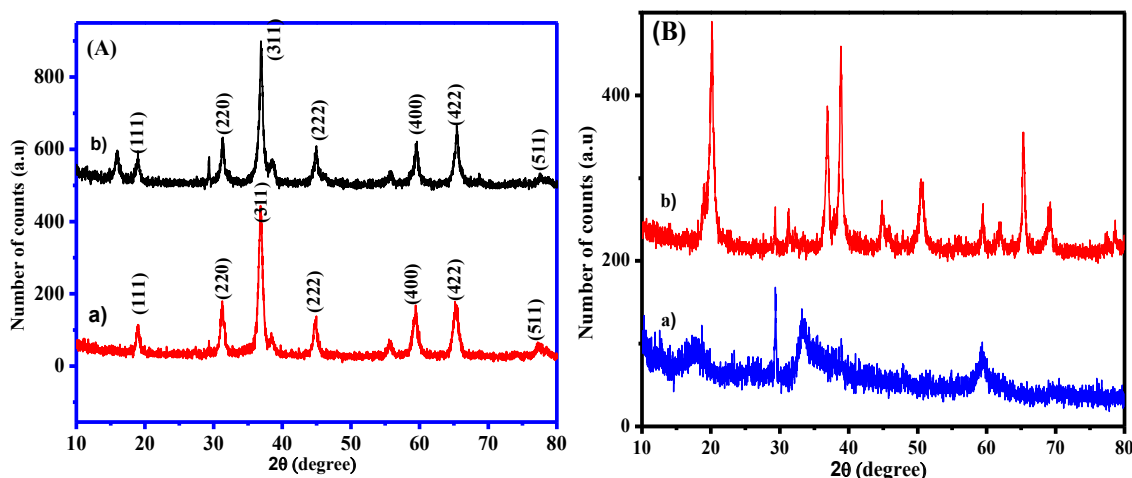


Fig. 2. XRD pattern of (A) calcined  $\text{Co}_3\text{O}_4$  NPs synthesized in a) chemical and b) green method; and (B), XRD pattern of uncalcined  $\text{Co}_3\text{O}_4$  NPs synthesized in a) green and b) chemically method.

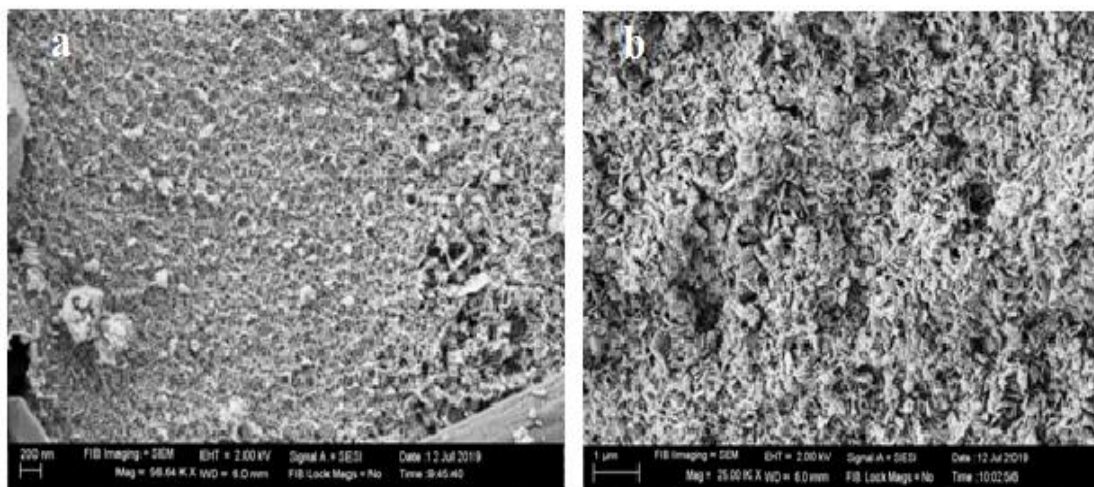


Fig. 3. SEM images of (a) biologically and (b) chemically synthesized  $\text{Co}_3\text{O}_4$  NPs.

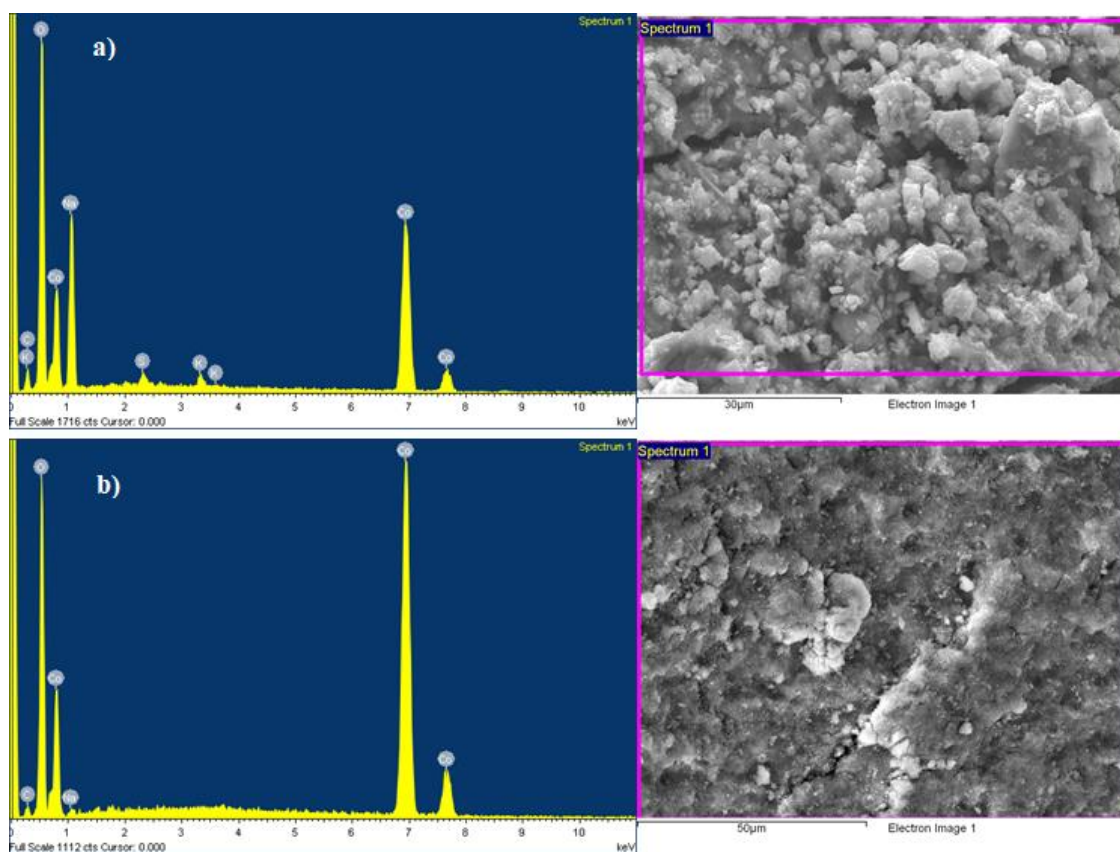


Fig. 4. SEM-EDS spectra of (a) biologically and (b) chemically synthesized  $\text{Co}_3\text{O}_4$  NPs.

found in the respective spectra. In addition to this, energy dispersive X-ray spectroscopy analysis showed the composition of  $\text{Co}_3\text{O}_4$  NPs contains only the element Co and O atom; this reveals that the synthesized  $\text{Co}_3\text{O}_4$  NPs obtained using the two

methods are free from any impurities and foreign materials. Some extra elements such as C, S, and K are observed under the EDX images of  $\text{Co}_3\text{O}_4$  NPs, which could be comes from ceramic materials during the preparation of paste for SEM-EDX

characterization, and also the existence of C like materials will be obtained from the decomposition and reaction of atmospheric carbon dioxide and in another way it might be from few remnants of leaf extract of *Phytolacca dodecandra* used during synthesis process as supported by related previously reported works [16, 17]. EDX also shows that biologically synthesized  $\text{Co}_3\text{O}_4$  NPs has a good crystallinity nature as compared to chemically synthesized  $\text{Co}_3\text{O}_4$  NPs. The absence of any foreign material other than the required synthesized  $\text{Co}_3\text{O}_4$  NPs indicates that the synthesized  $\text{Co}_3\text{O}_4$  NPs are highly pure.

*Ultraviolet-Visible Diffuse Reflectance Spectroscopy (UV-Vis DRS) Analysis*

The optical behavior of the synthesized  $\text{Co}_3\text{O}_4$  nanoparticles was investigated by using ultra violet visible diffuse reflectance spectroscopy (UV-Vis DRS). Fig. 5 displays the Tauc plots of both green and chemically synthesized cobalt oxide nanoparticles extracted from the corresponding UV-Vis DRS datas. Energy bandgaps of  $\text{Co}_3\text{O}_4$  NPs synthesized in these two different methods were determined from Tauc plot using Kubelka-Munk functions. The bandgap energies of  $\text{Co}_3\text{O}_4$  NPs were found to be 3.35 eV and 3.18 eV, respectively for the biologically and chemically synthesized

$\text{Co}_3\text{O}_4$  NPs.

Cobalt oxide nanoparticles synthesized by chemical method possess high band gap energy as compared to green synthesized  $\text{Co}_3\text{O}_4$  NPs this is due to quantum confinement difference between nanoparticles synthesized in biological and chemical precipitation methods. Higher bandgap nanoparticles (synthesized in chemical method) possess high quantum confinement than lower bandgap-nanoparticles (synthesized in biological method). Therefore, as it can be studied in the present work, if the average size of the particles is very small, light interacts with the samples instead of absorption with parts of the light scattered and reflected back [17, 18].

*Fourier Transform Infrared (FT-IR) Analysis*

FTIR spectral analysis of both the biosynthesized and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs are shown in Fig. 6. The functional groups of the molecules in the plant extract that are responsible for capping and stabilizing of nanoparticles were confirmed by major bands at 3636, 3423, 1634 and 1055  $\text{cm}^{-1}$  in the FT-IR spectrum. The two intense bands appeared at 3635 and 1055  $\text{cm}^{-1}$  have been assigned to the stretching and binding vibrations of hydroxyl group of phenolic compound found in uncalcined  $\text{Co}_3\text{O}_4$  NPs that is emanated from the

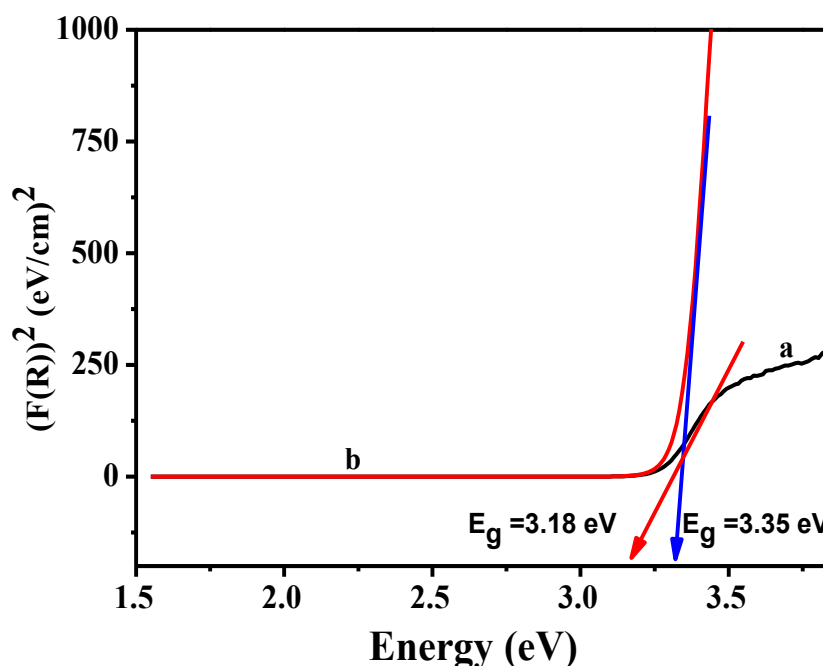


Fig. 5. Tauc plots of a) chemically and b) green (biologically) synthesized  $\text{Co}_3\text{O}_4$  NPs and their calculated bandgaps.

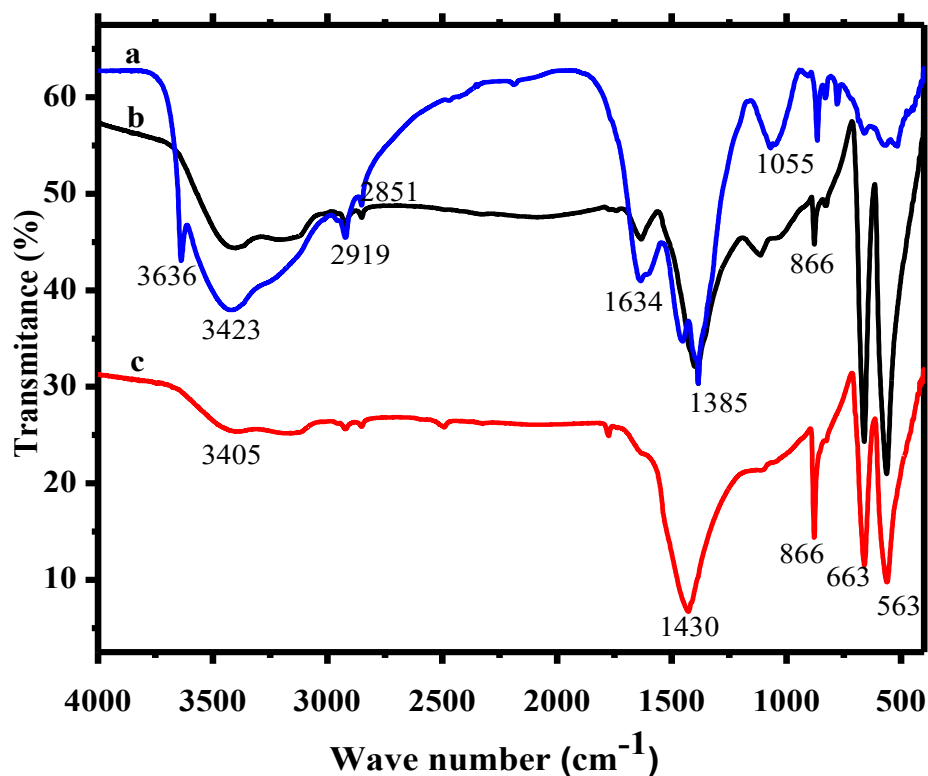


Fig. 6. (a) Uncalcinated, (b) calcinated and (c) chemically synthesized FT-IR spectra of  $\text{Co}_3\text{O}_4$  nanoparticles.

plant extract (Fig. 6a); and broad bands appeared at  $3405\text{ cm}^{-1}$  was assigned to O-H stretching vibration mode emanated from moistures adsorbed on the surface of calcined  $\text{Co}_3\text{O}_4$  NPs. The major bands at  $1634\text{ cm}^{-1}$ ,  $1055\text{ cm}^{-1}$  and  $563\text{ cm}^{-1}$  (in curve a) can be attributed to the carbonyl functional groups, amides and  $\text{Co}_3\text{O}_4$  NPs respectively in the uncalcinated sample [19, 20].

The broad and intense absorption band located at  $1385\text{ cm}^{-1}$  (in Fig. 6a and 6b) and at  $1430\text{ cm}^{-1}$  (in Fig. 6c) confirms the presence of carbonyl functional groups emanated from the leaf extract of *Phytolacca dodecandra* and  $\text{CO}_2$  gas molecules adsorbed on  $\text{Co}_3\text{O}_4$  NPs respectively [15, 19]. Fig. 6 (a), Fig. 6(b) and Fig. 6(c) shows the FT-IR spectra of uncalcinated biosynthesized, calcined biosynthesized and chemically synthesized  $\text{Co}_3\text{O}_4$  NPs respectively. The strong bands at  $563$  and  $663\text{ cm}^{-1}$  belonging to cobalt-oxygen bond stretching vibration that confirms formation of  $\text{Co}_3\text{O}_4$  nanostructure [21-24]. Disappearance of bands at  $3636\text{ cm}^{-1}$ ,  $2919$ ,  $2851\text{ cm}^{-1}$ ,  $1634\text{ cm}^{-1}$  and  $1055\text{ cm}^{-1}$  in the case of calcined  $\text{Co}_3\text{O}_4$  NPs (Fig. 6b) and in chemically synthesized  $\text{Co}_3\text{O}_4$  NPs confirms removal of organic compounds after calcination

[15].

#### Antibacterial studies of $\text{Co}_3\text{O}_4$ NPs

The antibacterial activity of the synthesized  $\text{Co}_3\text{O}_4$  nanoparticles was investigated against both gram negative and gram- positive bacteria strains using disc diffusion method. To analyze the effect of nanoparticles concentration on antibacterial activity,  $25\mu\text{g/mL}$  and  $50\mu\text{g/mL}$  of biologically and chemically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles were prepared and tested against *Escherichia coli* and *Staphylococcus aureus* bacteria strains. The antibacterial activity of  $\text{Co}_3\text{O}_4$  nanoparticles was compared with the positive control ciprofloxacin; the results of antibacterial studies clearly suggests that,  $\text{Co}_3\text{O}_4$  nanoparticles synthesized through biological method shows better antibacterial activity as compared to chemically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles, even at low concentration with concentration of  $25\mu\text{g/mL}$ . This is due to the fact that, in biologically synthesized  $\text{Co}_3\text{O}_4$  nanoparticles, the production of reactive oxygen species (ROS) is high to inhibit or kill the bacteria due to the presence phytochemicals emanated from *Phytolacca dodecandra* [25]; and also due



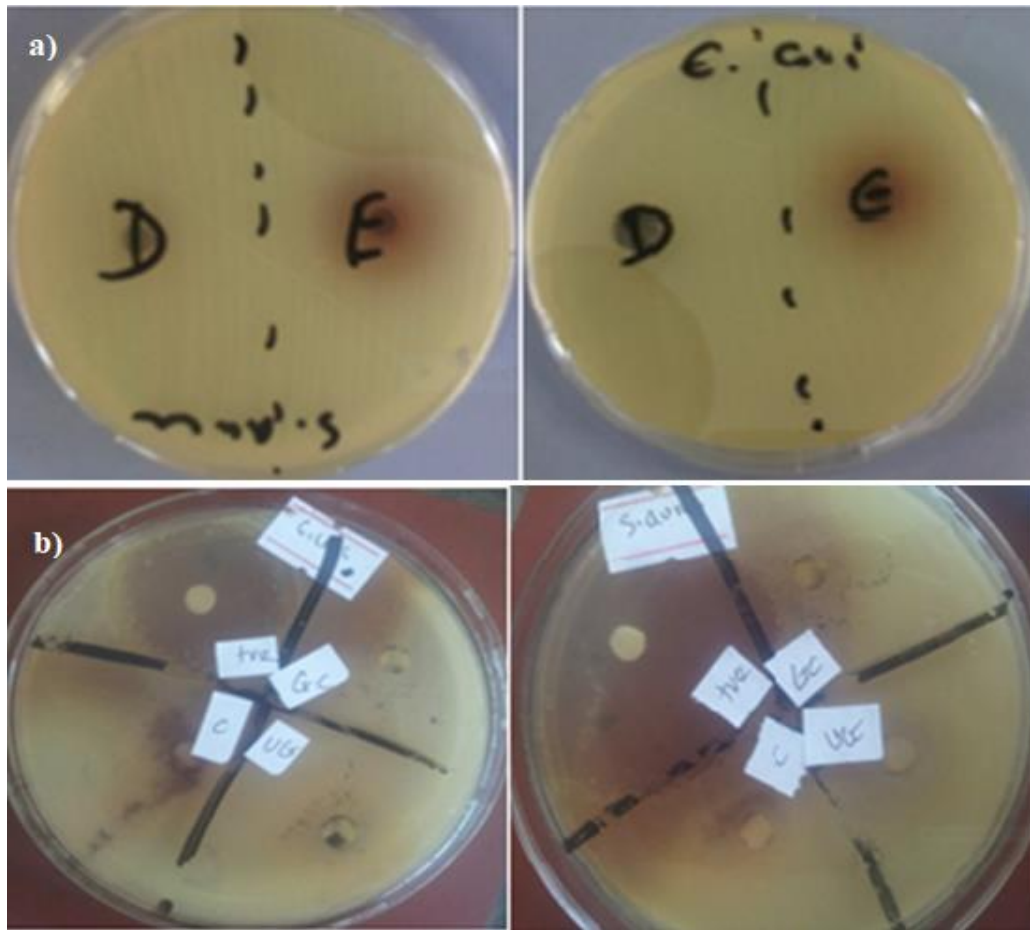


Fig. 7. Antibacterial activity of  $\text{Co}_3\text{O}_4$  NPs a) at concentration of  $25 \mu\text{g/mL}$  for chemically synthesized (D) and biologically synthesized (E); b) at  $50 \mu\text{g/mL}$  concentration for biologically (GC & UG) and chemically synthesized.

Table 1. Zone of inhibition (mm) of biologically (E) and chemically (D) synthesized  $\text{Co}_3\text{O}_4$  NPs using  $25\mu\text{g/ml}$ .

S.No	Bacteria	Concentration	+ve control	Green	Chemical
		$25\mu\text{g/ml}$	ciprofloxacin	(E)	(D)
1	<i>E.coli</i>		14.5	10.5	8.8
2	<i>S.aureus</i>		14	8.3	8.11

Table 2. Zone of inhibition (mm) of biologically (GC & UG) and chemically (C) synthesized Co<sub>3</sub>O<sub>4</sub> NPs using 50 µg/mL

S.No	Bacteria	Concentration	+ve control	Green		Chemical
		50 µg/ml	ciprofloxacin	GC	UG	C
1	<i>E.coli</i>		27.3	12.5	11	11
2	<i>S. aureus</i>		25.5	11.6	12.5	12

to relatively higher surface area of NPs to volume ration in case of green synthesized ones.

Where GC refers to green synthesized and calcined Co<sub>3</sub>O<sub>4</sub> NP while UG refers to green synthesized and uncalcined Co<sub>3</sub>O<sub>4</sub> NP, and C refers to chemically synthesized Co<sub>3</sub>O<sub>4</sub> NP.

The antibacterial activity of chemically synthesized Co<sub>3</sub>O<sub>4</sub> NPs is relatively low as it were confirmed through the measurement of the zone of inhibition, due to the low concentration of ROS and surface area of this nanoparticles compared to those synthesized in biological method. Fig.7 shows the zone of inhibition of the synthesized Co<sub>3</sub>O<sub>4</sub> nanoparticles against the two bacteria strains.

As reported by [14, 26-29] the production of ROS is used to break the bacterial cell membrane and as a result, as the superoxide radical production increased, ROS production also increased and results in the enhanced antibacterial application. The antibacterial activity of the synthesized Co<sub>3</sub>O<sub>4</sub> nanoparticles in this work is found to be within the range of the previously reported works [29].

### CONCLUSION

In the present work Co<sub>3</sub>O<sub>4</sub> nanoparticles were synthesized biologically in the presence of Phytolacca dodecandra leaf extract and through chemical methods using co-precipitation method and characterized. The average crystalline size and band gap energy were found to be 10.79 and 11.9 nm, 3.35 and 3.18 eV for the biologically and

chemically synthesized Co<sub>3</sub>O<sub>4</sub> NPs, respectively. SEM/EDS analysis confirms the spherical shape and morphology of Co<sub>3</sub>O<sub>4</sub> nanoparticles, as well the result also confirms the absence of any impurities and foreign materials on its EDS image. The Phytolacca dodecandra extract mediated synthesized Co<sub>3</sub>O<sub>4</sub> NPs exhibited considerable antimicrobial activity against both gram negative and gram-positive bacteria strains as compared to the Co<sub>3</sub>O<sub>4</sub> NPs obtained via co-precipitation protocol. Based on the present findings, it can be conclude that Co<sub>3</sub>O<sub>4</sub> nanoparticles synthesized though the presence of Phytolacca dodecandra extract have shown better antibacterial activity even at low concentration NPs (25µg/ml), with zone inhibition of 10.5 mm against E.Coli, and 8.3 mm against S. aureus than chemically synthesized Co<sub>3</sub>O<sub>4</sub> nanoparticles with corresponding zones of inhibition of 8.8 mm and 8.11 mm for both Gram negative and Gram positive human pathogenic bacterial strains respective due to the enhanced production of reactive oxygen species.

### CONFLICT OF INTEREST

The authors declare that there is no conflict of interests regarding the publication of this manuscript.

### REFERENCES

1. Joseph D S. Practical approaches to green solvents. Sci., 2002; 297: 799-803.
2. Ma'mani L, Sheykhan M, Heydari A, Faraji M, Yamini Y. Sulfonic acid supported on hydroxyapatite-encapsulated-γ-

- Fe<sub>2</sub>O<sub>3</sub> nanocrystallites as a magnetically Brønsted acid for N-formylation of amines. *Appl Catal A-gen.*, 2010; 377: 64-69.
3. Gubin S P, Koksharov Yu A, Khomutov G B, Yurkov, G Yu. Magnetic nanoparticles: preparation, structure and properties. *Russ. Chem. Rev.*, 2005; 74: 489-520.
  4. Guzmán M G, Dille J, Godet S. Synthesis of silver nanoparticles by chemical reduction method and their antibacterial activity. *Int. J. Chem. Biomol. Eng.*, 2009; 2: 104-111.
  5. Xiao-qin L, Wei-Xian Z. Iron nanoparticles: The core-shell structure and unique properties for Ni (II) sequestration. *Langmuir*, 2006; 22: 4638-4642.
  6. Ganapathi Rao K, Ashok CH, Venkateswara Rao K, Shilpa Chakra CH, Akshaykranth, A. Eco-Friendly Synthesis of MgO Nanoparticles from Orange Fruit Wast. *Int. J. Adv. Res. phy. sci.*, 2015; 2: 1-6.
  7. Bouchard L S, Anwar M S, Liu G L, Hann B, Xie Z H, Gray J W, Chen F. F. Picomolar sensitivity MRI and photoacoustic imaging of cobalt nanoparticles. *Proc. Natl. Acad. Sci.*, 2009; 106: 4085-4089.
  8. Kitakami O, Sato H, Shimada Y, Sato F, Tanaka M. Size effect on the crystal phase of cobalt fine particles. *Phy. Revi B*, 1997; 56: 13849-13854.
  9. Sekhon B S. (2010). Metalloantibiotics and antibiotic mimics-an overview. *J Pharm Educ Res.*, 2010; 1.
  10. Ansari M A, Khan H M, Khan A A, Malik A, Sultan A, Shahid M, Shujatullah F, Azam A. Evaluation of antibacterial activity of silver nanoparticles against MSSA and MSRA on isolates from skin infections. *Biol. Med.*, 2011;3: 141-146.
  11. Biradar D, Lingappa K, Dayanand A. Antibacterial activity of nano gold particles synthesized by *Bacillus Sps.* *J. eco Biotechnol.*, 2012; 4: 43-45.
  12. Muniappan R, Reddy G V, Raman, A. *Biological control of tropical weeds using arthropods.* Cambridge University Press, 2009.
  13. Bamisaye F, Ajani E, Nurain I, Minari J. Medico-botanical investigation of siam weed (*chromolaena odorata*) used among the "Ijebu" people of Ogun state, Nigeria. *J. Med. Sci.*, 2014; 5: 20-24.
  14. Rathod P, Nemade K, Waghule S. Study of Structure and Optical for Chemically Synthesized Titanium Dioxide Nanoparticles. *Int. J. Phys. Chem. Sci.*, 2015; 4,491-495.
  15. Eneyew T B, Bedasa A G, Osman A Z, Hadgu H B, Fedlu K S. Synthesis of Titanium Oxide Nanoparticles Using Root Extract of *Kniphofia foliosa* as a Template, Characterization, and Its Application on Drug Resistance Bacteria. *J. Nanomater.*, 2020, article 2817037: 2020.
  16. Igwe O, Ekebo E. Biofabrication of cobalt Nanoparticles using leaf extract of *Chromolaena odorata* and their potential antibacterial application. *Res. J. Chem. Sci.*, 2018; 8: 11-17.
  17. Rajabia A. Yaminia Y, Faraji M, Nourmohammadian F. Modified magnetite nanoparticles with cetyltrimethyl ammonium bromide as superior adsorbent for rapid removal of the disperse dyes from wastewater of textile companies. *Nano. Chem. Res.*, 2016; 1: 49-56.
  18. Teng Y, Yamamoto S, Kusano Y, Azuma M, Shimakawa Y. One pot hydrothermal synthesis of uniformly cubic Co<sub>3</sub>O<sub>4</sub> nanocrystals. *Mater. Lett.*, 2010; 64: 239-242.
  19. Caroling G, Vinodhini E, Ranjitham A M, Shanthi P. Biosynthesis of Copper Nanoparticles Using Aqueous *Phyllanthus Embilica* (Gooseberry) Extract- Characterisation and Study of Antimicrobial Effects. *Int. J. Nano. Chem.*, 2015; 1: 53-63.
  20. Farnaz M, Davood G, and Leila L, The Study of Photocatalytic Behavior of Carbon-ZnS Nanocomposites Prepared with Microwave Co- precipitation Method. *J Nanostruct.* 2020; 10: 434-447.
  21. Khodashenas B, Ghorbani H R. Synthesis of copper nanoparticles: an overview of the various methods. *Korean. J. Eng. Chem.*, 2014; 3: 1105-1109.
  22. Ahmed S, Ahmad M, Swami B L, Ikram S. Green synthesis of silver nanoparticles using *Azadirachta indica* aqueous leaf extract. *J. Radiat. Res. Appl. Sci.*, 2016; 9: 1-7.
  23. Ledwith D M, Whelan A M, Kelly J M. A rapid, straightforward method for controlling the morphology of stable silver nanoparticles. *J. Mat. Chem.*, 2007; 17: 2459-2464.
  24. Murugan Perachiselvi J, Jenson S, Muthiah SB, Pushpalaksmi E, Annadurai G. Facile Synthesis of Cobalt Oxide Nanoparticle for Biological Studies. *Appl. Ecol. Environ. Sci.*, 2020; 8: 269-272.
  25. Muhammad H, Ruzma S, Bilal A, Zain-ul-A, Sirajul H, Salahudin M, Shaukat A, Rizwan T K. Green synthesis of cobalt oxide nanoparticles for potential biological applications. *Mater. Res. Express*, 2020; 7: article 025019.
  26. Hrishikesh U, Soumitra S, Rajdeep S, Sujit T, Mrinal K B, Sanjib K P. Green Synthesis, Characterization and Antibacterial Activity of ZnO Nanoparticles. *American Journal of Plant Sciences*, 2018; 9: 1279-1291.
  27. Thirunavukkarasu S, Abdul A R, Chidambaram J, Govindasamy R, Sampath M, Arivarasan V K, Kanayairam V, John, Jayachandran V, Se-Kwon K. Green synthesis of titanium dioxide nanoparticles using *Psidium guajava* extract and its antibacterial and antioxidant properties. *Asian Pac J Trop Med.*, 2014; 7: 968-76.
  28. Waseem A, Krishna K J, Shivani S. Green synthesis of titanium dioxide (TiO<sub>2</sub>) nanoparticles by using *Mentha arvensis* leaves extract and its antimicrobial properties. *Inor. Nano-Met. Chem.*, 2020; 50: 1032-1038.
  29. Muhammad H, Ruzma S, Bilal A, Zain-ul-A, Sirajul H, Salahudin M, Shaukat A and Rizwan T K. Green synthesis of cobalt oxide nanoparticles for potential biological applications. *Mater. Res. Express.*, 2020; 7: 025019.