

## RESEARCH PAPER

## Development of Nano Copper Sulfide (CuS) Structures for Electrochemical Detection of Vitamin C

M. Sudeep <sup>1\*</sup>, Cheelenahally Manjunatha <sup>2</sup>, M. P. Sham Aan <sup>2</sup>, S. Ashoka <sup>3</sup>, R. Suresh <sup>1</sup>, S. M. Ujwal <sup>1</sup>

<sup>1</sup> Department of Chemical Engineering, R V College of Engineering, Bangalore, India

<sup>2</sup> Department of Chemistry, R V College of Engineering, Bangalore, India

<sup>3</sup> Department of Chemistry, Dayananda Sagar University, Bangalore-560068, India

### ARTICLE INFO

#### Article History:

Received 03 April 2021

Accepted 27 June 2021

Published 01 July 2021

#### Keywords:

Ascorbic Acid

CuS

Cyclic Voltammetry

Electrochemical

Hydrothermal

### ABSTRACT

Copper Sulfide (CuS) has received significant interest due to its attractive physical and chemical properties. In this study, the development and characterization of nano CuS (a p-type semiconductor with a bandgap of 1.2~2 eV) for the detection of ascorbic acid (Vitamin C) is reported. Nano CuS was synthesized hydrothermally by studying the effects of cationic and anionic surfactants (CTAB and SDS). The as-synthesized nanostructures were characterized for surface morphology, chemical composition, and crystal structure. The developed CuS nanoparticles were then drop-cast on a graphite electrode and subjected to the electrochemical detection of ascorbic acid. Further, the deposition time of the analyte and the deposition potential of the electrode was evaluated. It was observed that the time required for ascorbic acid to deposit on the electrode was 20 seconds and deposition potential was found to be 0.34V. Besides, the effect of analyte concentration on the sensing ability of the nanomaterial was studied and a linear relationship between the two was observed. The working pH was found to be 9.4.

### How to cite this article

Sudeep M, Manjunatha C, Sham Aan M. P, Ashoka S, Suresh R, Ujwal S. M. Development of Nano Copper Sulfide (CuS) Structures for Electrochemical Detection of Vitamin C. J Nanostruct, 2021; 11(3):628-637. DOI: 110.22052/JNS.2021.03.020

### INTRODUCTION

Researchers are exploring numerous techniques to synthesize materials on a nanoscale owing to their great advantage of enhanced properties such as lightweight, increased strength, photocatalytic ability, and enhanced chemical catalytic activity [1]. These nanomaterials are suitable for diverse applications such as solar cells, nano-fabrics, sensors, cosmetics, and for the domains such as medical, nano-biotechnology, bio-engineering, defense, security etc., [1]. Research on the synthesis of metal chalcogenides such as CuS and their multi-faceted applications due to unique structural and optical properties, are gaining momentum. In recent years the quantum confinement effect attributed to their small

crystallite size is explored [2].

Among the different chalcogenides, the copper-based chalcogenides such as nanoparticles (NPs) of Cu-S/Se, Cu-In-S/Se, and Cu-Zn-Sn-S/Se are opted for photovoltaic, optoelectronic, electrochemical, and photocatalytic applications [3]. CuS NPs, also known as Copper monosulfide NPs are incredibly attractive due to abundant availability of the constituent elements, non-toxicity, low cost, and applications in various fields [3,4]. CuS is a p-type semiconductor with phase dependent band gap varying from 1.1 to 2.0 eV [5,6]. The semiconducting nature of CuS backed by an outstanding electrochemical activity, rich valency, good chemical stability, metal-like conductivity, and ease of synthesis in various

\* Corresponding Author Email: [sudeepm756@gmail.com](mailto:sudeepm756@gmail.com)



This work is licensed under the Creative Commons Attribution 4.0 International License. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

shapes at nanoscale makes it a potential candidate for electrochemical sensing applications [7,8].

Among several analytical methods of detecting biomolecules such as fluorescence, spectrometry, chemiluminescence, electrochemistry, etc., electrochemical detection is considered a simple, sensitive, fast, and cost-efficient method [9]. Among the electrochemical methods, voltammetry is known for the detection of ascorbic acid due to its ability to detect a specific component even at very low concentrations, fast analysis, inherent simplicity, and ease of application. Also, there is no need for sophisticated instruments and trained personnel for voltammetry [10]. Electrochemical biosensors find their use in a variety of fields including medical, biological, food, and environment due to their advantages such as enhanced sensitivity, portability, low cost, online detection, rapid response, and reusability [11].

CuS generally exists in the hexagonal crystalline phase having a P63/MMC space group and a primitive hexagonal unit cell with  $a = 3.8020 \text{ \AA}$  and

$c = 16.430 \text{ \AA}$ . CuS is active both spectroscopically at 620 nm in the UV-Vis region and electrochemically between - 0.4 V to -0.7 V at different scan rates in an alkaline solution [12]. Its properties depend on the morphologies such as nanowires, nanoplates, nanotubes, nanorods, nanoflakes, hollow spheres, and complex hierarchal structures [13]. There are numerous methods available for the synthesis of nano CuS such as solvothermal [14], microwave [15], ultrasonic irradiation [16], and thermolysis of single-source precursors in high boiling point solvents that act as surface passivating agents [17,18]. Among these, the hydrothermal method prompts rapid reaction due to the interaction at high pressure. It offers advantages, such as low-temperature operation, reproducibility, homogeneity, and product purity [19].

In this study, the hydrothermal synthesis of CuS nanoparticles and the impact of surfactants on the size and morphology are reported. Further, the as-synthesized nanoparticles were tested for electrochemical detection of ascorbic acid by

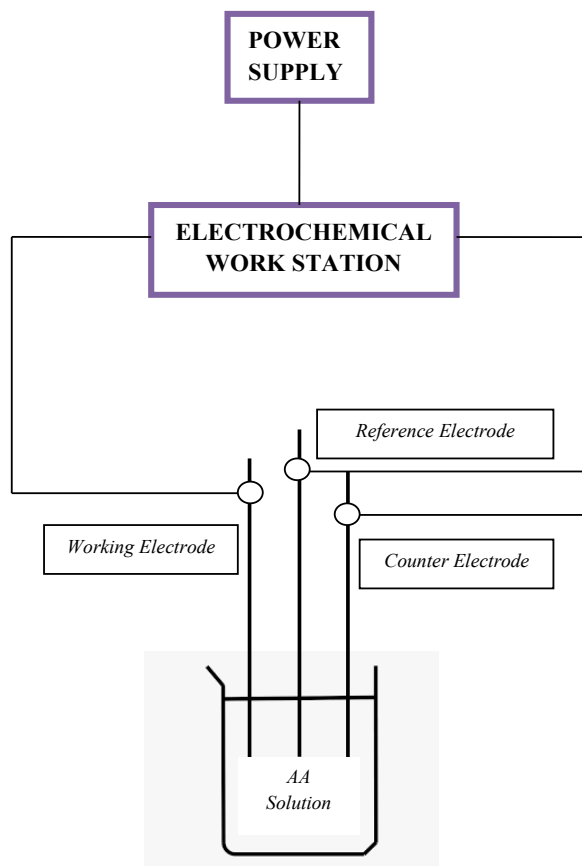


Fig. 1. Schematic of experimental setup for electrochemical

employing cyclic voltammetry.

#### MATERIALS AND METHODS

All the chemicals utilized were of analytical grade, purchased from Merck India Ltd., and were used as received without further purification. Cupric Sulphate ( $\text{CuSO}_4 \cdot 2\text{H}_2\text{O}$ ), Sodium Sulfide ( $\text{Na}_2\text{S} \cdot x\text{H}_2\text{O}$ ), Sodium Dodecyl Sulfate ( $\text{C}_{12}\text{H}_{24}\text{NaO}_4\text{S}$ ), N,N,N,N-Cetyl Trimethyl Ammonium Bromide ( $\text{C}_{19}\text{H}_{42}\text{BrN}$ ), and Acetone were used.

$\text{CuSO}_4$  and  $\text{Na}_2\text{S}$  were weighed in the mole ratio 1:2 and dissolved in 30ml of deionized water. 0.1g of SDS was added to the reactant solution under vigorous stirring to ensure that the reactants were well dispersed and the obtained solution transferred into a Teflon-lined autoclave. The above procedure was repeated by replacing the SDS with CTAB to study the impact of the surfactant. The autoclave was sealed and maintained at  $120^\circ\text{C}$  for 18 h. Later it was allowed to cool to room temperature, naturally. The as-obtained precipitate was centrifuged, washed sequentially with deionized water and acetone, and finally dried at  $60^\circ\text{C}$  for 2h in a hot air oven.

The sensing of ascorbic acid by the as-synthesized nanoparticles was carried out in an electrochemical sensing setup consisting of working, reference, and inert electrodes. The working electrode was fabricated by drop-casting the CuS solution on a graphite electrode. The working electrode was dipped in the electrolyte

made of 2.5 mmol ascorbic acid solution (1 ml), phosphate buffer of pH 9 (8 ml), and 0.1M KCl solution (2 ml). Cyclic voltammetry was used to check the ability of nano CuS to detect ascorbic acid and to determine the voltage at which oxidation of ascorbic acid occurs. Fig. 1 is a schematic representation of the experimental setup. The oxidation of the ascorbic acid takes place at the working electrode and reduction takes place at the counter electrode. The potential developed due to this redox reaction is measured against the reference Ag/AgCl electrode. The effect of the concentration of ascorbic acid on the sensitivity of nano CuS was studied by varying the concentration of ascorbic acid and recording the respective peak values of current. The response of nano CuS to various concentrations was measured by adding 1 ml of 2.5 mmol ascorbic acid to the electrolyte solution, every 10 seconds. Optimum pH was determined by using buffer solutions of pH ranging from 3 to 9. These buffer solutions were prepared using 0.1 M HCl, 0.1 M Disodium Hydrogen Phosphate, and 0.1 M NaOH. The analyte was prepared by adding 8 ml of buffer solution to 2 ml of 0.1 M KCl and 5 ml of 2.5 mmol ascorbic acid. The optimum pH and concentration were determined at which the deposition time and deposition potential were measured.

All the synthesized samples were characterized on a Panalytical Powder Diffractometer with Cu K $\alpha$  radiation ( $\lambda=1.5418 \text{ \AA}$ ). The morphologies, sizes,

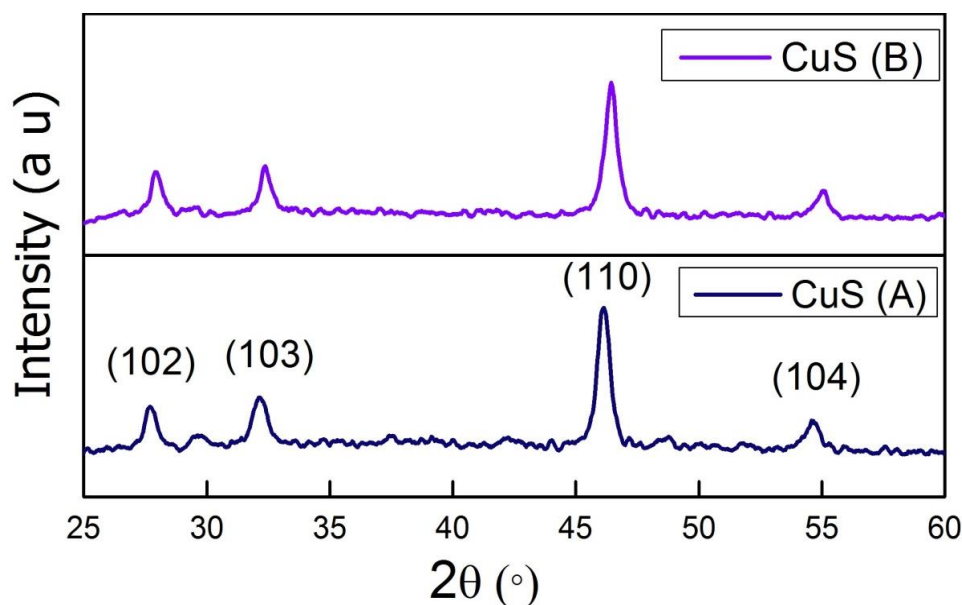


Fig. 2. PXRD of CuS nanoparticles synthesized using different surfactants

and purity of the final product were determined by scanning electron microscope (Tescan-VEGA3 LMU) and EDS analysis.

RESULTS AND DISCUSSION

The hydrothermal reaction between  $\text{CuSO}_4$  and  $\text{Na}_2\text{S}$  resulted in a black precipitate. The obtained product was subjected to powder diffraction and all the peaks in Fig. 2 were indexed to digenite  $\text{CuS}$  (JCPDS Card No. 06-0464) with  $a = 3.792 \text{ \AA}$  and  $c = 16.34 \text{ \AA}$ . From the pattern, it is evident that the product is pure due to the absence of peaks corresponding to the precursors, copper oxide, or other phases of copper sulfide. The sharp and pronounced diffraction peaks suggest that the as-synthesized products are crystalline in nature [20].

EDAX spectra further confirmed the presence of Cu and S peaks alone and quantitative analysis revealed that Cu and S are in a stoichiometric ratio of 1:2.

Fig. 3(A) depicts the SEM images of nano  $\text{CuS}$  structures synthesized using SDS as the surfactant and deionized water as the solvent. It can be seen that much-elongated rice millet-like nano architectures with aggregation are present. Further, these images show the uniform nanoparticle clusters with particle sizes ranging from 49-64 nm. The aggregation can be attributed to the surfactant SDS which aids in the self-assembly of nanoparticles. The end-to-end growth of nanoparticles resulted in the formation of clusters of nano  $\text{CuS}$  architectures. However,

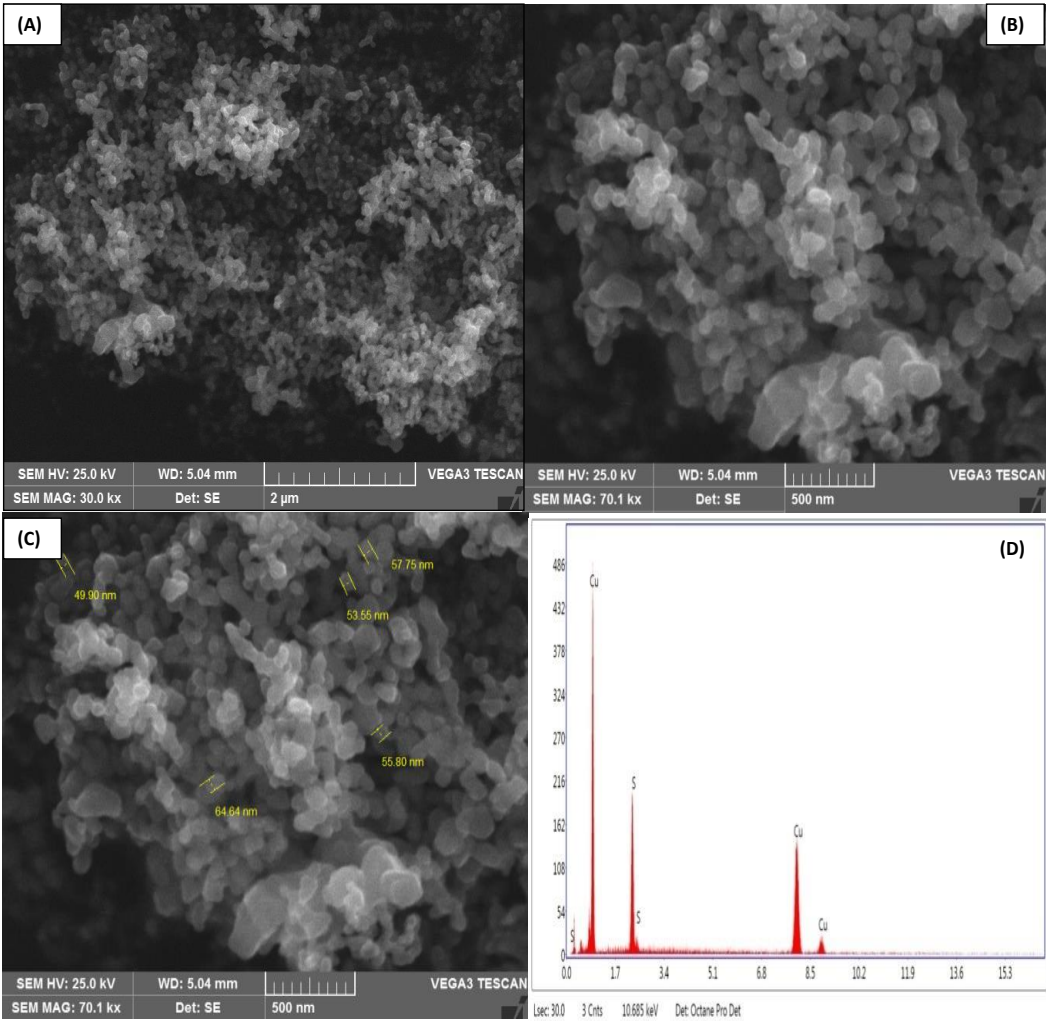


Fig. 3. SEM images of  $\text{CuS}$  nanoparticles with SDS as surfactant. SEM image at a magnification of (A) 2  $\mu\text{m}$  (B) 500nm (C) 500 nm with dimensions (D) EDS of  $\text{CuS}$  nanoparticles

the exact shape of the nanoparticles could not be determined due to excess agglomeration [21]. The XRD pattern of the as-obtained CuS nanoparticles shown in Fig. 2 (A) can be indexed as a dijenite phase (JCPDS Card No. 2-1292).

Fig. 3(B) shows the SEM images of nano CuS structures synthesized with CTAB as the surfactant and deionized water as the solvent. The nanoparticles are found to be uniform with particle sizes ranging from 17 – 40 nm. However, the aggregation is not much pronounced as in the case of SDS. CTAB, being a cationic surfactant, caps CuS and inhibits the lateral growth of CuS clusters helping to reduce agglomeration of nanoparticles. Aggregation of nanoparticles is strongly due to Van der Waals forces of attraction and  $\pi$ - $\pi$  interaction. Hence, obtaining a stable dispersion is a challenge [22]. The fine and mostly monodispersed particles reveal that the growth of nanoparticles was restricted by CTAB [23]. CTAB thus facilitates the homogeneous formation of stable nano CuS structures with well-defined morphology [24]. The XRD pattern of the as-prepared CuS nanoparticles is shown in Fig. 2 (B). All the peaks of the CuS nanoparticles can be indexed as dijenite phase

(JCPDS Card No. 23-960) with lattice constants of  $a = 11.11 \text{ \AA}$  and  $c = 16.36 \text{ \AA}$ .

A noteworthy change is the reduction in the size of the nanoparticles when CTAB was employed as the surfactant. The aforementioned differences are correlated to the structure, size, and type of the surfactant. CTAB, due to its long chain, methyl branches, and cationic nature, prevents aggregation by restricting nanoparticles from being in close vicinity to each other. While the small size and the anionic nature of SDS cause the cupric ions to come closer to each other making the particles appear larger [21].

Electrochemical behavior of ascorbic acid indicates that it can either be in oxidized form (L-dehydroascorbic acid) or reduced form (L-ascorbic acid) obeying the equilibrium as follows [22]:

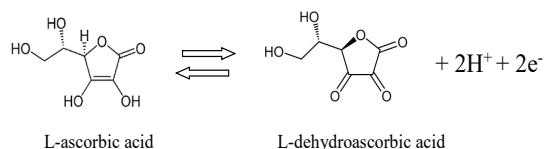


Fig. 4 shows the cyclic voltammogram obtained

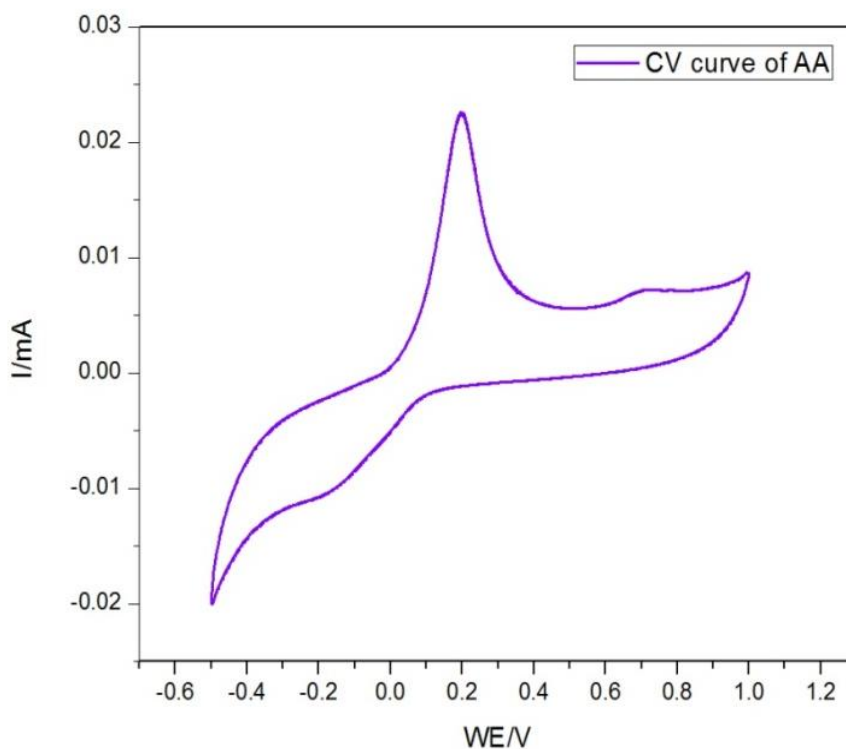


Fig. 4. Plot of current vs. voltage of working electrode (WE) (cyclic voltammogram of Ascorbic Acid (AA))



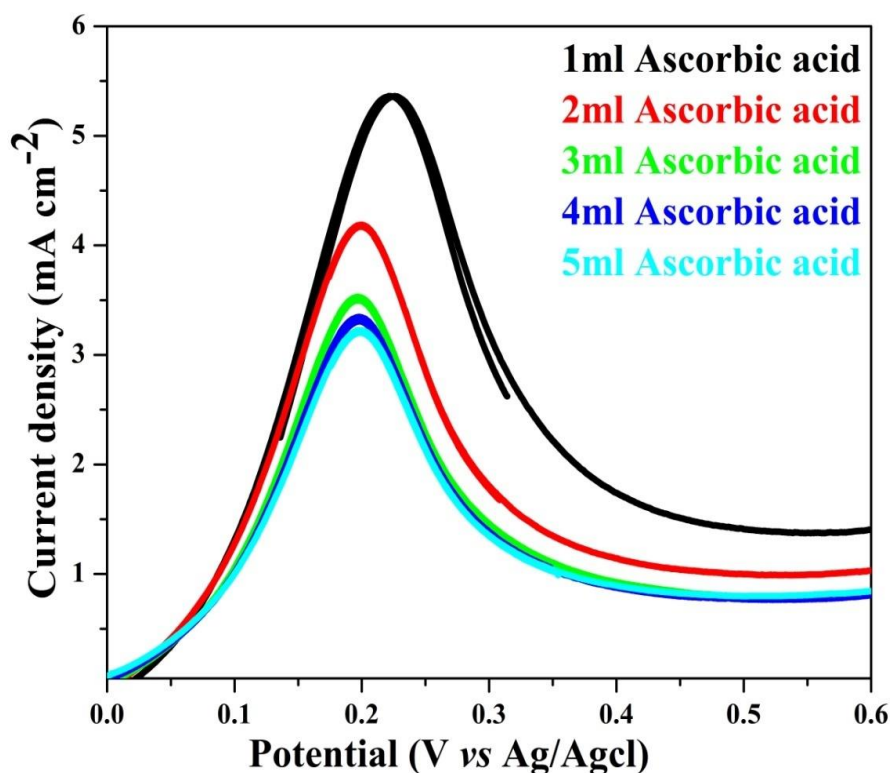


Fig. 5. A series of oxidation peaks for different concentrations of Ascorbic Acid at the working electrode

at a scan rate of  $10 \text{ mVs}^{-1}$ . The peak occurring at  $0.2 \text{ V}$  [23,24] confirms the detection of ascorbic acid by the CuS nanostructures. This peak represents the oxidation of ascorbic acid as indicated by the forward reaction of equation (1). Also, the absence of a reduction peak, as evident from the figure, further confirms the irreversibility of electrochemical oxidation of ascorbic acid [25,26].

Effect of concentration of ascorbic acid on the peak current

The ability of the nano CuS to detect ascorbic acid is correlated to the current registered by the working electrode. Variation in current is due to the variation in the concentration of ascorbic acid. In an experiment, the current flowing through the working electrode dipped in the analyte was monitored. The concentration of the ascorbic acid was varied by adding  $1 \text{ ml}$  of  $50 \text{ ppm}$  ascorbic acid to the stock solution as described in Section 2.1. A series of oxidation peaks for different concentrations of the analyte are shown in Fig. 5. A strong response is obtained at the analyte concentration of  $5 \text{ ml}$  ascorbic acid. Further, the relationship between the electrode current and concentration of the targeted species was obtained

and the resultant graph is shown in Fig. 6. A plot of average currents against the concentration of ascorbic acid indicates linearity as depicted in Fig. 7 [27].

A direct correlation between current ( $I$ ) and concentration ( $C$ ) is seen, allowing for the CuS nanoparticles to act as biosensors without any signal modification as indicated by equation (2). The statistical analysis and the fitted curve shown in Fig. S1, is enclosed in the supporting information.

$$I = 0.00548C + 0.0056$$

The concentration of ascorbic acid can be determined by equation (1) of the trend line in Fig. S1 relating the peak current  $I$  and concentration  $C$  of ascorbic acid. The error induced in the calculation of slope and intercept is of the order of  $10^{-3}$  which is as shown in Table 1 and Table 2 presents the analysis of variation (ANOVA), which are presented in the supporting information.

Effect of pH of buffer solution on the electrochemical detection of ascorbic acid

One of the key parameters that influence the

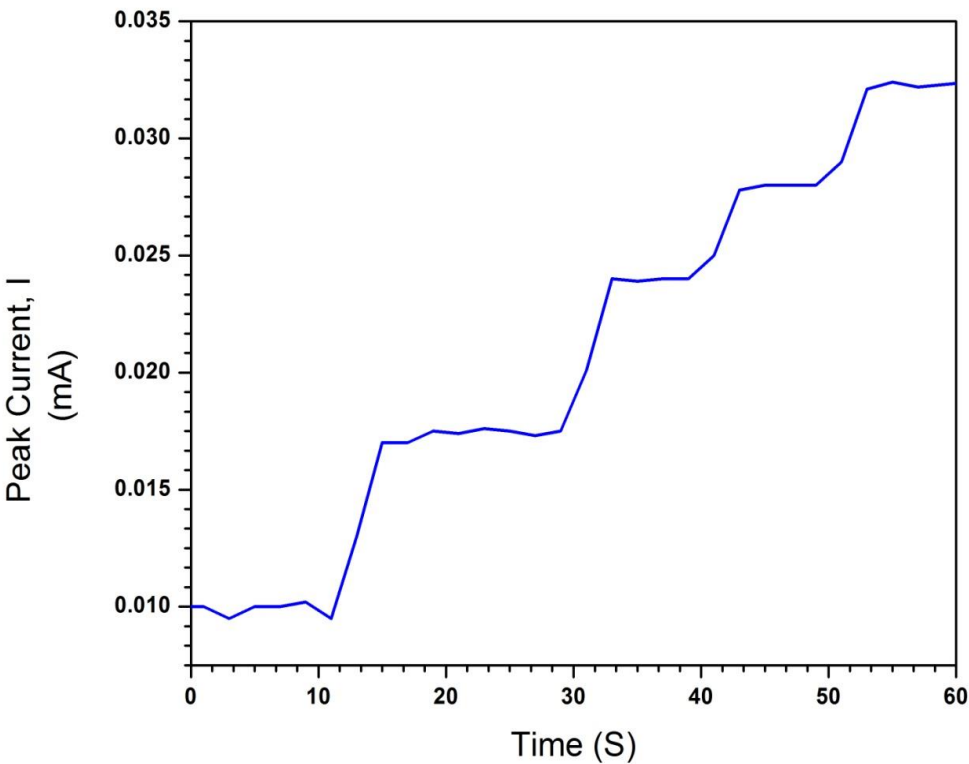


Fig. 6. Plot of Peak Current vs. Time for 1 ml of 50 ppm added at every 10 seconds interval

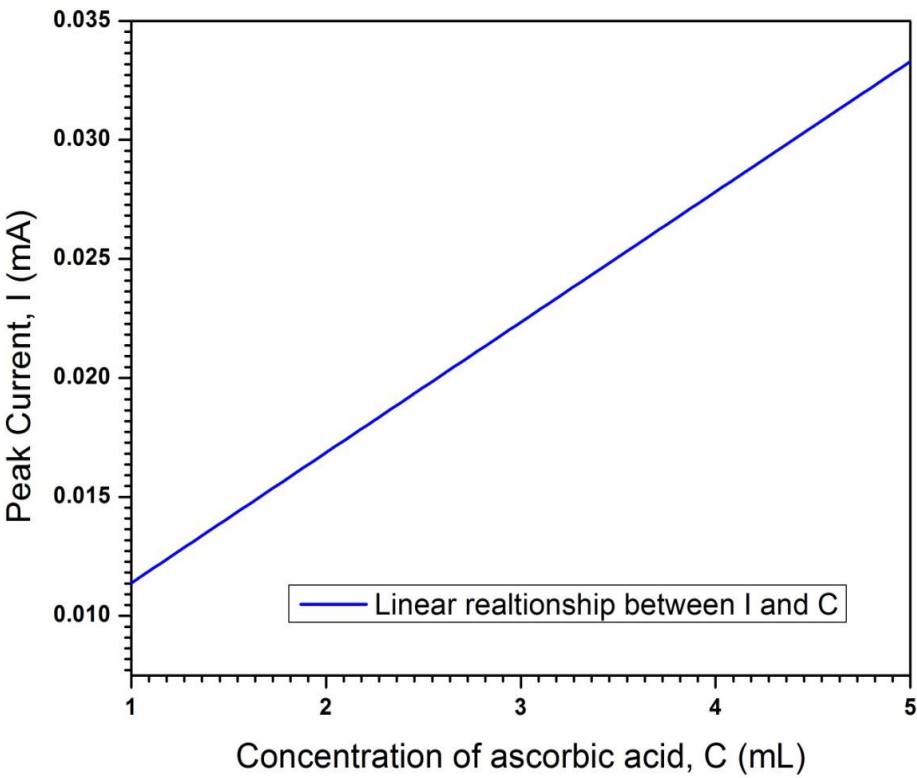


Fig. 7. Calibration plot

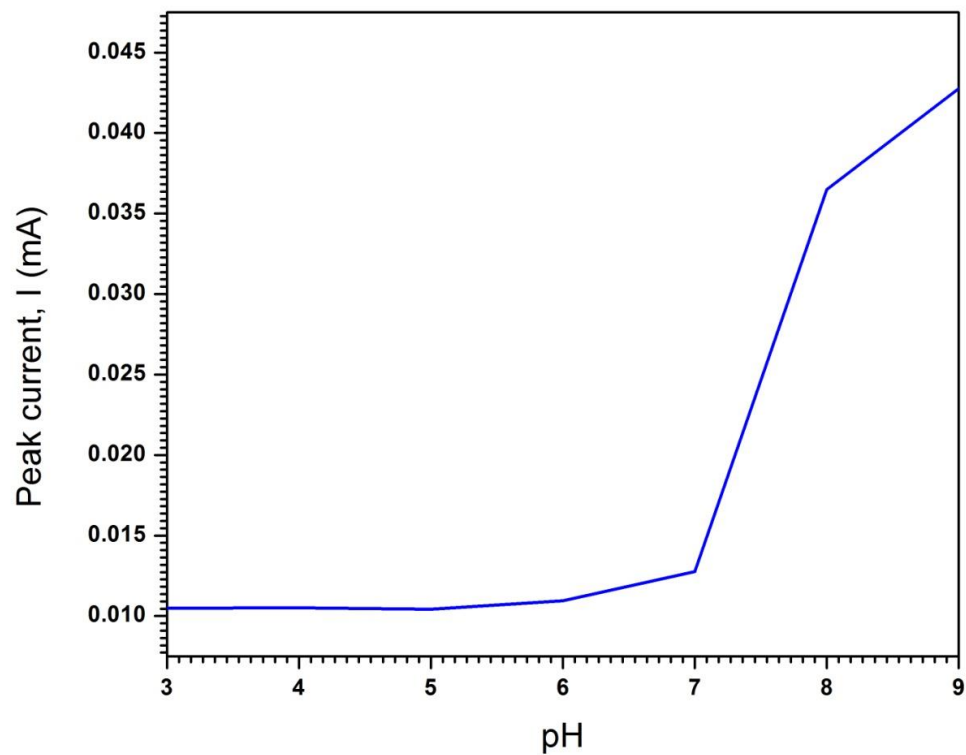


Fig. 8. Plot of Peak Current vs. pH of buffer solution

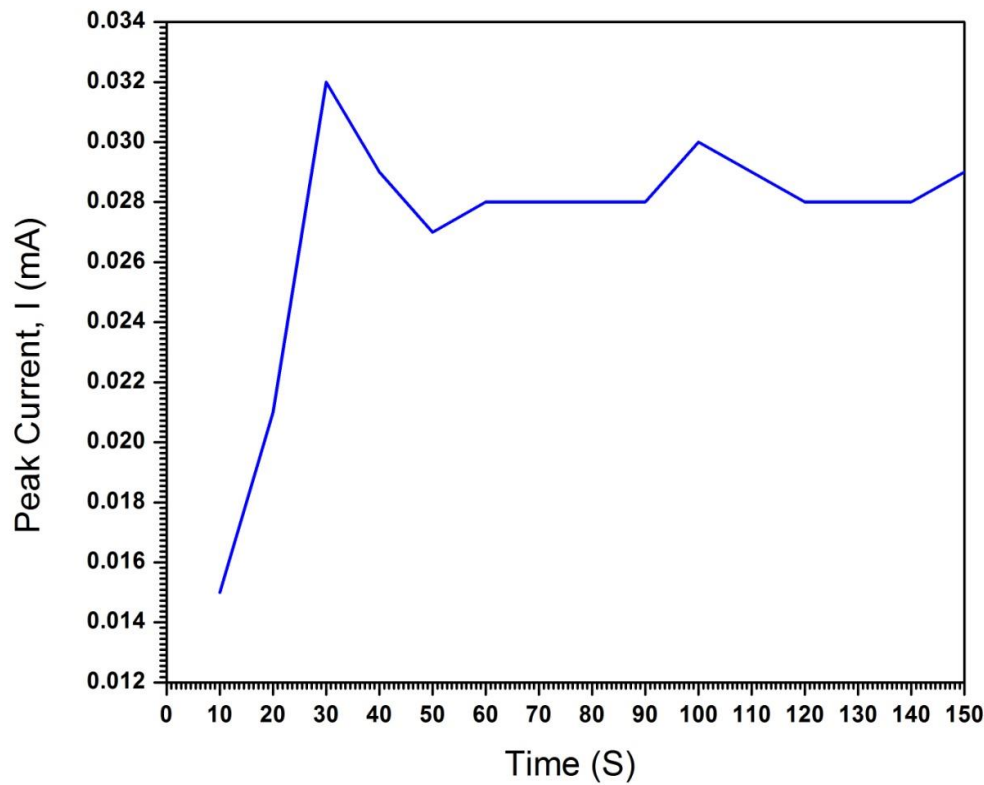


Fig. 9. Plot of Peak Current vs Deposition Time



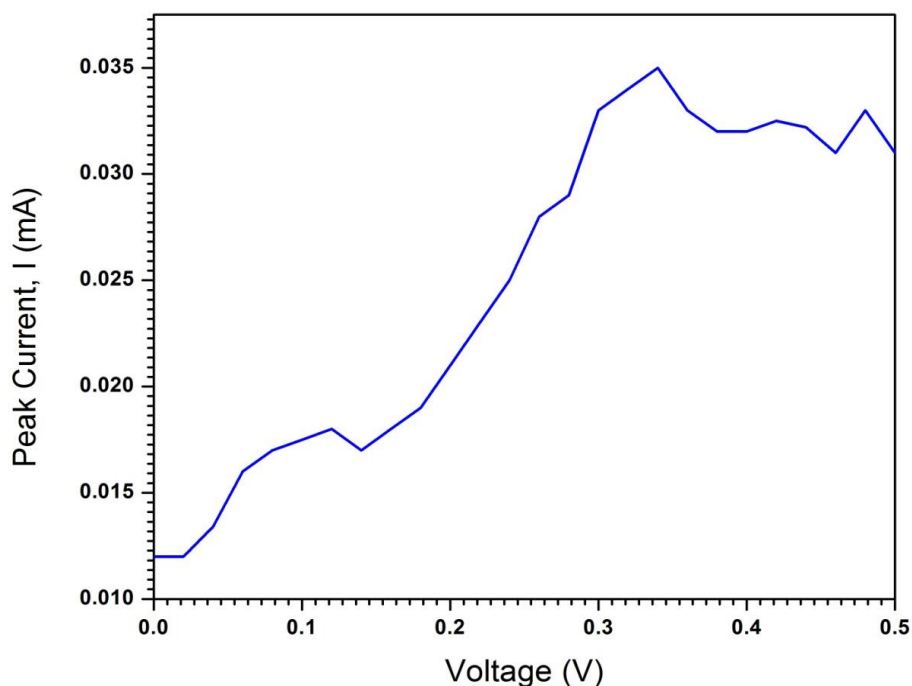


Fig. 10. Response of Peak Current for various Deposition Potentials

response of the electrode in the electrochemical detection of ascorbic acid is the pH of the buffer solution [28]. The pH of the buffer solution or the supporting electrolyte was varied from 3 to 9 to study its effect on the oxidation peak current of ascorbic acid. Fig. 8 shows the oxidation peak currents registered at different pH. The onset of current is observed at a pH of 7 and the peak is observed at a pH of 9 in the considered range of pH. Thus, the pH of the electrolyte solution was chosen to be 9 for all the further studies [29].

The effect of deposition time on the peak current was examined in the time range of 0-150 seconds at the optimized pH of 9 and a concentration of 5 ml of ascorbic acid solution. The peak current was observed at 20 seconds as shown in Fig. 9. Hence 20 seconds was taken as the deposition time for measuring the deposition potential. The electrochemical sensing ability of the nano CuS is affected by another important factor, the deposition potential [30]. The potential was varied from 0 V to 0.6 V and the corresponding response of the working electrode in terms of current was recorded as indicated in Fig. 10. The highest current was measured at 0.3V. This indicates that ascorbic acid observes maximum deposition onto the nanocomposite electrode at this voltage and is designated as deposition potential.

## CONCLUSION

In summary, CuS nanoparticles were synthesized hydrothermally by studying the effects of surfactants on size and morphology. CuS nanoparticles were synthesized at a hydrothermal temperature of 120°C and a duration of 18 hours. The use of SDS as a surfactant resulted in the agglomeration of nanoparticles giving large clusters of size range 49–64nm. However, a particle size of 17 – 40 nm was obtained when CTAB was used as the surfactant. The nanoparticles obtained were elongated in shape. The as-synthesized nanoparticles were used for electrochemical detection of ascorbic acid by drop-casting on a graphite electrode. Cyclic voltammogram recorded the ascorbic acid oxidation peak at 0.2V confirming the ability of the nanoparticles to detect Vitamin C (ascorbic acid). The sensitivity of the nano CuS towards ascorbic acid was studied and a direct correlation was obtained indicating the use of nano CuS as a biosensor without the need for signal amplification. The concentration of ascorbic acid and pH of the buffer solution necessary for the optimum electrochemical response were found to be 5ml and 9 respectively. At this optimum concentration and pH, the deposition time and deposition potential were found to be 20 seconds and 0.3V respectively.

## ACKNOWLEDGMENTS

The authors wholeheartedly thank the HOD, Dept. of Chemistry, Dept. of Chemical Engineering of R V College of Engineering Bengaluru, for providing laboratory facilities and constant support. The authors also extend their gratitude to the Dept. of Chemistry of Dayananda Sagar University, Bengaluru for guidance on electrochemical studies. The authors acknowledge the encouraging effort of the Raashtreeya Sikshana Samithi Trust (RSST).

## CONFLICT OF INTEREST

The authors declare that there is no conflict of interests regarding the publication of this manuscript.

## REFERENCES

- Ajibade PA, Botha NL. Synthesis, optical and structural properties of copper sulfide nanocrystals from single molecule precursors. *Nanomaterials*. 2017 Feb;7(2):32.
- Sun S, Li P, Liang S, Yang Z. Diversified copper sulfide (Cu<sub>2-x</sub>S) micro-/nanostructures: a comprehensive review on synthesis, modifications and applications. *Nanoscale*. 2017;9(32):11357-404.
- Chen W, Xie Y, Hu C, Zeng T, Jiang H, Qiao F, Gu J, Dong X, Zhao X. Room temperature synthesis of aqueous soluble covellite CuS nanocrystals with high photothermal conversion. *CrystEngComm*. 2018;20(30):4283-90.
- Raj CJ, Kim BC, Cho WJ, Lee WG, Seo Y, Yu KH. Electrochemical capacitor behavior of copper sulfide (CuS) nanoplatelets. *Journal of alloys and compounds*. 2014 Feb 15;586:191-6.
- Zhu T, Xia B, Zhou L, Lou XW. Arrays of ultrafine CuS nanoneedles supported on a CNT backbone for application in supercapacitors. *Journal of Materials Chemistry*. 2012;22(16):7851-5.
- Phuruangrat A, Thongtem T, Thongtem S. Cyclic microwave-assisted synthesis and characterization of nano-crystalline alkaline earth metal tungstates. *Journal of the Ceramic Society of Japan*. 2008;116(1353):605-9.
- Liu S, Wei T, Liu Q, Tu W, Lan Y, Han M, Bao J, Dai Z. A nanoscaled Au-horseradish peroxidase composite fabricated by an interface reaction and its characterization, immobilization and biosensing. *Analytical Methods*. 2015;7(8):3466-71.
- Pisoschi AM, Danet AF, Kalinowski S. Ascorbic acid determination in commercial fruit juice samples by cyclic voltammetry. *Journal of Automated Methods and Management in Chemistry*. 2008 Jan 1;2008.
- Shamraiz U, Hussain RA, Badshah A. Fabrication and applications of copper sulfide (CuS) nanostructures. *Journal of solid state chemistry*. 2016 Jun 1;238:25-40.
- Park J, Joo J, Kwon SG, Jang Y, Hyeon T. Synthesis of monodisperse spherical nanocrystals. *Angewandte Chemie International Edition*. 2007 Jun 18;46(25):4630-60.
- Banerjee N, Krupanidhi SB. Synthesis and structural characterization of two-dimensional hierarchical covellite nano-structures. *Materials Chemistry and Physics*. 2012 Dec 14;137(2):466-71.
- Wada Y, Kuramoto H, Anand J, Kitamura T, Sakata T, Mori H, Yanagida S. Microwave-assisted size control of CdS nanocrystallites. *Journal of Materials Chemistry*. 2001 Jan 1;11(7):1936-40.
- Ghows N, Entezari MH. A novel method for the synthesis of CdS nanoparticles without surfactant. *Ultrasonics sonochemistry*. 2011 Jan 1;18(1):269-75.
- Sohrabnezhad SH, Pourahmad A. CdS semiconductor nanoparticles embedded in AIMCM-41 by solid-state reaction. *Journal of alloys and compounds*. 2010 Aug 27;505(1):324-7.
- Phuruangrat A, Thongtem T, Thongtem S. Cyclic microwave-assisted synthesis and characterization of nano-crystalline alkaline earth metal tungstates. *Journal of the Ceramic Society of Japan*. 2008;116(1353):605-9.
- Salavati-Niasari M, Alizadeh S, Mousavi-Kamazani M, Mir N, Rezaei O, Ahmadi E. Surfactant-free fabrication of copper sulfides (CuS, Cu<sub>2</sub>S) via hydrothermal method. *Journal of Cluster Science*. 2013 Dec 1;24(4):1181-91.
- Li F, Wu J, Qin Q, Li Z, Huang X. Controllable synthesis, optical and photocatalytic properties of CuS nanomaterials with hierarchical structures. *Powder Technology*. 2010 Mar 10;198(2):267-74.
- Darouie M, Afshar S, Zare K, Monajjemi M. Investigation of different factors towards synthesis of CuS spherical nanoparticles. *Journal of Experimental Nanoscience*. 2013 May 1;8(4):451-61.
- Saranya M, Santhosh C, Ramachandran R, Kollu P, Saravanan P, Vinoba M, Jeong SK, Grace AN. Hydrothermal growth of CuS nanostructures and its photocatalytic properties. *Powder technology*. 2014 Jan 1;252:25-32.
- Wu SH, Chen DH. Synthesis of high-concentration Cu nanoparticles in aqueous CTAB solution. *Journal of colloid and interface science*. 2004 May 1;273(1):165-9.
- Kamyabi M.A., Asgari Z., Monfared H.H. and Morsali A., 2009. Electrochemical oxidation of ascorbic acid and simultaneous determination of ascorbic acid and dopamine at a bis (4-(4-pyridyl)-2, 2': 6', 2''-terpyridine) iron (III) thiocyanate carbon paste modified electrode. *Journal of Electroanalytical Chemistry*, 632(1-2), pp.170-176.
- Ahmed NA, Hammache H, Eyraud M, Chassigneux C, Vacandio F, Knauth P, Makhloufi L, Gabouze NE. Voltammetric determination of ascorbic acid with zinc oxide modified glassy carbon electrode. *Journal of the Iranian Chemical Society*. 2019 Sep 1;16(9):1957-63.
- Ernst H, Knoll M. Electrochemical characterisation of uric acid and ascorbic acid at a platinum electrode. *Analytica chimica acta*. 2001 Dec 10;449(1-2):129-34.
- Adams RN. Probing brain chemistry with electroanalytical techniques. *Analytical Chemistry*. 1976 Dec 1;48(14):1126A-38A.
- Wen XL, Liu ZL, Han ZX, Rieker A. Significant Micellar Effect on the Oxidative Electrochemistry of Ascorbic Acid. *Journal of Chemical Research, Synopses*. 1997 Jan 1(3):108-9.
- Pei LZ, Lin N, Wei T, Liu HD, Cai ZY. Electrochemical determination of ascorbic acid using Cu sulfide modified glassy carbon electrode. *Surface Engineering and Applied Electrochemistry*. 2016 Nov 1;52(6):565-71.
- Olana BN, Kitte SA, Soreta TR. Electrochemical determination of ascorbic acid at p-phenylenediamine film-holes modified glassy carbon electrode. *Journal of the Serbian Chemical Society*. 2015;80(9):1161-75.
- Yang T, Wang Y, Hasebe Y, Chen L, Zhang Z, Hu Z. Electrochemical Sensor for Detection of Ascorbic Acid Using a Methylene Blue-Doped Polyimide-Modified Glassy Carbon Electrode. *Int. J. Electrochem. Sci*. 2019 Sep 1;14:8494-505.
- Kucukkolbasi S, Erdogan ZO, Baslak C, Sogut D, Kus M. A Highly Sensitive Ascorbic Acid Sensor Based on Graphene Oxide/CdTe Quantum Dots-Modified Glassy Carbon Electrode. *Russian Journal of Electrochemistry*. 2019 Feb 1;55(2):107-14.