

# Removal of Ammonia from Air, using Three Iranian Natural Zeolites

*\*H Asilian<sup>1</sup>, SB Mortazavi<sup>1</sup>, H Kazemian<sup>2</sup>, S Phaghiehzadeh<sup>1</sup>, Sj Shahtaheri<sup>3</sup>, M Salem<sup>1</sup>*

<sup>1</sup>*Dept. of Occupational and Environmental Health, Medical Faculty, Tarbiat Modarres University, Tehran, Iran*

<sup>2</sup>*Jaber Ibn Hayyan Research lab, Atomic Energy Organization of Iran, Tehran, Iran*

<sup>3</sup>*Dept. of Occupational Health, School of Public Health, Tehran University of Medical Sciences, Iran*

---

## Abstract

Ammonia in air can be hazardous to human and animal life and should be removed from the environment. Recently the removal of environmental pollutants such as ammonia by means of natural and modified zeolites has attracted a lot of attention and interests. In this study the capability of three Iranian natural zeolites (Clinoptilolite) in point of view of removal of ammonia from air was investigated. Through this research, different zeolites from various regions of Iran including Semnan, Meyaneh, and Firoozkooh resources were considered to be studied. These samples of zeolites were ground and granulized into 425  $\mu\text{m}$  to 4 mm and were utilized in dynamic sorption experiments. Curves of sorption were plotted and breakthrough and saturated points of zeolite samples were obtained. The adsorption capacities at different ammonia concentrations, temperatures, and flow – rates were also calculated. Results obtained showed that, the natural Iranian zeolite (Clinoptilolite) was identified to be more efficient adsorbent than the others to remove ammonia from the air. In the same conditions, the obtained breakthrough time for clinoptilolite sample of Meyaneh was longer than the others ( 135min ), while, the adsorption capacity of Semnan clinoptilolite was higher than adsorbents ( 6.30 mg /g ) ( $P<0.0001$ ).

**Keywords:** *Ammonia removal, Adsorbent, Iranian natural zeolites, Clinoptilolite.*

---

## Introduction

Ammonia is a colorless, diffusive at 760 mmHg, with a hot odor which is hazardous at concentration of more than 50 ppm (1). This gas is used extensively in the chemical industries. Its production in The USA has been increased from  $5.8 \times 10^6$  ton/year in 1964 and  $11.5 \times 10^6$  ton/year in 1974 to  $25.5 \times 10^6$  ton in 1990 (2). The amount of ammonia released yearly during industrial and agricultural processes, has been estimated to be about 113-244  $\times 10^6$  ton world wide (2). In Iran also a considerable amount of ammonia is released into the environment from different industries such as oil refineries, petrochemical complexes and fertilizer manufacturing, causing variety of problems associated with the control systems (3). Emission of  $\text{NH}_3$  as a pollutant from sources can cause human and environmental ef-

fects such as eye and throat irritation, cough, acute pulmonary effects, pulmonary edema, pneumonia, biological nitrification and finally death of aquatic organism (4). According to the above mentioned reasons, controlling of this pollutant essentially is required. So far, different methods such as washing out with water (scrubbing), condensation and biological methods are used for removal and control of  $\text{NH}_3$ , which they have disadvantages (5). Nowadays the development of alternative treatment techniques such as using solid sorbents as a natural adsorbent (e.g. natural zeolites in this study) has a great interest for scientists. Zeolite, molecular sieves, as a well known category of aluminosilicate which exists both naturally and synthetically, shows a very good capability in gas separation technology. The abundance of natural zeolite resources in Iran can play a great role to develop this technology. Zeolite is a

well known category of crystalline mineral which hydrated aluminosilicate of alkaline and alkaline earth elements with a typical formula of  $M_{x/n} [(AlO_2)_x(SiO_2)_y] \cdot w \cdot H_2O$ . In geological concerns, natural zeolites can be formed in active volcanic environment under hydrothermal conditions, as well as sedimentary origins crystalline framework of zeolites structure contains a variety of channels and pores.

According to the published results, zeolites are suitable adsorbent for different polar and nonpolar molecules such as  $CO_2$ ,  $SO_2$ ,  $NO_2$ ,  $NO$ ,  $H_2S$ ,  $NH_3$ ,  $H_2O$ , aliphatic hydrocarbons, aromatic hydrocarbons, alcohols, ketons, and other similar molecules (6- 8). Use of natural zeolite as a sorbent is considerably increased in different industries (9).

Adsorption, ion-exchanging and catalytic behavior of different zeolites, has made them as an interesting material for different industrial and environmental applications. Early studies on the application of zeolites as adsorbents, were reported in 1938 when Barrer published some scientific information of the properties and characteristics of zeolites (10). Natural and

synthetic zeolites have been known as an important material in modern technology for extracting and removal of pollutant from air and other waste stream (10).


Nowadays, production and utilization of zeolites for industrial processes has made the method to be one of the important scientific fields of research and study (11).

This paper presents the results obtained from the study on dynamic adsorption experiments on some zeolites from different regions of Iran for  $NH_3$  removal from air.

### Materials and Methods

Three different Iranian natural Clinoptilolites were obtained from semnan ( $Z_s$ ), Meyaneh ( $Z_m$ ) and Firoozkooh ( $Z_f$ ) regions of Iran.

The samples were ground (Maxillary grinder) and particle size of 2-4 mm, 1-2 mm, and 425  $\mu m$ -1mm were selected for further studies. All of the sorption experiments were done on a dynamics system. A simple schematic of the designed system is shown in Fig. 1.

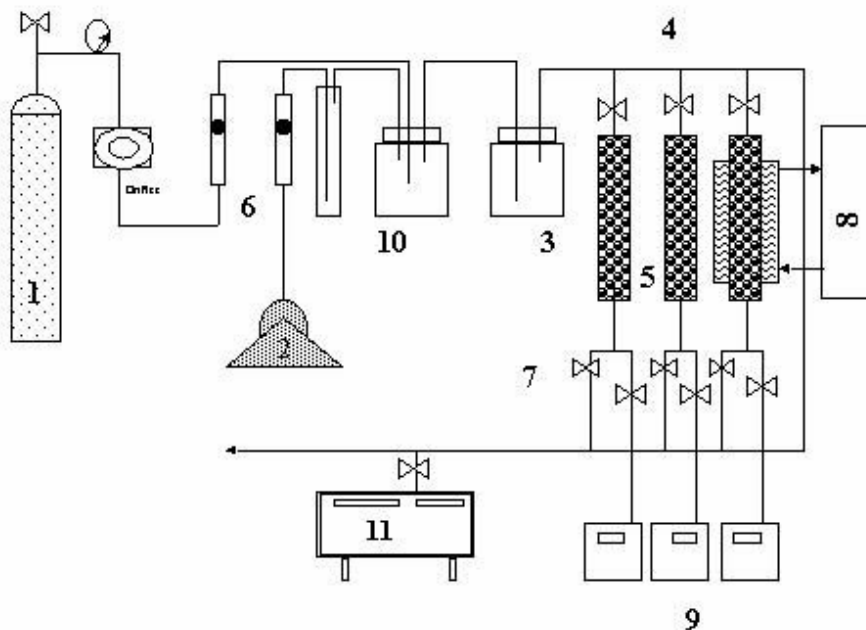

**Fig. 1:** Schematic diagram of the designed system for study of dynamic adsorption of  $NH_3$

The components of system in figure (1) is as follows:

NH<sub>3</sub> gas supplier

Air supplier pump

Mixer of air and NH<sub>3</sub>

Distributor of mixed gasses through columns

Zeolites bed ( columns )

Flow meter

Valves and connections

Thermometer

Gas meter

Humidity adsorbent ( cilicagel )

NH<sub>3</sub> analyzer

During the experiments, the flow rate (exhaust) of NH<sub>3</sub> and air was adjusted at range of cm<sup>3</sup>/ min by a flowmeter followed by mixing thoroughly NH<sub>3</sub> and air in the connected bottles to the system. Before entering the mixed gas to the columns, concentration of the ammonia was measured by a gas chromatograph equipped with, propak N column, TCD detector, as well as by a portable analyzer of NH<sub>3</sub> (multi-warn Drager, Germany) with an electrochemical sensor.

After fixing the concentration in system, the entrance value of columns with 10 g zeolite was opened followed by adjusting the flow – rate of the gas by flow – meter at the required level. Starting time, temperature, pressure, flow – rate and the numeral of gas meters were recorded. Concentration of NH<sub>3</sub> at the outlet of the columns was measured before breakthrough point every 5 min and after breakthrough up to saturated point every 15min.

The column temperature was also adjusted by water circulation system.

## Results

In order to characterize the zeolite samples, X- ray fluorescence method ( XRF) was used. The obtained results from chemical analysis of the samples are shown in Table 1.

**Table 1:** Chemical composition of the zeolite samples, by X-ray fluorescence

Components	Contents wt%		
	Z <sub>s</sub>	Z <sub>f</sub>	Z <sub>m</sub>
SiO <sub>2</sub>	64.4	67.24	67.35
Al <sub>2</sub> O <sub>3</sub>	12.80	11.71	11.73
Fe <sub>2</sub> O <sub>3</sub>	1.31	0.58	0.88
TiO <sub>2</sub>	0.31	0.42	0.34
CaO	2.37	3.04	2.34
MgO	1.15	1.16	1.21
Na <sub>2</sub> O	1.13	1.19	0.88
K <sub>2</sub> O	2.64	1.48	1.72
P <sub>2</sub> O <sub>5</sub>	0.21	no	no
LoI	13.47	13.19	12.94
Total	99.55	100.4	99.43

no = not observed

\* Loss on ignition

The X-ray diffraction patterns and thermal analysis of the samples were also obtained. According to the results of used characterization techniques, all of the investigated natural zeolites were Clinoptilolite and belong to the hlandite (HEU) group. The results of column adsorption experiments including breakthrough volume and time, saturated point and time for different zeolites are illustrated in Table 2 and Figs. 2,3 and 4.

**Table 2:** The breakthrough and saturation point and adsorption capacity of natural clinoptilolite for NH<sub>3</sub> (T = 22°C, amount of zeolite in each column 10g, particle size 1-2 mm ).

Zeolite type	Z <sub>s</sub>	Z <sub>m</sub>	Z <sub>f</sub>
Experiment Parameters			
Inlet mean concentration into column (ppm)	180	180	180
Mean flow-rate (lit/min)	2.1	2.1	2.1
Saturated time (min)	130	135	90
Saturated time (min)	252	225	242
Adsorption capacity up to brakthrough (mg/g)	3.25	3.37	2.25
Adsorption capacity up to brakthrough (mg/g)	6.30	5.62	6

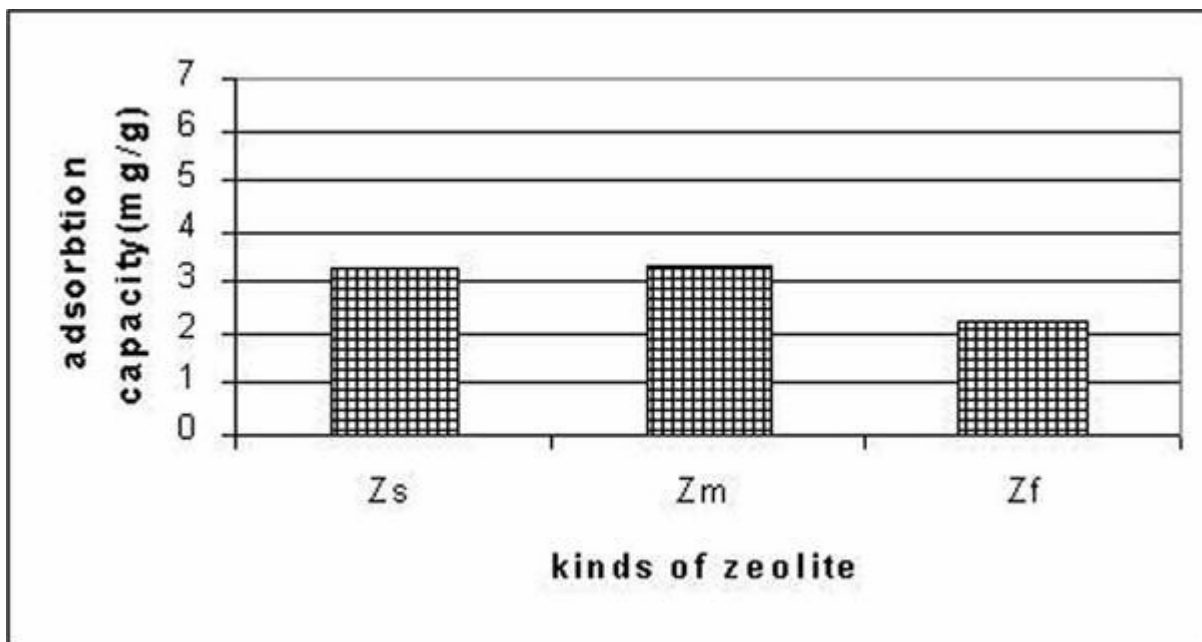


Fig. 2: Ammonia adsorption capacity up to breakthrough point for different Iranian natural clinoptilolite ( T = 22°C)


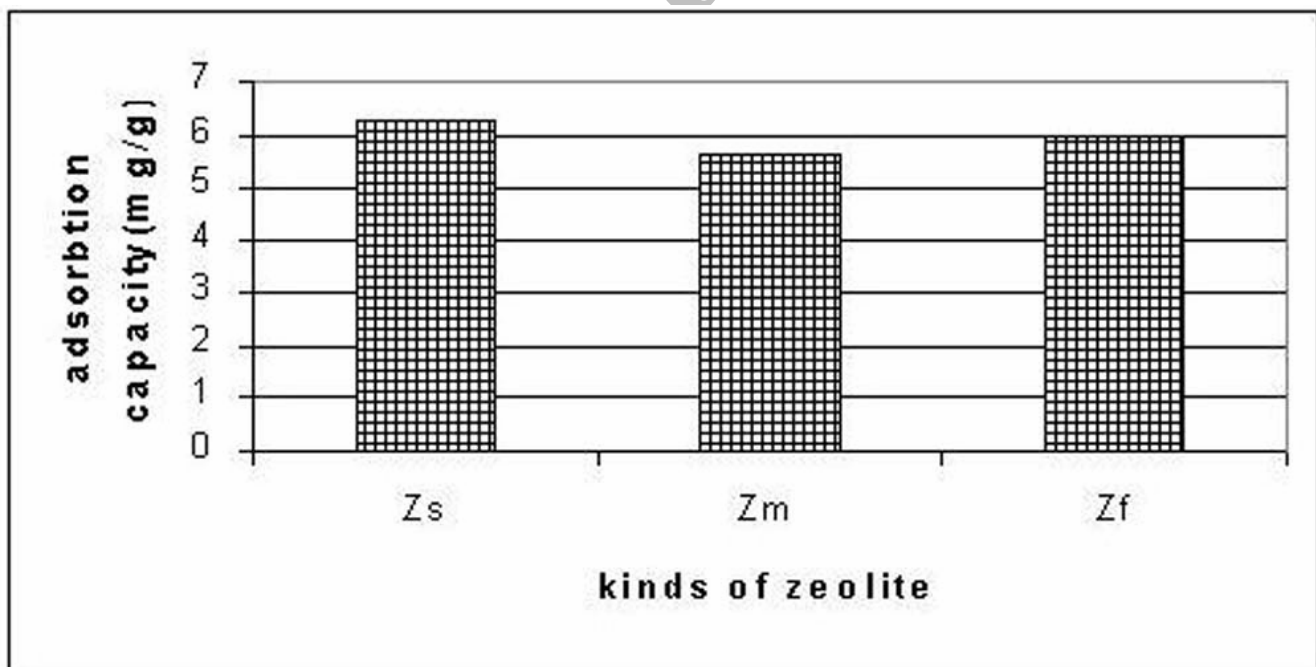


Fig. 3: Ammonia adsorption capacity up to saturation point for different Iranian natural clinoptilolite ( T = 22°C )

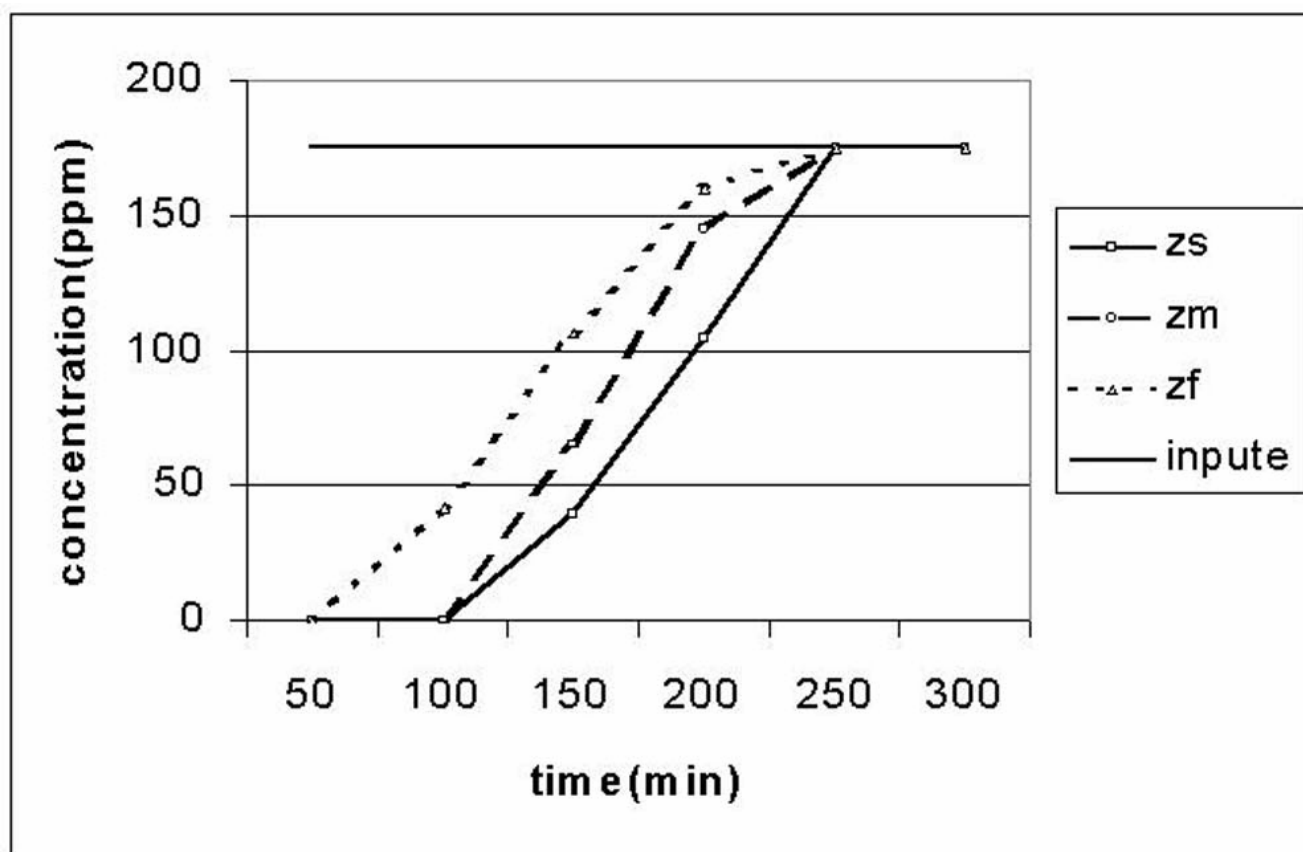

**Fig. 4:** Breakthrough and saturation curves of NH<sub>3</sub> adsorption on different Iranian natural clinoptilolite (T = 22°C, adsorbent = 10 g, particle size 1-2 mm ).

## Discussion

The obtained results of the performed dynamic adsorption tests showed that all of the investigated Iranian natural Clinoptilolites could be suitable and efficient adsorbents for NH<sub>3</sub>. The similarity of chemical behavior of NH<sub>3</sub> and H<sub>2</sub>O molecules, can be mentioned as one of the main reasons for selectivity of zeolite toward NH<sub>3</sub>. However, another parameter, i.e. the high dipolar moment of NH<sub>3</sub> can increase the adsorption selectivity. Investigation of Table 2 and Fig. 2, showed that the breakthrough adsorption capacity of Z<sub>m</sub> sample is higher than other investigated samples (3.37 mg/g in comparison to 2.25 mg/g for Z<sub>f</sub> and 3.25 mg/g for Z<sub>s</sub>) and its breakthrough time is longer (135 min in comparison to 90 min for Z<sub>f</sub> and 130 min for Z<sub>s</sub>). The saturated point for Z<sub>m</sub> is

attained faster than Z<sub>s</sub> and Z<sub>f</sub> samples. The presence of the clay phase in the Meyaneh zeolite can be considered as a reason for longer breakthrough time. It is worth mentioning that, the clay phase can be considered as an adsorbent for gaseous molecules. It seems that, the kinetic reaction of ammonia adsorption on clay phase in the Meyaneh zeolite is faster in comparison to clinoptilolite phase (12).

The required time to attain saturation point for Z<sub>m</sub> clinoptilolite (240 min ) as well as adsorption capacity ( 6.30mg/g) is higher than other zeolite samples. The higher amount of aluminum and water content of this sample plays the main role for such a behavior.

In this study, the effect of temperature, particles size of zeolite sorbent as well as the flow – rate of the gas on the adsorption process were also

evaluated. From the data obtained, It can be concluded that, as the column temperature increases from ambient temperature to 35°C and 60°C, breakthrough point will achieve in longer time and consequently the adsorption capacity is increased. Removal of H<sub>2</sub>O molecules from the zeolites framework by increasing the temperature can facilitate the NH<sub>3</sub> sorption processes. By releasing of H<sub>2</sub>O molecules, the substitution of NH<sub>3</sub> molecules can be facilitated on the basis of data obtained from thermal analysis techniques.

Through this study, it was also clarified that, decreasing the sorbent particle size, from range of 1-2 mm to the range of 425 µm – 1 mm, the adsorption capacity as well as breakthrough time were considerably increased, although decreasing the particle size causes an increase in the pressure drop of the system. This process caused also a decrease in the flow – rate of the pump, which wasn't quantitatively measured. It is worth mentioning that, above process should be consider carefully optimizing the process for industrial application. These investigations also showed that, in the same conditions, an increase in gas flow – rate cause a decrease in breakthrough time and vice versa.

From the results obtained in this study, following conclusions can be made :

The investigated Iranian natural Clinoptilolite zeolites are suitable adsorbent for removal of ammonia from the polluted air streams.

In the same condition, Meyaneh Clinoptilolite had a longer breakthrough time (135min) while Semnan Clinoptilolite had higher adsorption capacity ( 6.30 mg/g), ( $P < 0.0001$ ).

According to the effect of the zeolite composition on the adsorption behavior, it seems that the modification of zeolite can improve the NH<sub>3</sub> adsorption efficiency.

Based on the above results, the investigated natural zeolites can be used for removal of NH<sub>3</sub>, from the exhausted media of different industries. To optimize the conditions of removal process, further studies and researches should to be performed.

## Acknowledgements

The scientific and logistic cooperation of following organizations are highly appreciated : Jaber Ibn Hayyan research laboratories, Atomic Energy Organization of Iran ( AEOI) Dept. of Occupational Health, Thehran University of Medical Sciences. Dept of Occupationa Health, University of Baghiyatallah, Iran

## References

1. USEPA (United States Environmental Protection Agency) (1995). Control technology center. *Control and pollution prevention options for ammonia emissions*. 456/R-95-002.
2. WHO (World Health Organization) (1998). *International program on chemical safety environmental health criteria*. 54.
3. MTMU (Medical faculty of Tarbiat Modares University) (2000). Report to Iran petrochemical research center: *Qualitative and quantitative evaluation of atmospheric contaminants in Tabriz and Urmia petrochemical complexes Tehran*
4. ATSDR (Agency for toxic substances and disease registry) (1998). *Toxicological profile for ammonia*. US Department of health and human service USA, DOC. p.125.
5. USEPA (United States Environmental Protection Agency) (1995). Clean air technology center. *Zeolite a versatile air pollution adsorber*. 456/F-98-004.
6. Malherbe R, Fernandes L, Colado L et al (1995). Phsico – chemical properties of natural zeolites used for adsorption of water. In: Ming DW, Munpton FA, Eds. *Int, comm, natural zeolite*, pp. 299- 308.
7. Malherbe R, Fernandez L, Lopez L, Pozas C, Montes A (1995). *Natural zeolites*. In: 93conference volume international committee on natural zeolite , Brockport , Newyork , pp . 299-308.
8. Malherbe R (1995). Complementary approach to the volume filling theory of

- adsorption in zeolites , *Microporous and mesoporous materials*.
9. Chmielewska H, Konecny E, Bosan J (1992). Ammonia removal from selective Ion exchange on slovak clinoptilolite. *Actahydrochim, hydrofoil*, 20: 269 – 72.
  10. Barrer RM (1978). *Zeolites and clay minerals as sorbents and molecular sieves* . Academic Press . London . pp. 103-223.
  11. Roskill (1995). *The economics of zeolites*. Fourth, ISBN0 86214 4310.
  12. Kazemian H (2002). *Zeolite science in IRAN* (a brief review). In : zeolite, O2, 6<sup>th</sup> Int. Occurrence, properties and utilization of natural zeolite, Thessaloniki, Greece.

Archive of SID