

Synthesizing and Characterizing Functionalized Short Multiwall Carbon Nanotubes with Folate, Magnetite and Polyethylene Glycol as Multi-targeted Nanocarrier of Anti-cancer Drugs

Mahmoud Jafari^a, Danial Heidari^{a,b} and Pedram Ebrahimnejad^{b,c*}

^aDepartment of Physics, K. N. Toosi University of Technology, Tehran, Iran; ^bDepartment of Pharmaceutics, Faculty of Pharmacy, Mazandaran University of Medical Sciences, Sari, Iran; ^cPharmaceutical Sciences Research Center, Mazandaran University of Medical Sciences, Sari, Iran.

Abstract

Multifunctional nanomaterials showed great advantages in drug delivery. Folic acid (FA) binding protein, a glycosyl phosphatidyl inositol anchored cell surface receptor for folate, is overexpressed in several human tumors, whereas it is highly restricted in normal tissues. Therefore, in this study, FA, polyethylene glycol (PEG), and Fe₃O₄ nanoparticles multifunctionalized short multiwall carbon nanotubes (PEG-FA-SMWCNT@Fe₃O₄) were synthesized by conjugating folate, PEG, and magnetite nanoparticles with carboxylated multiwall carbon nanotubes. The prepared c-SMWCNT@Fe₃O₄ was characterized by X-ray diffraction (XRD) and vibrating sample magnetometer (VSM) in order to investigate crystal and magnetic properties, respectively. The images obtained by scanning electron microscopy (SEM) showed that the magnetite nanoparticles were attached to the surfaces of carbon nanotubes and SMWCNT@Fe₃O₄ was formed. Investigation of functional groups using Fourier transform infrared (FTIR) spectra indicated that PEG-FA was successfully linked to SMWCNT@Fe₃O₄.

Keywords: Carbon Nanotubes; Multi Function; Nanotechnology; Targeting.

Introduction

Nano-sized materials exhibit interesting properties (1) and present new opportunities for a wide range of studies and applications in various areas including physics (2), chemistry (3), biology (4), and medicine (5). Use of nanotechnology in various therapeutic sectors has revolutionized the field of medicine, in which nanostructures are used as biomedical tools for investigation (6).

Common anticancer drugs not only affect cancer cells but also influence normal cells

and cause severe side effects. To achieve more effective cancer chemotherapy, it is essential to appropriately select anticancer drugs for the cancer cells. Since the complications of anticancer drugs include their impact on normal cells, it is preferred to utilize targeted drug delivery systems. Nanoparticulate drug delivery systems such as liposomes (7), polymers (8), nanoparticles (5), dendrimers (9), and carbon nanotubes (10) which contain anticancer agents have received a great deal of attention due to their unique accumulation behaviors in tumor sites. One of the best and ideal solutions for most of the serious problems in chemotherapy is application of drug-loaded NPs which have targeting functions (11). NP surface is decorated

* Corresponding author:

E-mail: p_ebrahimnejad@yahoo.com

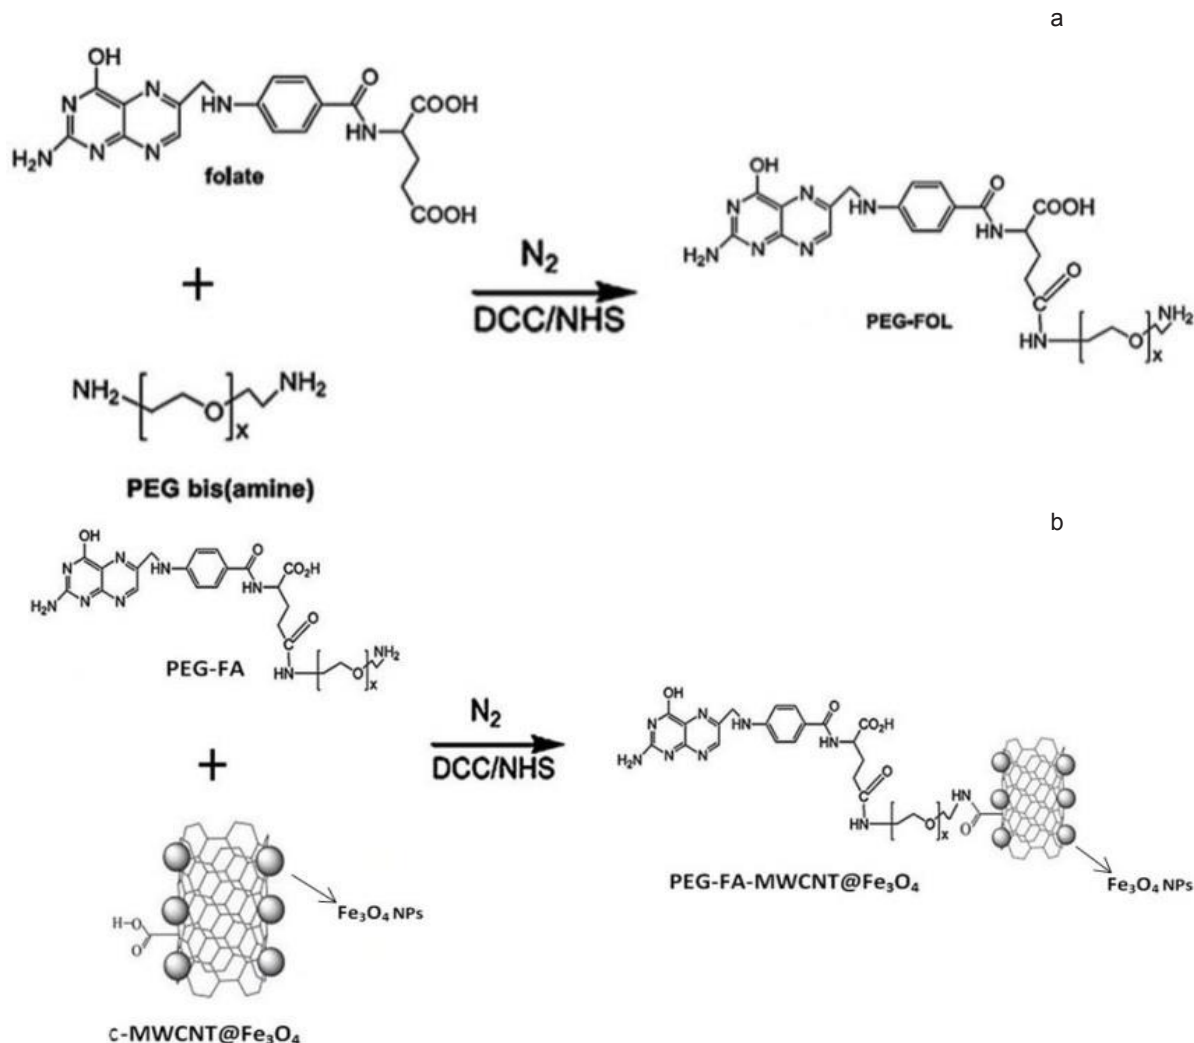


Figure 1. Schematic representation of (a) PEG-FA, and (b) PEG-FA-SMWCNTs@Fe₃O₄ conjugate.

with different ligands that are delivered within cells through receptor-mediated endocytosis. Folate (FOL), as one of these endocytosis, has been widely used owing to its many advantages such as small ligand size, convenient availability, low cost, relative simplicity and defined conjugation chemistry, high receptor affinity, absence of normal tissue receptor expression, and therefore high tumor tissue specificity (5, 9 and 12). As a glycosyl phosphatidyl inositol anchored cell surface receptor for folate, folate binding protein is over-expressed in some human tumors; however, it is widely limited in normal tissues (13). Using folate decorated liposomes, micelles, and NPs of biodegradable

polymers including poly-lactide-co-glycolide (PLGA), PLGA-polyethylene glycol (PEG), D-alpha-tocopheryl polyethylene glycol 1000 succinate (vitamin E TPGS)–folate conjugate, doxorubicin–PLGA–vitamin E TPGS conjugate, and PLGA-PEG-FOL conjugate as anticancer agents has raised cellular uptake and cell cytotoxicity of the formulated anticancer drugs (5, 9 and 10).

In attempts to investigate a suitable nanocarrier system, carbon nanotubes (CNTs) have attracted great attention in recent years (10, 14). Suitable functionalization is an important factor that affects cytotoxicity and performance of CNTs in biological systems (15).

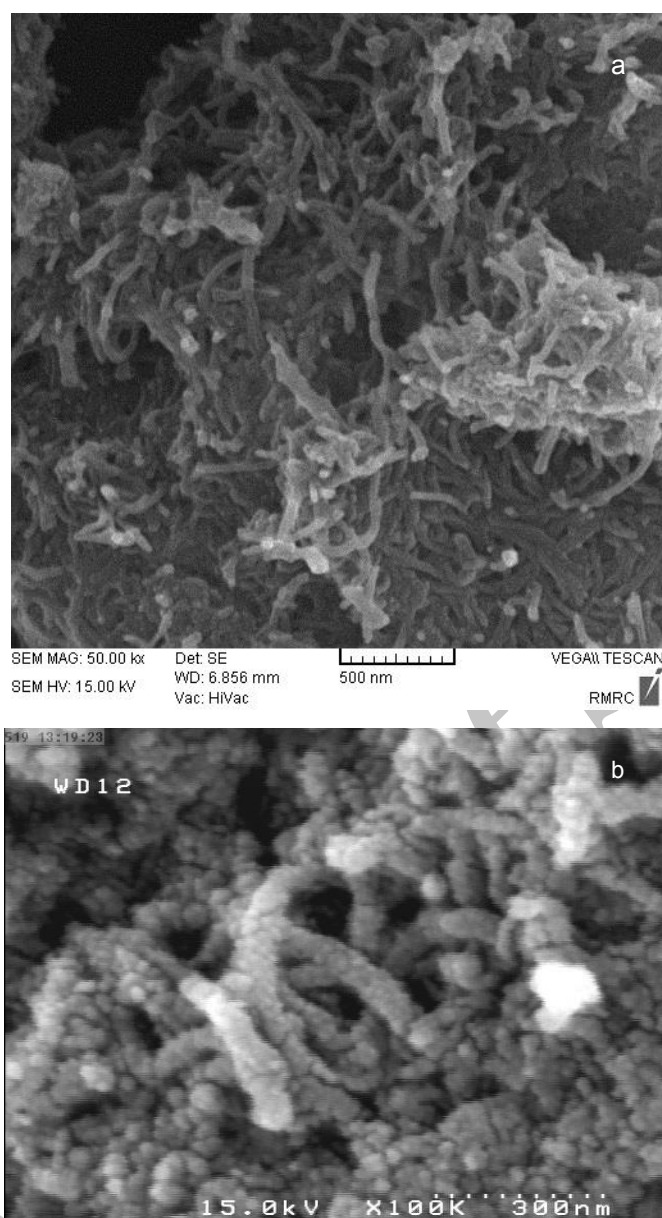


Figure 2. SEM images of (a) c-SWCNT, and (b) c-SWCNT@Fe₃O₄.

In the present work, PEG-FA-conjugated SMWCNT@Fe₃O₄, which could be used as a multi-targeted drug nanocarrier for delivering an anti-cancer agent to cancer cells with the assistance of an external magnetic field, was prepared and characterized.

Experimental

Materials

Short MWCNTs (diameter: 30–50 nm, length:

0.5–2 μm, purity: >95%, and SSA: 200 m²/g) were purchased from Neutrino Nanotechnologies Co., Iran. Ferrous chloride tetrahydrate (FeCl₂·4H₂O, 99%), ferric chloride hexahydrate (FeCl₃·6H₂O, 99%), sodium hydroxide (NaOH), concentrated nitric acid (HNO₃, 68% v/v), and concentrated sulfuric acid (H₂SO₄, 98% v/v) were purchased from Merck Co. Ltd., Germany. Poly (ethylene glycol) bis-amine (NH₂-PEG-NH₂, MW: 1500), folic acid, N-hydroxysuccinimide (NHS), and dicyclohexylcarbodiimide (DCC) were obtained

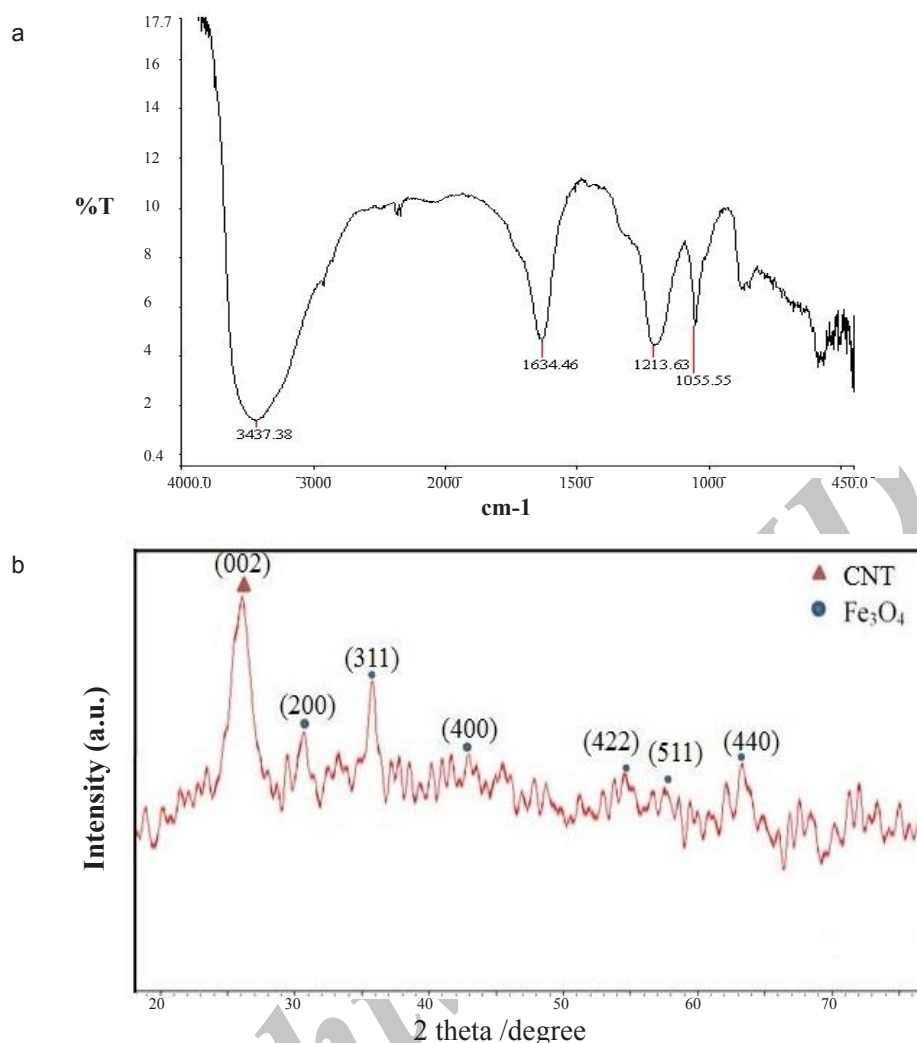


Figure 3. (a) FTIR spectrum of c-SMWCNT, and (b) XRD patterns of c-SMWCNT@Fe₃O₄

from Sigma (St. Louis, MO).

Methods

Functionalizing carboxylic acid on SMWCNTs

Briefly, 90 mL of concentrated H₂SO₄ was added to 1 g of raw SMWCNT under stirring. Subsequently, 30 mL of concentrated HNO₃ was added drop-wise to the mixture under sonication. The resulting mixture was refluxed at 110°C in an oil bath for 12 h. After dilution with 5-fold water, the solution was filtered through a paper filter (Whatman 42) to remove any unreacted bulk of CNTs. The added water was evaporated to almost reach the previous volume (120 mL) (10, 14-16).

Neutralizing the solution acidity by base

In the previous work, magnetization method of carbon nanotubes was explained, a summary of which is given below. The remainder acid could be neutralized with sodium hydroxide in 50 wt% aqueous solution to form sodium sulfate and sodium nitrate salts and water as the end products of the reaction. After reaching pH value up to 11, the mixture containing carboxylated SMWCNTs (c-SMWCNTs) was ready for the attachment of Fe₃O₄ nanoparticles (16).

Attaching Fe₃O₄ nanoparticles to c-SMWCNT

First, FeCl₃•6H₂O (420 mg) was dissolved in the mixture under sonication. Then, FeCl₂•4H₂O

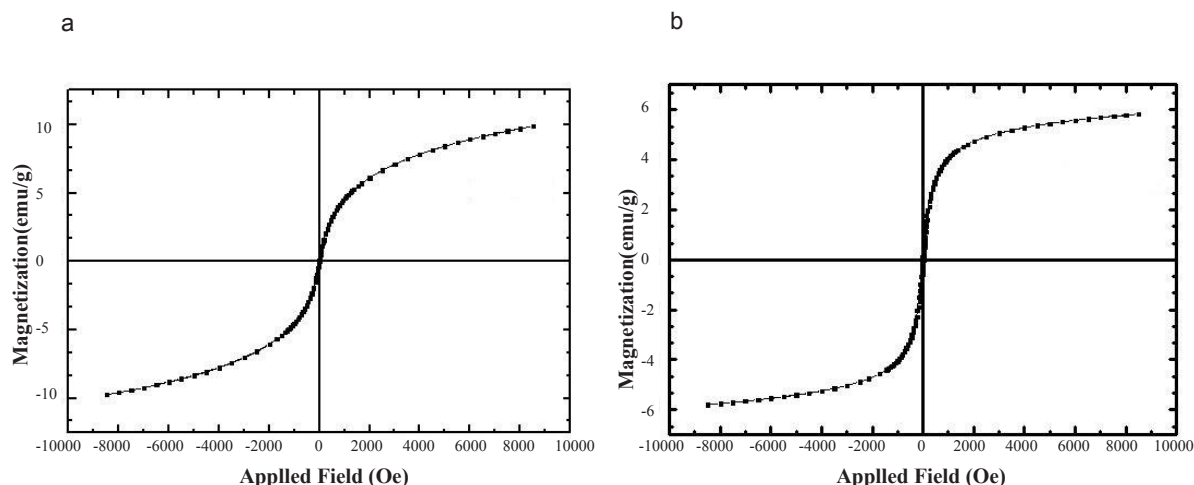


Figure 4. Magnetization curves of (a) Fe_3O_4 nanoparticles, and (b) $\text{c-SMWCNT@Fe}_3\text{O}_4$

(153 mg) was dissolved in 6 mL deionized water and added drop-wise to the final mixture under vigorous stirring and nitrogen atmosphere at 80°C . After aging for 15 min at the same temperature, the mixture was cooled down to room temperature under stirring. Then, the product was collected using a strong magnet and washed with deionized water for several times until reaching the pH value of about 7 (16-20).

Preparing PEG-FOL conjugate

In order to activate folic acid carboxylic groups by NHS and DCC, 110 mg of folic acid was dissolved in DMSO (5 mL). After dissolving NHS (57 mg), DCC (100 mg), and PEG-bis-amine (50 mg) in triethylamine (50 mL), the mixture was stirred under nitrogen atmosphere at room temperature in dark for 24 h. Stoichiometric molar ratio of FA/DCC/NHS was 1:2:2. Unreacted triethylamine was removed by a rotary evaporator and the resulting product was diluted with 15 mL of deionized water and dialyzed against deionized water for several times (Spectra Por 6, MW cut off=1000) and then freeze-dried. Synthesis scheme of PEG-FA conjugate is shown in (Figure 1(a)) (5, 14).

Fabricating PEG-FA-SMWCNTs@ Fe_3O_4

First, carboxylic acid groups of 70 mg $\text{c-SMWCNTs@Fe}_3\text{O}_4$ dissolved in 10 mL of phosphate buffer solution (50 mM, pH 6.0) were activated by 160 mg of DCC and 115 mg of NHS at room temperature in dark under nitrogen atmosphere for 6 h. PEG-FA (180 mg)

was then added to the final mixture for coupling with $\text{c-SMWCNTs@Fe}_3\text{O}_4$ at room temperature in dark under nitrogen atmosphere for 20 h. Finally, the product was collected by magnetic separation, followed by three times of washing with deionized water and lyophilized. The synthetic scheme is described in Figure 1(b) (5, 10-12).

Results and discussion

SEM images of c-SMWCNT and $\text{c-SMWCNT@Fe}_3\text{O}_4$ are shown in Figures 2(a) and 2(b). It is obvious that Fe_3O_4 nanoparticles successfully attached to the side walls of c-SMWCNT and $\text{c-SMWCNT@Fe}_3\text{O}_4$ was formed (Figure 2(b)).

FTIR spectra of c-SMWCNTs are demonstrated in. Stretching C=O and C-O vibration at 1594.89 and 1213.63 cm^{-1} and strong stretching peaks of O-H at 3396.21 cm^{-1} indicated that carboxylic acid functional group was generated on the CNT surface (Figure 3(a)).

XRD pattern of decorated c-SMWCNTs with Fe_3O_4 NPs is illustrated in (Figure 3(b)). Diffraction peak at $2\theta=25.99^\circ$ was ascribed to the reflection of (200) plane of CNT, while the peaks at $2\theta=30.17^\circ$, 35.76° , 42.87° , 53.60° , 57.52° , and 63.35° were related to the (220), (311), (400), (422), (511), and (440) planes of the cubic Fe_3O_4 phase of inverse spinel structure (17-19).

Typical room-temperature magnetization curves of magnetic Fe_3O_4 nanoparticles (a) and $\text{c-SMWCNT@Fe}_3\text{O}_4$ (b) are demonstrated in

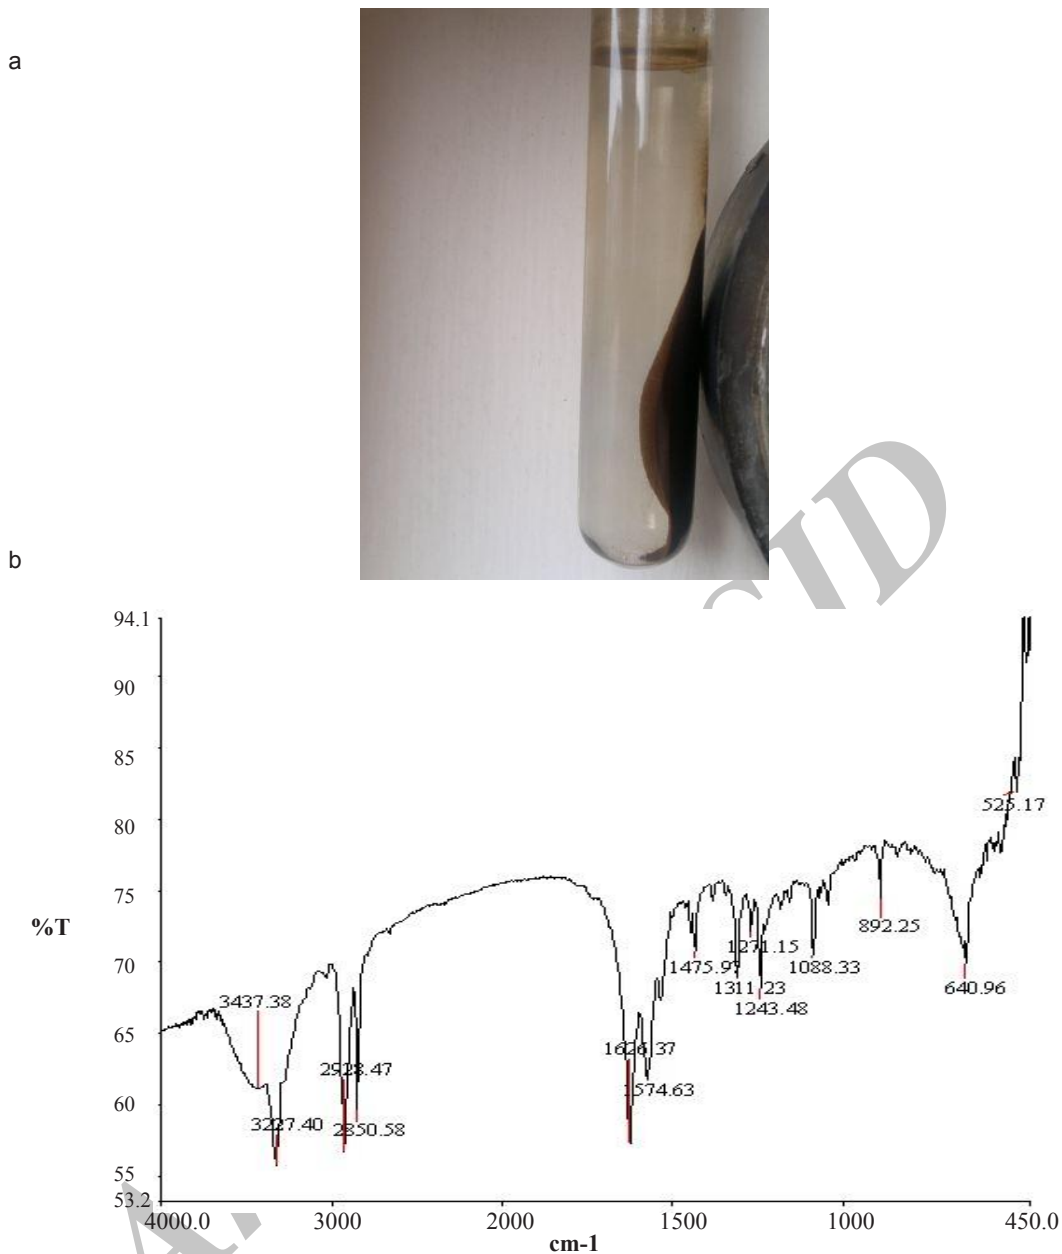


Figure 5. (a) Image of PEG-FA-SMWCNT@Fe₃O₄ with external magnetic field, (b) FTIR spectra of PEG-FA-SMWCNT@Fe₃O₄

Figures 4(a) and 4(b). Saturation magnetization of the pure Fe₃O₄ and c-SMWCNT@Fe₃O₄ was 9.86 and 5.83 emu/g, respectively. It can be observed that the saturation magnetization of c-SMWCNT@Fe₃O₄ was comparatively less than that of pure Fe₃O₄ nanoparticles, which could be attributed to the presence of CNTs in c-SMWCNT@Fe₃O₄ sample. The curves exhibited zero remanence and coercivity, which proved that both Fe₃O₄ nanoparticles and

c-SMWCNT@Fe₃O₄ had super-paramagnetic properties.

Since all purification steps were carried out by a strong magnet, all the unreacted folic acid and polyethylene glycol were removed (Figure 5a). Fe₃O₄ attached to c-SMWCNT was already proven. Consequently, by observing few absorption peaks in FTIR spectra corresponding to folic acid and polyethylene glycol, binding of PEG-FA to SMWCNTs@

Fe_3O_4 could be confirmed.

The band at 3437.38 cm^{-1} belonged to hydroxyl (O-H) stretching, while the absorption peak at 1475.97 cm^{-1} was attributed to the characteristic absorption band of phenyl ring. The bands at 2928.47 and 2850.58 cm^{-1} corresponded to C-H stretching vibrations, while the band at 1626.37 cm^{-1} belonged to C=O bond stretching vibration. Moreover, the bands at 1574.63 and 3227.40 cm^{-1} belonged to the bending and stretching modes of N-H vibration, respectively. The absorption peak at 1088.33 cm^{-1} was related to the stretching vibration of the C-O-C vibration of PEG (20-22). Concurrence of Fe_3O_4 infrared absorption peaks at 525.17 and 640.96 cm^{-1} (Figure 5 b), which shifted to higher wave numbers, confirmed that Fe_3O_4 attached to PEG-FA-SMWCNT and PEG-FA-SMWCNT@ Fe_3O_4 was formed.

Previous studies have approved the concept of forming NPs with a steric PEG barrier which could prevent their rapid uptake by mononuclear phagocyte system and promote their circulatory half-life (12, 16). More recent investigations have demonstrated that rapid RES uptake of NPs could be significantly reduced by changing their surface with poly (ethylene glycol) (PEG). PEG-modified NPs that are mostly prepared using a di-block copolymer of PLGA-b-PEG, liposome-PEG, dendrimer-PEG as an additive considerably prolong their half-life in the circulation owing to the presence of highly mobile and flexible PEG chains on the surface (16). Thus, the main reason for the attachment of PEG, FOL, and iron to carbon nanotubes could be preparing a novel nanocarrier with surface modification which could increase the potential for delivering anticancer drugs to the tumor site. This finding is in line with those of previous works (10, 12, 16, 23).

Conclusions

This study focused on functionalizing carboxylic acid groups on SMWCNTs (c-SMWCNTs), neutralizing the remainder acid of the solution by NaOH base to reach a pH value of up to 11, decorating c-SMWCNTs with magnetite (Fe_3O_4) nanoparticles (c-SMWCNTs@ Fe_3O_4), and functionalizing c-SMWCNTs@

Fe_3O_4 with PEG-Folic acid conjugated (PEG-FA-SMWCNTs@ Fe_3O_4). In accordance with obtained results success of the fully efficient, simple, and short-term method in attaching Fe_3O_4 to the surface of carbon nanotubes was confirmed using scanning electron microscopy, Fourier transform infrared spectroscopy, and X-ray diffraction spectroscopy. FTIR analysis also was used to investigate the link between PEG-FA and SMWCNTs@ Fe_3O_4 . This purposed nanocarrier has potential for future study in drug targeting.

Acknowledgment

The authors would like to thank Research Council of the Mazandaran University of Medical Sciences for their support.

References

- (1) Krehula S and Musić S. A novel route for the synthesis of nanosize particles of metallic palladium. *Materials Letters*. (2008) 62:4369-70.
- (2) Chen R, Choudhary P, Schurr RN, Bhattacharya P, Brown JM and Chun Ke P. Interaction of lipid vesicle with silver nanoparticle-serum albumin protein corona. *Appl. Phys. Lett*. (2012) 100:13703-137034.
- (3) Rostamizadeh S, Shadjou N, Azad Mand Jalali N. ($\alpha\text{-Fe}_2\text{O}_3$)-MCM-41 as a magnetically recoverable nanocatalyst for the synthesis of pyrazolo[4,3-c]pyridines at room temperature. *Catal. Commun.*(2012) 26:218-24.
- (4) Hinow PandBoczko EM. Molecular seismology: an inverse problem in nanobiology. *J. Theor. Biol.* (2007) 246:145-58.
- (5) Ebrahimnejad P, Dinarvand R, Sajadi A, Jaafari MR, Nomani AR, Azizi E, Rad-Malekshahi MandAtyabi F. Preparation and *in-vitro* evaluation of actively targetable nanoparticles for SN-38 delivery against HT-29 cell lines. *Nanomedicine*. (2010) 6:478-85.
- (6) Vaidyanathan R, Kalishwaralal K, Gopalram Sand Gurunathan S. RETRACTED: Nanosilver—The burgeoning therapeutic molecule and its green synthesis. *Biotechnol. Adv.*(2009) 27:924-37.
- (7) El Maghraby GM, Barry BW and Williams AC. Liposomes and skin: from drug delivery to model membranes. *Eur.J.Pharm. Sci.* (2008) 34:203-22.
- (8) Eldar-Boock A, Miller K, Sanchis J, Lupu R, Vicent MJ and Satchi-Fainaro R. Integrin-assisted drug delivery of nano-scaled polymer therapeutics bearing paclitaxel. *Biomaterials*. (2011) 32:3862-74.
- (9) Hari B, Kalaimagal K, Porkodi R, Gajula PK and Ajay J. Dendrimer: Globular nanostructured materials for drug delivery. *Int. J. PharmTech.Res.*(2012) 4:432-51.
- (10) Li R, Wu Ra, Zhao L, Hu Z, Guo S, Pan X and Zou

- H. Folate and iron difunctionalized multiwall carbon nanotubes as dual-targeted drug nanocarrier to cancer cells. *Carbon*. (2011) 49:1797-805.
- (11) Singh P, Gupta U, Asthana Aand Jain NK. Folate and folate-PEG-PAMAM dendrimers: synthesis, characterization, and targeted anticancer drug delivery potential in tumor bearing mice. *Bioconjug. Chem*. (2008) 19:2239-52.
- (12) Zhang Z, Huey Lee Sand Feng SS. Folate-decorated poly(lactide-co-glycolide)-vitamin E TPGS nanoparticles for targeted drug delivery. *Biomaterials*. (2007) 28:1889-99.
- (13) Xu Z, Gu W, Huang J, Sui H, Zhou Z, Yang Y, Yan Zand Li Y. *In-vitro* and *in-vivo* evaluation of actively targetable nanoparticles for paclitaxel delivery. *Int. J. Pharm.* (2005) 288:361-8.
- (14) Modi CD, Patel SJ, Desai ABand Murthy R. Functionalization and evaluation of PEGylated carbon nanotubes as novel drug delivery for methotrexate. *J. Appl. Pharm. Sci.* (2011) 1:103-08.
- (15) Montes-Fonseca SL, Orrantia-Borunda E, Aguilar-Elguezabal A, Gonzalez Horta C, Talamas-Rohana Pand Sanchez-Ramirez B. Cytotoxicity of functionalized carbon nanotubes in J774A macrophages. *Nanomedicine*. (2012) 8:853-9.
- (16) Ebrahimnejad P, Jafari M and Heidari D. An Efficient Method for Fabrication of Carboxylated Short Multi-walled Carbon Nanotubes Decorated with Magnetic Iron Oxide Nanoparticles. *Curr. Nanosci.* (2013) 9:615-18.
- (17) Fei C, Zhang Y, Yang Z, Liu Y, Xiong R, Shi Jand Ruan X. Synthesis and magnetic properties of hard magnetic (CoFe₂O₄)-soft magnetic (Fe₃O₄) nano-composite ceramics by SPS technology. *J. Magn. Magn. Mater.* (2011) 323:1811-16.
- (18) Wang X, Zhao Z, Qu J, Wang Zand Qiu J. Fabrication and characterization of magnetic Fe₃O₄-CNT composites. *J. Phys. Chem. Solids*. (2010) 71:673-76.
- (19) Li J-h, Hong R-y, Luo G-h, Zheng Y, Li H-zand Wei D-g. An easy approach to encapsulating Fe₃O₄ nanoparticles in multiwalled carbon nanotubes. *New. Carbon. Mater.* (2010) 25:192-98.
- (20) Chen Z, Xu R, Zhang Yand Gu N. Effects of proteins from culture medium on surface property of silanes-functionalized magnetic nanoparticles. *Nanoscale. Res. Lett.* (2009) 4:204-09.
- (21) Stevanović M, Radulović A, Jordović Band Uskoković D. Poly (DL-lactide-co-glycolide) nanospheres for the sustained release of folic acid. *J. Biomed. Nanotechnol.* (2008) 4:349-58.
- (22) Shen Y, Tang J, Nie Z, Wang Y, Ren Yand Zuo L. Preparation and application of magnetic Fe₃O₄ nanoparticles for wastewater purification. *Sep. Purif. Technol.* (2009) 68:312-19.
- (23) Tripathi A, Gupta Rand Saraf SA. PLGA nanoparticles of anti tubercular drug: drug loading and release studies of a water in-soluble drug. *Int. J. Pharm. Tech. Res.* (2010) 2:2116-23.

This article is available online at <http://www.ijpr.ir>