

Swelling kinetics study of hydrolyzed carboxymethylcellulose-poly (sodium acrylate-co-acrylamide) superabsorbent hydrogel with salt-sensitivity properties

M. Sadeghi*

Department of Chemistry, Science Faculty, Islamic Azad University, Arak Branch, Arak, Iran

G. Koutchakzadeh

Department of Chemistry, Science Faculty, Islamic Azad University, Khoramabad Branch, Khoramabad, Iran

Abstract

In this work, we have focused on study of swelling kinetics and salt-sensitivity behavior of a superabsorbing hydrogel based on carboxymethylcellulose (CMC) and polyacrylonitrile (PAN). The physical mixture of CMC and PAN was hydrolyzed by NaOH solution to yield hydrogel, CMC-poly (sodium acrylate-co-acrylamide). The swelling kinetics of the hydrogels with various particle sizes was preliminary investigated as well. The swelling of the hydrogel showed a second order kinetics of swelling in water. In addition, swelling measurements of the synthesized hydrogels in various chloride salt solutions was measured. Results indicated that a swelling-loss with an increase in the ionic strength of the salt solutions.

Keywords: Hydrogel; Carboxymethylcellulose; Polyacrylonitrile; Swelling kinetics.

Introduction:

In recent years, increasing interest in natural-based superabsorbent hydrogel has developed mainly due to high hydrophilicity, biocompatibility, non-toxicity, and biodegradability of biopolymers. These materials are defined as crosslinked macromolecular networks that can absorb water or physical fluids up to many times of their own weight in a short time, but are not dissolved when brought into contact with water^[1]. Because of excellent characteristics, superabsorbent hydrogels are widely used in many fields, such as agricultural and horticultural, disposable diapers, feminine napkins, pharmaceuticals and medical applications^[2-4]. Hence, synthesis and investigation of specific and new superabsorbent hydrogels with high absorbency, mechanical strength and initial absorption rate, has been the goal of several research groups in the past decades^[5-8].

Because of their exceptional properties, i.e. biocompatibility, biodegradability, renewability, and non-toxicity, polysaccharides are the main part of the natural-based

* Corresponding author

superabsorbent hydrogels. Carboxymethylcellulose (CMC), an anionic water-soluble polysaccharide, is important modified cellulose which is used in various fields such as detergent, food, paper and textile industries.

To the best of our knowledge based on a precise survey of the Chemical Abstracts, there is no published report on the synthesis of a superabsorbing hydrogel via alkaline hydrolysis of CMC-polyacrylonitrile physical mixture. Hence, the objectives of this study were to synthesis and investigate swelling kinetics of a superabsorbent hydrogel made of CMC and polyacrylonitrile.

Experimental:

A general one step preparative method for synthesis of carboxymethylcellulose-poly (sodium acrylate-co-acrylamide) [CMC-poly(NaAA-co-AAm)] hydrogel was conducted as follows. CMC (0.50g) was added to a three-neck reactor equipped with a mechanical stirrer (Heidolph RZR 2021, three blade propeller type, 300 rpm), including 35 mL doubly distilled water. The reactor was immersed in a thermostated water bath. After complete dissolution of CMC to form a homogeneous solution, certain weight percent of sodium hydroxide (10.0 wt %) was added to the CMC solution at 80 oC. The mixture was allowed to stir for 60 min. The polyacrylonitrile (1.50 g) was dispersed in the reaction mixture to saponify. During the saponification NH₃ gas was evolved and a color change from red to light yellow. This discoloration was an indication of the reaction completion. The pasty mixture was allowed to cool to room temperature and neutralized to pH 8.0 by addition of 10 wt % aqueous acetic acid solution. Then the gelled product was scissored to small pieces and poured in methanol (200 mL) to dewater for 5 h. The hardened particles were filtered and dried in oven (50 oC, 10 h). After grinding, the powdered superabsorbent hydrogel was stored away from moisture, heat and light.

Results and Discussion

Swelling behavior in salt solutions

The swelling capacity of superabsorbent hydrogels could be significantly affected by various factors of the external solutions such as its valencies and salt concentration. The presence of ions in the swelling medium has a profound effect on the absorbency behavior of the superabsorbent hydrogels. Many theories were reported in the case of swelling behavior of ionic hydrogels in saline solutions. The simplest one of the theories is Donnan equilibrium theory. This theory attributes the electrostatic interactions (ion swelling pressure) to the difference between the osmotic pressure of freely mobile ions in the gel and in the outer solutions. The osmotic pressure is the driving force for swelling of superabsorbents. Increasing the ionic mobile ion concentration difference between the polymer gel and external medium which, in turn, reduces the gel volume, i.e. the gel shrinks and swelling capacity decreases (charge screening effect). In addition, in the case of salt solutions with multivalent cations, "ionic crosslinking" at surface of particles causing an appreciably decrease in swelling capacity. For example, Castel et al. reported that calcium ion can drastically decrease the swelling capacity for a hydrolyzed starch-graft-polyacrylonitrile, due to the complexing ability of the carboxylate group to include the formation of intra- and inter-molecular complexes^[9].

The effect of charge of cation on swelling can be concluded from Figure 1. With increasing the charge of cation, degree of crosslinking is increased and swelling is consequently decreased.

Figure 1 also shows the swelling capacity of the hydrogel, [CMC–poly(NaAA-co-AAm)], as a function of the salt concentration for NaCl, CaCl₂, and AlCl₃ solutions. The results reveal that the swelling ratio decreases as the salt concentration of the medium increases. The known relationship between swelling and concentration of salt solution is stated as following equation^[10]:

$$\text{Swelling} = k [\text{salt}]^{-n} \quad (1)$$

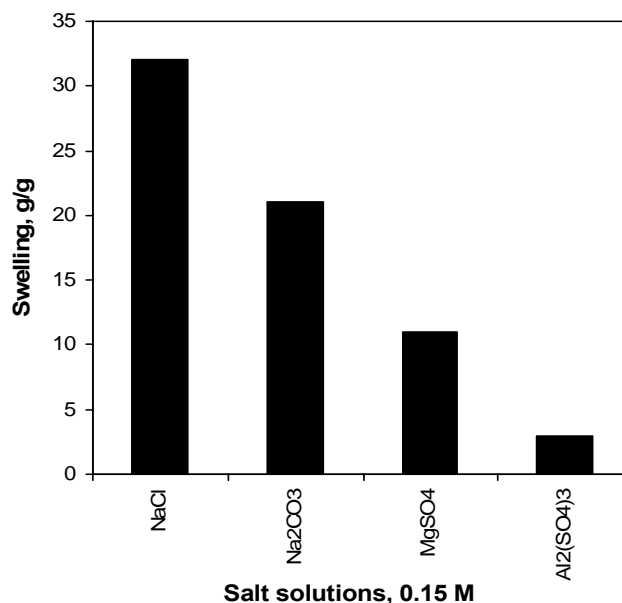


Figure 1. Swelling capacity variation of the CMC–poly(NaAA-co-AAm) superabsorbent in saline solutions with various concentrations.

where k and n are constant values for an individual superabsorbent. The k value is swelling at a high concentration of salt and n value is a measure of salt sensitivity. While the k values are almost the same (~ 8) for the swelling in various salt solutions the n values are totally different (Table 1). As given in Table 1, the n values are proportionally increases with the cation valency enhancement. These results imply that the effect of the ionic crosslinking acts as more effective factor against swelling rather than the charge screening effect of the cation.

TABLE I
k and n Values^a for the CMC–poly(NaAA-co-AAm) Hydrogel

Swelling medium	k	n
NaCl	8.3	0.38
CaCl ₂	8.2	0.48
AlCl ₃	8.4	0.53

^a Obtained from curve fitting (Fig. 1).

The results shown in Figure 2 indicate that the absorbency for the CMC–poly(NaAA-co-AAm) hydrogels in various salt solutions decreased with the increasing ionic strength of the salt solution. The effect of the ionic strength on water absorbency has been determined using the relation suggested by Hermans ^[11]:

$$Q_{5/3}(eq) = A + B \sqrt{I} \quad (2)$$

which $Q_{5/3}(eq)$ is the equilibrium water absorbency, I is the ionic strength of the external solution, and A and B are the empirical parameters. At low ionic strengths, the concentration of bound charges within the hydrogel network exceeds the concentration of salt in the external solutions, a large ion-swelling pressure causes the hydrogel to expand, thereby lowering the concentration of ions within the hydrogel. As the external salt concentration rises, the difference between the internal and external ion concentration decreases and the hydrogel deswells. The hydrogel continues to deswell with increasing external salt concentration until the mobile-ion concentrations inside and outside are approximately equal. These phenomena can also be explained on the basis of repulsion between fixed charged groups on the hydrogel. As ionic strength increases, repulsion is shielded and the hydrogel deswells (charge screening effect).

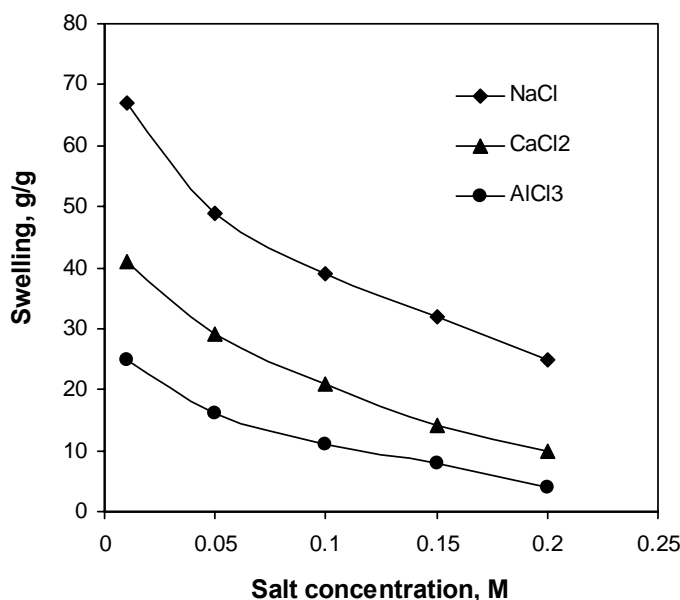


Figure 2. Effect of the ionic strength of salt solutions on the swelling capacity of the CMC–poly(NaAA-co-AAm) hydrogel.

Swelling kinetics studies

In practical applications, a higher swelling rate is required as well as a higher swelling capacity. It is well known that the swelling kinetics for the absorbents is significantly influenced by factors such as swelling capacity, size distribution of powder particles, specific surface area and composition of polymer. The influences of these parameters on the swelling capacity have been investigated by various workers ^[12, 13]. For example, the dependency of water absorbency of superabsorbent polymers on particle size investigated by Omidian et al. ^[14]. Results indicated that as the particle size became smaller, the rate of absorption increased. This may be attributed to an increase in surface area with decreasing particle size of samples.

Results in Figure 3 that shown the dynamic swelling behavior of the superabsorbent hydrogel with various particle sizes in water, confirm this fact.

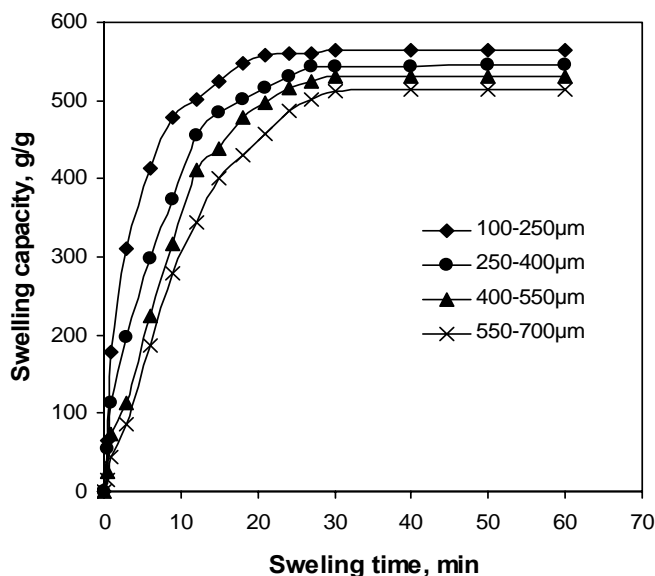


Figure 3. Representative swelling kinetics of the CMC–poly(NaAA-co-AAm) superabsorbent hydrogel with various particle sizes.

According to the figure, the rate of water absorbency sharply increases and then begins to level off. For preliminary study of swelling kinetics, a "Voigt-based model" may be used for fitting the swelling data (Eq. 3) [15]:

$$S_t = S_e (1 - e^{-t/\tau}) \tag{3}$$

where S_t is the swelling at time t , S_e is the equilibrium swelling (power parameter) and τ is the rate parameter. The τ value is a measure of swelling rate (i.e. the lower the τ value, the higher the rate of swelling). For calculate the rate parameter, by using the above formula and a little rearrangement, one can be plot $Ln(1 - S_t/S_e)$ versus time (t). The slope of the straight line fitted (slope = $-1/\tau$) gives the rate parameter. The rate parameters for superabsorbent are found to be 4.2, 8.4, 10.5, and 11.3 min for superabsorbent with particle sizes of 100-250, 250-400, 400-550, and 550-700 μm , respectively. According to the smaller τ value, the swelling of the superabsorbent with 100-250 μm particle sizes is faster than other counterparts.

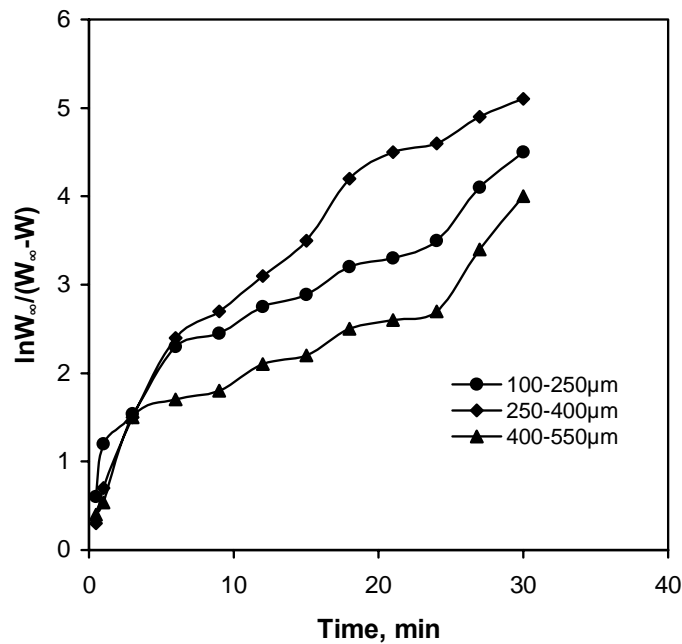


Figure 4. Plot of $\ln(W_{\infty}/(W_{\infty}-W))$ versus time, according to Eq. 5 (first order kinetics) for the superabsorbent hydrogels with different particle sizes.

We analyzed the swelling kinetics in order to find out whether swelling follows first or second order kinetics. We adopted the procedure followed by Quintana et al. [16]. For the first order kinetics, rate of swelling at any time is proportional to the water content before the equilibrium absorbed water (W_{∞}) has been reached. The swelling can be expressed as Eq. 4:

$$\frac{dW}{dt} = K(W_{\infty} - W) \quad (4)$$

where W is the water content of the superabsorbent at time t and K is a constant.

Upon integration of Eq. 4 between the limits $t=0$ to t and $W=0$ to W , the following expression can be obtained:

$$\ln \frac{W_{\infty}}{W_{\infty} - W} = Kt \quad (5)$$

If the swelling process of superabsorbent follows a first order kinetics, the plot of the variation of $\ln(W_{\infty}/(W_{\infty}-W))$ as a function of time should give a straight line. But none of the swelling studies in water followed Eq.5, as is clear from Figure 4.

Considering the second order kinetics, the swelling rate at any time may be expressed as Eq. 6:

$$\frac{dW}{dt} = K(W_{\infty} - W)^2 \quad (6)$$

Integration Eq. 6 with the limits $t=0$ to t and $W=0$ to W and after rearrangement, the following equation is obtained:

$$\frac{t}{W} = \frac{1}{KW_{\infty}^2} + \frac{1}{W_{\infty}}t \quad (7)$$

According to this equation, the swelling data must fit a straight line with a slope of $1/W_{\infty}$ and an ordinate of $1/KW_{\infty}^2$. The variation of t/W against time is plotted in Figure 5. It was found that swelling data of superabsorbent in water gives straight lines. So, the swelling of the synthesized superabsorbent composites with various particle sizes obey second order kinetics.

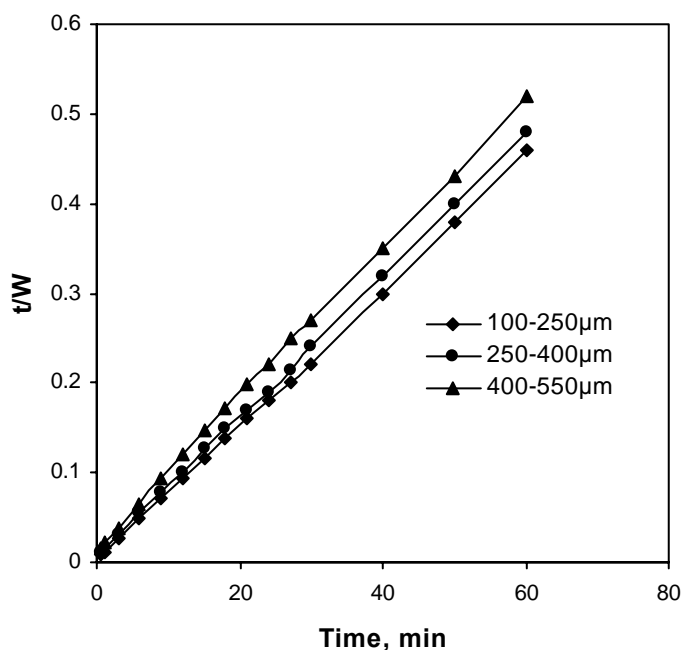


Figure 5. Plot t/W -time according to Eq. 7 (second order kinetics) for superabsorbent hydrogels with various particle sizes.

Conclusions

A novel superabsorbent hydrogel was synthesized in an aqueous solution by alkaline hydrolysis of the physical mixture of CMC and PAN. The reaction of CMC alkoxide anions with nitrile groups of polyacrylonitrile, forms crosslinking points and results in a three-dimensional network. Swelling measurement in various salt solutions shows a swelling-loss behavior. This behavior can be attributed to charge screening effect and ionic crosslinking for mono- and multi-valent cations, respectively. The swelling kinetics of the synthesized hydrogel was also investigated. The rate of water uptake is increased with decreasing the particle size of the hydrogels. This can be attributed to high surface availability of small particle size of superabsorbing polymers when brought into contact with water. In addition, according to the dynamic rate measurements, the swelling of the hydrogel showed a second order kinetics of swelling in water.

The synthetic approach applied in this paper to prepare the superabsorbent hydrogel comprises several advantages:

The practical one-step method for hydrogel synthesis is relatively simple and easy comparison with free radical graft copolymerization method.

The dark red-yellow color change provides a visual indication for recognizing the reaction completion.

No petrochemical monomer is needed. So, the process is not involved with several problems originated from a monomer (e.g., the monomer toxicity).

No initiator and expensive crosslinking agent is used. Therefore, this practical approach may be preferred to as a relatively "green process".

This facial and convenient preparative method conducted under normal atmospheric conditions in a short period of time. Because this method is not involved radical polymerization, so the expensive inert gases, e.g. argon, aren't needed for remove of molecular oxygen that is a radical scavenger in radical graft copolymerization reactions.

Biopolymeric convenient material, i.e. CMC, is used to yield super-swelling biomaterials with potential bioactivity and biocompatibility.

References:

- 1- Buchholz, F. L. and Graham, A. T., *Modern Superabsorbent Polymer Technology*, Elsevier, Amsterdam, (1997).
- 2- Peppas, L. B, and Harland, R. S., *In Absorbent Polymer Technology*, Elsevier, Amsterdam, (1990).
- 3- Po, R., *J. Macromol Sci Rev Macromol Chem Phys*, **C34**, 607 (1994).
- 4- Hoffman, A. S, *In Polymeric Materials Encyclopedia*; Salamone, J. C., Ed.; CRC Press, Boca Raton, FL, **5**, 3282 (1996).
- 5- Yazdani, P, Yazdani, M., Retuert, J.; and Quijada, R. *Macromol Chem Phys*, **201**, 923 (2000).
- 6- Sugahara, Y. and Takahisa, O. *J Appl Polym Sci*, **82**, 1437 (2001).
- 7- Patel, G. M.and Trivedi, H. C. *Eur Polym J*, **35**, 201 (1999).
- 8- Silong, S.; Rahman, L. *J Appl Polym Sci*, **76**, 516 (2000).
- 9- Castel, D., Ricard, A.and Audebert, R., *J Appl Polym Sci*, **39**, 11 (1990).
- 10- Flory,P. J, *Principles of Polymer Chemistry*; *Cornell University Press*: Ithaca, NY, (1953).
- 11- Hermans, J. J, *In Flow Properties of Disperse Systems*, Wiley Interscience, New York, (1953).
- 12- Kiatkamjorwong, S.; Phunchareon P., *J Appl Polym Sci*, **72**, 1349 (1999).
- 13- Wen-Fu, L.and You-Min, T. *J Appl Polym Sci*, **72**, 1221 (1999).
- 14- Omidian, H., Hashemi, S. A. and Sammes, P. G.; *Meldrum, I. Polymer*, **40**, 1753. (1999).
- 15- Omidian, H., Hashemi, S. A.and Sammes, P. G., *Meldrum, I. Polymer*, **39**, 6697 (1998).
- 16- Quintana J. R. and Valderruten N. E., *Katime I. Langmuir*, **15**, 4728.(1999).