

Effect of pH and calcium salt simultaneous changes on rheological behavior of xanthan gum- carboxymethyl cellulose blends

Sinoush Hemmatzadeh Dastgerdy¹,

1 M. Sc. in Food Science and Technology, National Standard Organization of Iran, Chaharmahal and Bakhtiary Standard Organization, ShahreKord, Iran.
Email: s.hemmatzadeh@yahoo.com

Mohammad Hojjatoleslami²

2 Assistant professor, Dept. of Food Science and Technology, Faculty of Agriculture, Islamic Azad University, ShahreKord branch, Iran.
Email: mohojjat@iaushk.ac.ir

Abstract— Effect of Calcium salt (CaCl₂, 1 and 5 mM) and pH (3, 5 and 7) on rheological properties of xanthan-carboxymethyl cellulose blend solutions have been investigated. Gum solutions in all ratios showed shear thinning flow behavior that was adjusted to the Herschel–Bulkley model. Salt addition and pH decreasing cause apparent viscosity reduction .

Keywords- xanthan gum; carboxymethyl cellulose; steady shear rheology; calcium salt.

I. INTRODUCTION

The term ‘hydrocolloids’ refers to a range of polysaccharides and proteins that are nowadays widely used in a variety of industrial sectors to perform a number of functions including thickening and gelling aqueous solutions, stabilizing foams, emulsions and dispersions, inhibiting ice and sugar crystal formation and the controlled release of flavours, etc.[10]

Xanthan gum is an extracellular polysaccharide secreted by the micro-organism *Xanthomonas campestris*. Xanthan is widely used as a food gum, which makes it unique among food gums. The unusual and very useful properties of xanthan undoubtedly result from the structural rigidity and extended nature of its molecules, which in turn result from its linear, cellulosic backbone, which is stiffened and shielded by the anionic trisaccharide side chains.[1]

Carboxymethylcellulose (CMC) is widely used in many application areas such as food, pharmaceutical, personal care, paper, paint and milling industry.[6]

The rheological properties of gums are particularly important when they are used in the formulation of any food for its effect on the textural attributes. The rheological properties of fluid food should be carefully taken into account for designing and modeling purposes. [14]

There are several studies on rheological properties of gum solution blends in the presence of salts. Molecular conformation of the complex of xanthan–LBG was assessed by the power law and the Huggins equations. Higiro et al.(2006) showed that addition of the salts reduced significantly the intrinsic viscosity and elastic component of the xanthan gum-LBG blends, with a pronounced effect from divalent ions, compared with monovalent ions.[4]

Houryieh et al. demonstrated that intermolecular interaction has occurred between xanthan and guar mixtures

in water and 2 mM NaCl, but may not occur in 40 mM NaCl.[5]

In previous works, effect of pH on rheological properties of gum solutions in the presence of salts, had not been investigated.[2,3,4,5,6,8,9,13 and 14]

The objective of this study was to investigate the effect of the simultaneous changes of pH and calcium salt on rheological behavior of xanthan gum- carboxymethyl cellulose blends.

II. MATERIALS AND TEST METHODS

Xanthan gum and carboxymethyl cellulose were purchased from Sigma (Sigma–Aldrich, St. Louis, MO). The stock solutions (0.1% m/v) were prepared by mixing 0.1 g of dry sample with deionized distilled water while continuously stirring at ambient temperature. The gum solutions were continuously stirred with a magnetic stirrer for 2 h at ambient temperature and were heated for 1 h at 80 °C in a water bath to completely hydrate the gums. The solutions were refrigerated for one night (16 h) to completely hydrate the gums. To study rheological properties of gum blends, the following treatments were considered: xanthan 100%, xanthan 75%–CMC 25%, xanthan 50%–CMC 50%, xanthan 25%–CMC 75%, and CMC 100%. Stock solutions were stirred at room temperature. Prepared xanthan and CMC solutions were mixed at 25 °C, and were stirred with a magnetic stirrer for 10 min. To study the effect of pH, the rheological properties were measured at neutral and acidic (5 and 3) pH values. A pH meter (Metrohm, France) and 1N HCl solution were applied for adjusting pH values. To study the effect of salt on the polysaccharide solutions, the appropriate amounts of calcium chloride were added to the prepared solutions of and were completely dissolved to obtain final concentrations of 1 and 5 mM CaCl₂. For rheological properties determination Brookfield rheometer¹ (LV DV III) equipped by ULA² and rheocalc³ software were used. All Rheological measurements were carried out at 25 °C by using a temperature-controlled circulating water bath⁴.

1- Brookfield engineering. INC, Middle Boro, MA02346 USA.

2- ULA-EY UL Adaptor

3- Rheocalc V3.2 Build 47-1

4- Brookfield engineering, TC 502

III. RESULTS AND DISCUSSION

Several models have been used to characterize the flow behavior of gum solutions and among them Power law model has been frequently used for the determination of rheological properties of the fluid food (Eq. (1)). In addition, Casson equation (Eq. (2)) and Herschel–Bulkley model (Eq. (3)) have been also used for the characterization of some gums solutions.[7,11 and12]

$$\sigma = K \dot{\gamma}^n \quad (1)$$

$$\sigma^{0/5} = K_1 \dot{\gamma}^{0/5} + \sigma_0^{0/5} \quad (2)$$

$$\sigma = K \dot{\gamma}^n + \sigma_0 \quad (3)$$

where σ (dyne/cm²) is shear stress, K (dyne sⁿ /cm²) is the consistency coefficient, $\dot{\gamma}$ (s⁻¹) is the shear rate, n (dimensionless) is the flow behavior index, σ_0 (dyne/cm²) is the yield stress and K_1 is plastic viscosity.

Several authors have employed the power law model (Eq. (1)) to describe the viscosity of gum solutions.[3,4 and 8]

Other authors have used the Casson model (Eq. (2)) for rheological description of some gum solutions and in other studies Herschel–Bulkley model has been used.[3 and 8]

It is shown That These three models are the best models for description of rheological properties of gum solutions. In this study these three models was investigated to select the best model to predict accurately the behavior of xanthan-CMC solutions. Rheological parameters under steady shear were measured. All of curves were adjusted to the three models and rheological parameters of the Casson (C), Power-law (PL) and Herschel–Bulkley (HB) models were investigated for description of rheological behaviour of xanthan–CMC blends in all ratios at pH 7, 5 and 3 before and after adding calcium salt (1 and 5 mM). All of samples showed high conformity with the three models, and in all treatments the regression coefficient, r^2 ; was not lower than 0.94, But curves were adjusted to the Herschel–Bulkley model (Eq. (2)) by the best-fit regression. In neutral pH and without adding salt, solutions exhibited shear-thinning behavior. Salt addition and pH decreasing induced newtonian behavior and apparent viscosity (AV) reduction. An increase in CMC concentration resulted in lower values of σ_0 and apparent viscosity, and a shift to newtonian behavior.

All of curves were adjusted to the three models and rheological parameters of the Casson (C), Power-law (PL) and Herschel–Bulkley (HB) models were investigated for description of rheological behaviour of xanthan–CMC blends in all ratios at pH 7, 5 and 3 before and after adding calcium salt (1 and 5 mM).

Figs. 1–5 show the apparent viscosity (AV) values of solutions prepared with xanthan gum and CMC. The AV of solutions decreased with increasing CMC concentration.

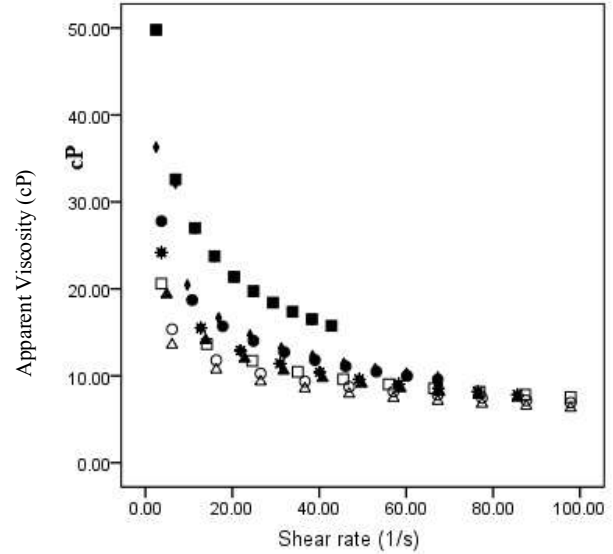


Figure 1. Viscosity as a function of shear rate of xanthan solution at pH 7, 5 and 3 without or with CaCl₂ (1 and 5 mM).

□ pH=3, without salt, ▽ pH=5, without salt, ■ pH=7, without salt
 △ pH=3, 5mM CaCl₂, ◆ pH=5, 1mM CaCl₂, ● pH=7, 1mM CaCl₂
 ○ pH=3, 1mM CaCl₂, * pH=5, 5mM CaCl₂, ▲ pH=7, 5mM CaCl₂

The highest AV value was observed for xanthan solutions that contained no CMC, at pH 7 without adding CaCl₂ salt (Fig. 1).

Fig. 2 shows that CMC solutions exhibit shear-thinning behaviour in low shear rates whereas at pH 3 or in the presence of 5 mM calcium ions, the AV of solutions increased slightly in high shear rate values due to increasing molecular interactions in these conditions.

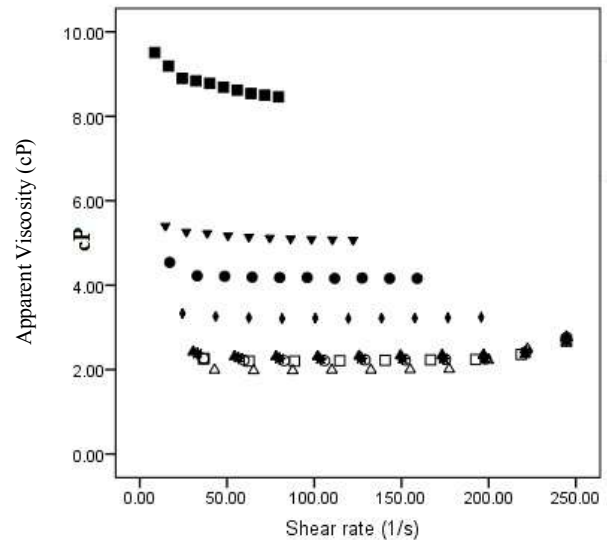


Figure 2. Viscosity as a function of shear rate of CMC solution at pH 7, 5 and 3 without or with CaCl₂ (1 and 5 mM).

□ pH=3, without salt, ▽ pH=5, without salt, ■ pH=7, without salt
 △ pH=3, 5mM CaCl₂, ◆ pH=5, 1mM CaCl₂, ● pH=7, 1mM CaCl₂
 ○ pH=3, 1mM CaCl₂, * pH=5, 5mM CaCl₂, ▲ pH=7, 5mM CaCl₂

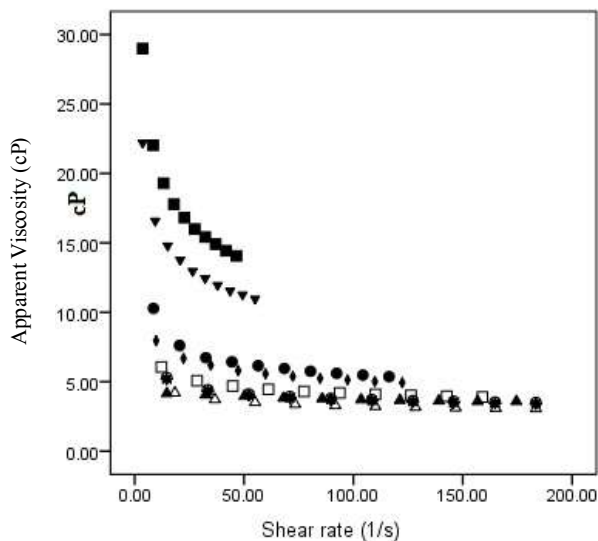


Figure 3. Viscosity as a function of shear rate of xanthan- CMC solutions (75/25) at pH 7, 5 and 3 without or with CaCl_2 (1 and 5 mM).
 □ pH=3, without salt, ▼ pH=5, without salt, ● pH=7, without salt
 △ pH=3, 5mM CaCl_2 , ◆ pH=5, 1mM CaCl_2 , ○ pH=7, 1mM CaCl_2
 ○ pH=3, 1mM CaCl_2 , * pH=5, 5mM CaCl_2 , ▲ pH=7, 5mM CaCl_2

Fig 3-5 show the effect of different ratios of gum solution blends on the AV of solutions in different experimental conditions. The results demonstrated that all solutions showed a non-Newtonian flow in which AV changed with shear rate. AV values of sample solutions decreased with increasing shear rate, thus solutions exhibited a shear thinning behavior. The addition of xanthan caused an increase in the AV values of the solution.

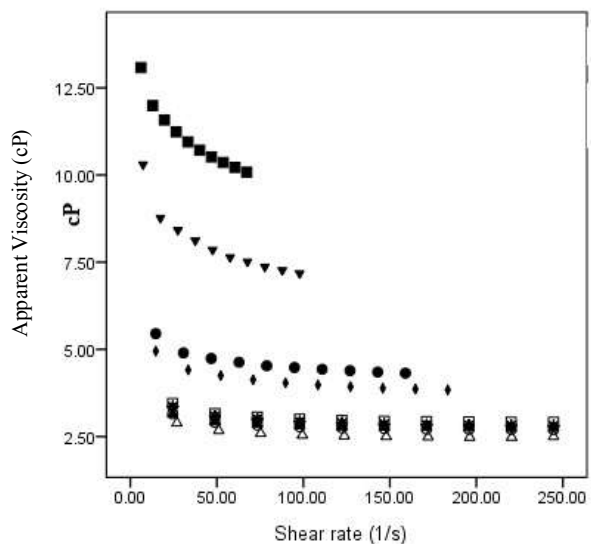


Figure 5. Viscosity as a function of shear rate of xanthan- CMC solutions (25/75) at pH 7, 5 and 3 without or with CaCl_2 (1 and 5 mM).
 □ pH=3, without salt, ▼ pH=5, without salt, ● pH=7, without salt
 △ pH=3, 5mM CaCl_2 , ◆ pH=5, 1mM CaCl_2 , ○ pH=7, 1mM CaCl_2
 ○ pH=3, 1mM CaCl_2 , * pH=5, 5mM CaCl_2 , ▲ pH=7, 5mM CaCl_2

The results demonstrated that when salt is added, charge screening causes the side chains to collapse down to the backbone, hence giving the xanthan molecule a rod-like shape and reducing the hydrodynamic volume. Similar results have been reported by others. [3,4, 5 and 10]

The more pronounced effect of the calcium ions on the apparent viscosity, was possibly due to molecular crosslinking between xanthan and calcium ions, which resulted in a greater extent of molecular contraction.[4]

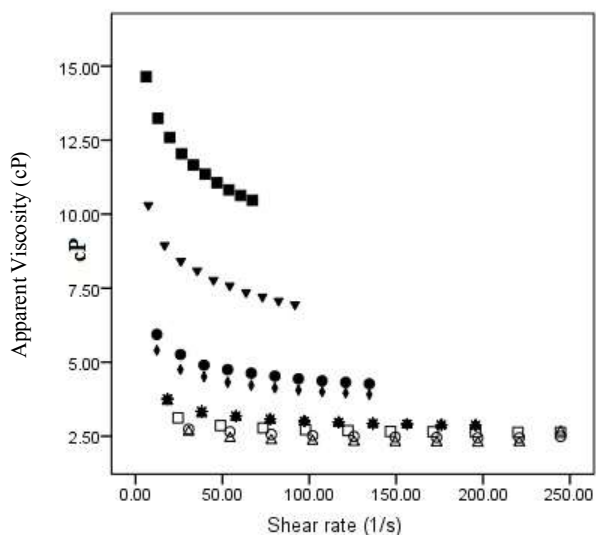


Figure 4. Viscosity as a function of shear rate of xanthan- CMC solutions (50/50) at pH 7, 5 and 3 without or with CaCl_2 (1 and 5 mM).
 □ pH=3, without salt, ▼ pH=5, without salt, ● pH=7, without salt
 △ pH=3, 5mM CaCl_2 , ◆ pH=5, 1mM CaCl_2 , ○ pH=7, 1mM CaCl_2
 ○ pH=3, 1mM CaCl_2 , * pH=5, 5mM CaCl_2 , ▲ pH=7, 5mM CaCl_2

IV. CONCLUSIONS

Xanthan-carboxymethyl cellulose blends in all ratios showed shear thinning flow behavior at 25°C. As the pH value of solutions decreased, a significant decrease in viscosity values was observed. Salt addition in different pH values cause apparent viscosity reduction. Adding salt cause a significant decrease in viscosity values for solutions with higher pH values, due to molecular interactions between xanthan and calcium ions. Gum solutions in all ratios showed shear thinning flow behavior that was adjusted to Casson, Power Law and Herschel–Bulkley models. The results demonstrated that Herschel–Bulkley model is the best model for description of rheological behaviour of xanthan-carboxymethyl cellulose blends in different under study conditions. Results showed that pH variations and salt concentration affect the rheological behavior of xanthan-CMC blends. So the desired function of the gums in the foods is influenced by pH and ionic strength of the food matrix and investigating the effect of other salts and acids is recommended.

V. REFERENCES

- [1] Fennema, O.R. (1996). *Food Chemistry*. Marcel Dekker Inc. New York.
- [2] García-Abuín, A., Gómez-Díaz, D., Navaza, J. M., Quintáns-R. and Lourdes C. (2010). Viscosimetric behaviour of carboxymethyl cellulose – arabic gum mixtures: A new step to modeling. *Carbohydrate Polymers*. 80, 26-30.
- [3] García -Ochoa, F., Santos, V.E., Casas, J.A. and Gomez, E. (2000). Xanthan gum: production, recovery, and properties. *Biotechnology Advances*. 18, 549-579.
- [4] Higiroy, J., Herald, T.J., Alavi and Bean, S. (2006). Rheological study of xanthan and locust bean gum interaction in dilute solution: effect of salt. *Food Research International*. 40, 435-447.
- [5] Khouryieh, H.A., Herald, T.J., Aramouni, F.M. and Alavi, S. (2007). Intrinsic and viscoelastic properties of xanthan / guar mixtures in dilute solutions: effect of salt concentration on the polymer interactions. *Food Research International*. 40, 883-893.
- [6] Larsson, H. (2008). The rheological behavior of weak gels made with a blocky CMC and salt. *Annual transactions of the nordic rheology society*, Vol 16. Copenhagen, Denmark.
- [7] Macosko, C.W. (1994) *Rheology, principles, measurements, and applications*. Wiley-VCH, Inc. New York-USA.
- [8] Martínez-Padilla, L.P., López-Araiza, F. and Tecante, A. (2004). Steady and oscillatory shear behavior of fluid gels formed by binary mixtures of xanthan and gellan. *Food hydrocolloids*, 18, 471-481.
- [9] Nickerson, M. T., Paulson, A.T. and Speers, R. A. (2003). Rheological properties of gellan solutions: effect of calcium ions and temperature on pre-gel formation. *Food hydrocolloids*, 17, 577-583.
- [10] Phillips, G.O. and Williams, P.A. (2000). *Hand book of Hydrocolloids*. CRC Press. New York.
- [11] Rosenthal, A. J. (1999). *Food texture, Measurement and Perception*. Aspen Publishers, Inc.
- [12] Steffe, G.F. (1996). *Rheological methods in food process engineering*. Freeman Press. New York.
- [13] Tako M. and Nakamura S. (1984) Rheological properties of deacetylated xanthan in aqueous media. *Agric Biol Chem* 1984, 12, 2987-93
- [14] Yaseen, E.I., Herald, T.J., Aramouni, F.M. and Alavi, S. (2005). Rheological properties of selected gum solutions. *Food research Int.* 38, 111-119.